



ARCHIVES
of
FOUNDRY ENGINEERING



DOI: 10.1515/afe-2017-0091

ISSN (2299-2944)
Volume 17
Issue 3/2017

Published quarterly as the organ of the Foundry Commission of the Polish Academy of Sciences

59 – 62

Influence of Heat Treatment on Content of the Carbide Phases in the Microstructure of High-Speed Steel

J. Jaworski *, R. Kluz, T. Trzepieciński

Rzeszow University of Technology, al. Powstańców Warszawy 8, 35-959 Rzeszów, Poland

*Corresponding author. E-mail address: jkktmiop@prz.edu.pl

Received 14.03.2017; accepted in revised form 29.06.2017

Abstract

This article presents the results of investigations of the effect of heat treatment temperature on the content of the carbide phase of HS3-1-2 and HS6-5-2 low-alloy high-speed steel. Analysis of the phase composition of carbides is carried out using the diffraction method. It is determined that with increasing austenitising temperature, the intensification of dissolution of M_6C carbide increases. As a result, an increase in the grain size of the austenite and the amount of retained austenite causes a significant reduction in the hardness of hardened steel HS3-1-2 to be observed. The results of diffraction investigations showed that M_7C_3 carbides containing mainly Cr and Fe carbides and M_6C carbides containing mainly Mo and W carbides are dissolved during austenitisation. During austenitisation of HS3-1-2 steel, the silicon is transferred from the matrix to carbides, thus replacing carbide-forming elements. An increase in a degree of tempering leads to intensification of carbide separation and this process reduce the grindability of tested steels.

Keywords: Heat treatment, Metallography, Carbide phase, High-speed steel, Microstructure

1. Introduction

High-speed steel (HSS) is complex iron-based alloy containing carbon, tungsten, molybdenum, vanadium, chromium and substantial amounts of cobalt [1]. To ensure applicable quality requirements during production of tools made of HSSs, it is very important that their cutting ability is not lower than comparable tools made of classic high-speed steels [2].

In the case of cutting tools, the maximum efficiency is determined mainly by hardness, strength and temperability of the tool material [3, 4]. These properties of the tool material can be adjusted within a relatively wide range by the parameters of the heat treatment [5]. Optimum heat treatment parameters ensure that the highest hardness, strength and temperability are achieved at the same time [6]. Determination of the optimum austenitising temperature requires special attention because it regulates a

number of important processes. On the one hand, with an increase in austenitising temperature higher dissolution of secondary carbides is observed, which increases temperability and strength. On the other hand when steel material is overheated to too high a temperature an excessive growth of grains is observed, which increases the amount of retained austenite. However, in the case of smaller carbon content in steel, ferrite can be formed or even part melting of the grain boundaries can occur. HSSs should be used in a state of high hardness, which involves the determination of the optimum temperatures of austenitising and tempering [2, 7-9]. Austenitising temperature of a tool steel set in the process of tool manufacture should produce a grain size determined by the Snyder-Graff of no less than 10, a bending strength of 2500–3000 MPa and a hardness of about 63 HRC.

Microstructural changes occurring in tool during grinding process depend mainly on the chemical composition of material,

thermal treatment and grinding parameters. The investigations of the effect of heat treatment on the coefficient of grinding [1] showed that this coefficient depends more on the fold of tempering than on the austenitization temperature. Both of these parameters determine the number and size of carbide phases leading to a decrease in the coefficient of grinding. The aim of this research is phase analysis and determination of the content of elements in carbide phases in HS3-1-2 and HS6-5-2 steels subjected to different heat treatment conditions.

2. Methods

Analysis of the phase composition of carbides is carried out using the diffraction method. The research material was prepared in the form of isolates containing carbon bound into carbides and unbounded carbon in solid solution. These isolates were obtained by electrolytic dissolution of samples. Conditions of electrolysis and the chemical composition of the electrolyte are shown in Table 1.

The isolate was removed from the sample by ultrasonic method. Then the isolate was washed in a centrifuge and dried in an evaporating dish at 105°C. Isolates were tested using the diffractometer. Copper and chromium lamps with a nickel filter were used. The wavelength of CuK α radiation was $\lambda = 0.229092$ nm. An analysis of the phase composition was performed for both grades of steel after annealing, hardening and tempering at 620°C for 4 hours. The HS3-1-2 steel was hardened at temperatures of 1080°C, 1120°C and 1150°C. The HS6-5-2 steel was hardened at a temperature of 1200°C and tempered at 550°C for 2 hours. The grain size was determined using Snyder-Graff (S-G) intercept method.

Determination of element contents in carbides was carried out via atomic absorption spectrometry (AAS), using a Perkin-Elmer model 503 atomic absorption spectrometer. The AAS method was used to determine the content of Fe, Cr, Mn, W, V, Mn and Si in the HS3-1-2 steel after the heat treatment processes. Isolates were dissolved in a solution of HNO₃ concentrated by 4% solution of NaF in the proportion 1:1, with later addition of hydrofluoric acid. The resulting percentages of elements in the isolate x were converted to percentages in carbides y according to the relationship:

$$a = \frac{x}{b} \cdot 100\% \quad (1)$$

$$y = \frac{x}{B} \cdot 100\% \quad (2)$$

Table 1.
Electrolysis conditions and chemical composition of the electrolyte

Steel grade	Composition of the electrolyte	Current density, A/cm ²	Time of electrolysis, min.
HS3-1-2	150 g KCl + 10 g of citric acid + 15 ml of HCL per 1 dm ³ of H ₂ O	30	8
HS6-5-2	1150 ml CH ₃ OH + 15 g of citric acid + 50 ml of HCL per 1 dm ³ of H ₂ O	3	90

where :

x – the content of the element in isolate determined by AAS method (%),

y – the content of the element in carbides (%),

a – the content of the element in isolate (%),

b – isolate mass (g),

B – mass of the specimen part dissolved electrolytically (g).

3. Results and discussion

The results of the phase analysis for tested steels according to the austenitising temperature are shown in Table 2. A significant dissolution of the M₇C₃ and M₆C carbides in HS3-1-2 at austenitising temperatures of 1120°C and 1150°C was observed, while no visible dissolution of the MC carbide at these temperatures was observed. Simultaneously, no M₂C primary carbide, besides MC carbide in HS3-1-2 steel, was revealed. The M₂C carbide did not occur in the microstructure in spite of the high carbon content in the HS3-1-2 steel, as this steel was additionally enriched by nitrogen. The phase analysis of HS6-5-2 steel revealed the dissolution of M₂₃C₆ type carbide at temperatures below 1210°C. The microstructure of tested steels is composed of alloying ferrite and carbides.

The composition of the carbide phase is similar after all heat treatment operations. Diffraction studies did not reveal significant differences between the carbide phases in hardened steel and carbide phases after tempering. This is due to two factors:

- the intensity of the deflected diffracted X-ray line for the family of planes affects not only the volume fraction of the specific phase in the solution but also has an influence on factors such as the chemical composition of the phases and the phase texturing.
- carbide precipitates are very small, so they can be revealed by the diffraction pattern.

It is known that when heating the steel for tempering, first M₇C₃ carbides are dissolved and M₆C and MC carbides inhibit the grain growth. M₆C carbide dissolution begins to intensify with an increase in austenitising temperature and as a result the size of austenite grains (Fig. 1) and the amount of residual austenite (Table 3) increase, causing a significant reduction in the hardness of HS3-1-2 hardened steel.

The grains in the samples hardened at a temperature of 1120°C are greater than in the samples hardened at 1160°C (Fig. 3), despite having the same annealing time and batch size.

Table 2.
 Results of phase analysis

Steel grade	Heat treatment	Occuring carbides	Comments
HS6-5-2	soft annealing	M ₆ C, M ₇ C ₃ , MC, M ₂₃ C ₆	M ₇ C ₃ – trace amount
	austenitization at 1210°C	M ₆ C, MC	isotale contain very small particles of martensite
	austenitization at 1210°C + tempering at 550°C for 2 hours	M ₆ C, MC	lack of martensite
	austenitization at 1210°C + tempering at 550°C (2 hours) + tempering at 620°C (4 hours)	M ₆ C, MC	
HS3-1-2	soft annealing	M ₆ C, MC, M ₇ C ₃	
	austenitization at 1080°C	M ₆ C, MC, M ₇ C ₃	
	austenitization at 1120°C	M ₆ C, MC, M ₇ C ₃	significant reduction of content of carbides M ₆ C and M ₇ C ₃ compared to austenitization at 1180°C is observed
	austenitization at 1150°C	M ₆ C, MC, M ₇ C ₃	
	austenitization at 1120°C + tempering at 550°C (2 hours)	M ₆ C, MC, M ₇ C ₃	based on the data the variation of fraction of individual phases in isolate cannot be determined
	austenitization at 1120°C + tempering at 550°C (2 hours) + tempering at 620°C (4 hours)	M ₆ C, MC, M ₇ C ₃	

 Table 3.
 Physico-mechanical properties of HS3-1-2 steel

Austenitizing temperature, °C	Hardness after hardening HRC	Grain size	After twice tempering (550°C, 2 hours)		After triply tempering (550°C, 1 hour)	
			Hardness HRC	Retained austenite, %	Hardness HRC	Retained austenite, %
1080	61	13	61	15	62	-
1100	61	12-13	62	16.5	62	-
1120	60	11-12	62	18	62.5	2
1140	59	10-11	63	19.5	63	4
1160	57	8	60	21	62	14.5
1180	53	7	55	30	61.5	21

 Table 4.
 The chemical composition of carbide isolate in HS3-1-2

Heat treatment of isolate	Chemical composition in isolate, % wt.						
	Fe	Mn	Cr	W	Mo	V	Si
soft annealing	33.79	0.65	20.54	13.25	5.28	8.12	0.83
austenitization at 1080°C	21.33	0.31	13.21	11.75	4.08	9.75	5.84
austenitization at 1120°C	11.16	0.12	6.34	9.84	3.75	9.84	9.26
austenitization at 1150°C	5.13	0.05	3.68	8.43	2.97	9.74	8.65
austenitization at 1120°C + tempering at 550°C for 2 hours	15.24	0.18	9.36	13.15	4.27	9.40	5.86
austenitization at 1120°C + tempering at 550°C for 2 hours + tempering at 620°C for 4 hours	88.64	0.76	16.54	12.14	4.57	9.27	1.01

After the third tempering the hardness of the steel significantly increases (Table 4) as a result of the evolution of a large number of carbides. As the sizes of these carbides are several times smaller than the primary carbides, their total area is

significantly higher, which can result in a reduction of the grindability of the tested steels.

After the third tempering the hardness of the steel significantly increases (Table 3) as a result of the evolution of a large number of carbides. As the size of secondary carbides is

several times smaller than the primary carbides, their total area is significantly higher, which can result in a reduction of the grindability of the tested steels. The results of the analysis of elements content in the carbide isolates in HS3-1-2 steel are shown in Table 4. During the austenitisation, dissolution of both the M_7C_3 carbides containing Cr and Fe and the M_6C carbides containing mainly Mo and W is observed.

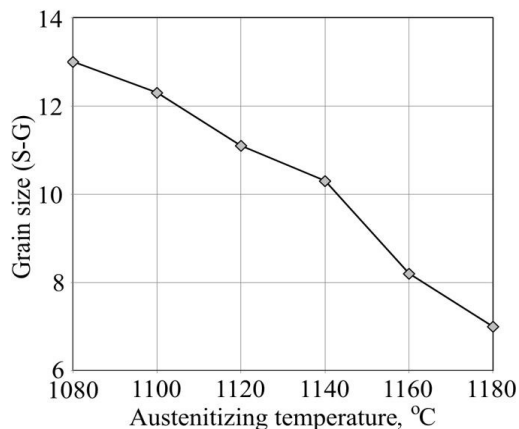


Fig. 1. The effect of austenitising temperature on the size of the austenite grain

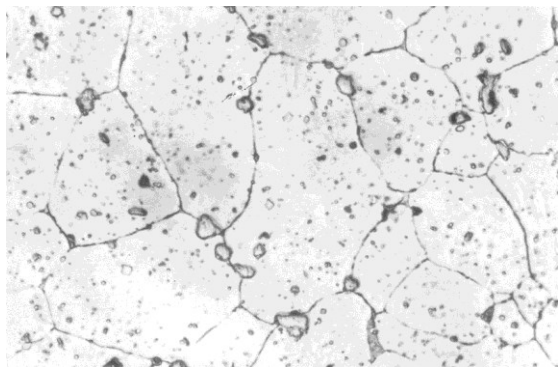


Fig. 2. Microstructure of the HS3-1-2 steel austenitized at 1160°C; etching using reagent of 8% HNO_3 ; magnification 500×

This is related to the transition of Cr, Fe, Mo and W carbides into the matrix. Vanadium is an element that transfers to matrix in a very small amount, which indicates no dissolution of the MC carbide. An increase in the content of elements in carbides after tempering is proof that the processes of separation or growth of carbides occurred. Of particular importance in this context is the change in silicon content in the steel during heat treatment processes (Table 4). The percentage of silicon increases with an increase in austenitising temperature. However, the percentage of silicon carbide decreases during the tempering. Thus, it should be concluded that during austenitisation the silicon is transferred into the carbides. Silicon is incorporated into the network of the M_6C carbide, replacing the atoms of elements such as Cr, Fe, Mn, Mo, V and W.

4. Conclusions

From the experimental results, the following conclusions can be drawn:

1. An increase in austenitising temperature intensifies the dissolution of M_6C carbide causing an increase in the austenite grain size.
2. During austenitization the process of dissolution of M_7C_3 and M_6C carbides occurs and, as a result of this process, elements such as Cr, Fe, Mo, and W are separated from the matrix.
3. During austenitization silicon separates from the matrix to the carbides and simultaneously the carbide-forming elements in matrix are replaced.
4. An increase in a degree of tempering leads to intensification of carbide separation and this process can reduce the grindability of tested steels.

References

- [1] Jaworski, J. (2009). The influence of grinding parameters of the surface layer of low-alloyed high-speed steel. *Archives of Foundry Engineering*. 9(1), 103-106.
- [2] Jaworski, J. & Trzepieciński, T. (2016). Research on durability of turning tools made of low-alloy high-speed steel. *Kovove Mater.* 54(1), 17-25. DOI: 10.4149/km_2016_1_17.
- [3] Pietrowski, S. & Szymczak, T. (2010). Alfinated coating structure on HS6-5-2 (SW7M) high speed steel. *Archives of Foundry Engineering*. 10(4), 191-198.
- [4] Bochnowski, W. (2009). The influence of arc plasma electric and laser treatment on the structure and properties of the high speed steel. *Archives of Foundry Engineering*. 9(3), 17-20.
- [5] Lu, L., Hou, L.G., Zhang, J.X., Wang, H.B., Cui, H., Huang, J.F., Zhang, Y.A. & Zhang, J.S. (2016). Improved the microstructures and properties of M3:2 high-speed steel by spray forming and niobium alloying. *Mater. Charact.* 117, 1-8. DOI: 10.1016/j.matchar.2016.04.010.
- [6] Herranz, G., Romero, A., de Castro, V. & Rodriguez, G.P. (2014). Processing of AISI M2 high speed steel reinforced with vanadium carbide by solar sintering. *Mater. Design* 54, 934-946. DOI: 10.1016/j.matdes.2013.09.027.
- [7] Xu, L., Xing, J., Wei, S., Zhang, Y. & Long, R. (2007). Optimization of heat treatment technique of high-vanadium high-speed steel based on back-propagation neural networks. *Mater. Design*. 28(5), 1452-1432. DOI: 10.1016/j.matdes.2006.03.022.
- [8] Cao, H.T., Dong, X.P., Pan, Z., Wu, X.W., Huang, Q.W. & Pei, Y.T. (2016). Surface alloying of high-vanadium high-speed steel on ductile iron using plasma transferred arc technique: Microstructure and wear properties. *Mater. Design*. 100, 223-234. DOI: 10.1016/j.matdes.2016.03.114.
- [9] Sackl, S., Leitner, H., Clemens, H. & Primig, S. (2016). On the evolution of secondary hardening carbides during continuous versus isothermal heat treatment of high speed steel HS 6-5-2. *Mater. Charact.* 120, 323-330. DOI: 10.1016/j.matdes.2016