



cyclohexanol (CH-anol), *i.e.* hydrolysis of intermediate CH-enA to cyclohexanone (CH-anon), which is by the hydrogen converted to CH-anol<sup>13, 17</sup>. Thus, is an effort to enhance selectivity of catalytic hydrogenation of aniline unto major product, CHA.

One way to suppress the formation of undesirable secondary amines is the addition of ammonia into reaction mixture. However, the addition of ammonia results in considerable decrease in the catalytic activity of used metal catalysts, especially the ones of ruthenium and rhodium<sup>11, 13</sup>. The alternative is the rational choice of catalyst for hydrogenation of AN. High yields are achieved with the use of nickel and cobalt catalysts<sup>18</sup>, but nickel catalysts also show high selectivity for the secondary products NPCHA and DCHA<sup>15, 19</sup>. For the hydrogenation of AN towards CHA are more appropriate less active, yet more selective cobalt catalysts in preference to nickel catalysts<sup>19</sup>. It has been found that the addition of alkali hydroxides into reaction mixture has a positive effect on the reactivity of the hydrogenation of AN in liquid phase as well as on the selectivity, due to the suppressing formation of undesirable side products<sup>20, 21</sup>. The presence of alkali hinders the condensation of molecules of CHA and CHI, thus prevents the formation of DCHA<sup>21</sup>. Likewise, the nickel catalysts promoted with sodium hydroxide and used in hydrogenation of AN to CHA in vapour phase significantly increased the selectivity of the title reaction<sup>17</sup>.

As summarized above, there are published works dealing with the study of addition of alkali metal hydroxides into reaction mixture or their loading in heterogeneous catalysts on the performance of hydrogenation of aniline, particularly from the perspective of the reaction selectivity. However, the question then arises, about the effect of alkali metal cations in the form carbonate salts on the catalytic hydrogenation of AN. Hence, focus of this work lies in the study of influence of presence of alkali metal carbonates in matter of cobalt catalyst on the catalytic activity and selectivity for the selective hydrogenation of aniline to cyclohexylamine in vapour phase.

## MATERIALS AND METHODS

### Chemicals

Aniline (99.9%) and cyclohexylamine (99.9%) were provided by BorsodChem MCHZ and aniline was additionally distilled. Methanol (> 99.9%) was purchased from Penta Chemicals. Gas chromatography (GC) standards: dicyclohexylamine (99.9%), *N*-cyclohexylidencyclohexylamine (>50%), and *N*-phenylcyclohexylamine (>50%) were obtained from BorsodChem MCHZ as well. All solid chemicals were used without further purification.  $\text{CoCO}_3 \cdot \text{Co}(\text{OH})_2$  (>99%) was purchased from Freeport Cobalt Oy,  $\text{Co}_3\text{O}_4$  (>99%) from Umicore and the  $\text{CaCO}_3$  (>99%),  $\text{Li}_2\text{CO}_3$  (>99%),  $\text{Na}_2\text{CO}_3$  (>99%),  $\text{K}_2\text{CO}_3$  (>99%) and  $\text{Cs}_2\text{CO}_3$  (>99%) were acquired from local suppliers. Electrolytic hydrogen (grade 3.0), nitrogen (grade 4.0) and helium (grade 5.5) were purchased from SIAD Czech spol., and additionally catalytically purified.

### Distillation of aniline

The commercial AN with content of *ca.* 0.02 wt% of water was distilled to reach final concentration of water of < 0.01 wt%. The necessity to use dry aniline lies in the fact that the content of water affects the catalytic properties and performance of  $\text{Na}_2\text{CO}_3$ -promoted cobalt catalyst during the AN hydrogenation<sup>22</sup>. Distillation of commercial AN was carried out in distillation column of length of 1.4 m, inner diameter of 30 mm and with column structured packing Sulzer DX with efficiency of 18 theoretical plates. Distillation was performed under reduced pressure of 9.0–9.8 kPa and temperature range of reboiler of 65–86 °C. As a distillate fractions of AN- $\text{H}_2\text{O}$  were removed, the residue AN with 0.005 wt% of  $\text{H}_2\text{O}$  was used as reactant for hydrogenation experiments.


### Catalysts preparation

The model cobalt catalysts for the catalytic tests were prepared by the two-stage homogenization of solid components, first cobalt precursors  $\text{CoCO}_3 \cdot \text{Co}(\text{OH})_2$  and  $\text{Co}_3\text{O}_4$ , with chemical promoter  $\text{Me}_2\text{CO}_3$  (Me = Li, Na, K and Cs) and after that with diluent material  $\text{CaCO}_3$  in agate mill. The molar ratios of solid components for their physical mixing were as follows:  $\text{CoCO}_3 \cdot \text{Co}(\text{OH})_2 / \text{Co}_3\text{O}_4$  0.71, Co-precursors/ $\text{Me}_2\text{CO}_3$  9.0 and Co-precursors/ $\text{CaCO}_3$  0.7. Thereafter, homogeneous catalyst matter was compressed into cylindrical tablets of diameter of 10 mm. Then tablets were crushed and the granulate fractions were sorted. For the catalytic tests was used fraction of 0.80–1.25 mm. For the chemisorption measurements the model cobalt catalysts were prepared pursuant to above-described procedure but only from one cobalt precursor, *i.e.*  $\text{CoCO}_3 \cdot \text{Co}(\text{OH})_2$ , and chemical promoter  $\text{Me}_2\text{CO}_3$  (molar ratio Co-precursor/ $\text{Me}_2\text{CO}_3$  23.0). For the chemisorption measurements was used granulate fraction of 25–45  $\mu\text{m}$ .

### Catalytic tests

Catalytic hydrogenation of AN was performed in glass tubular continuous-flow U-shaped reactor of an inner diameter of 7 mm. The used experimental apparatus<sup>15</sup> for the catalytic hydrogenation reactions in gaseous phase (Fig. 2) is described as follows: Inlet of hydrogen (or hydrogen + nitrogen mixture) (1) into catalytic purifier with copper catalyst (2) and subsequently to column with molecular sieve (3) for the additional depuration of trace amount of oxygen and water in gases. The aniline (4) was fed into reactor (5) by a piston pump. The reactor was placed in bath of heat transfer medium, *i.e.* Rose's metal alloy (6). The side arm of reactor was still heated by the infrared lamp (7) in order to suppress premature condensation of outlet gaseous reaction mixture. The outlet reaction mixture was condensed in Liebig condenser (8) cooled by water (9) and absorbed into methanol in freeze trap (10) placed in a cooling bath of ice-water mixture (11) tempered at 0 °C. Waste gases such as hydrogen and ammonia were disposed (12).

The experiments were preceded by the reduction of individual cobalt catalysts. The conditions of catalysts reduction were as follows: 230 °C for 2 hours under a flow of mixture  $\text{H}_2 + \text{N}_2$  (30 mol% + 70 mol%) at rate of 50 l h<sup>-1</sup> and 230 °C for 8 hours under a flow of pure  $\text{H}_2$  at rate of 50 l h<sup>-1</sup>. In the final step, the cata-

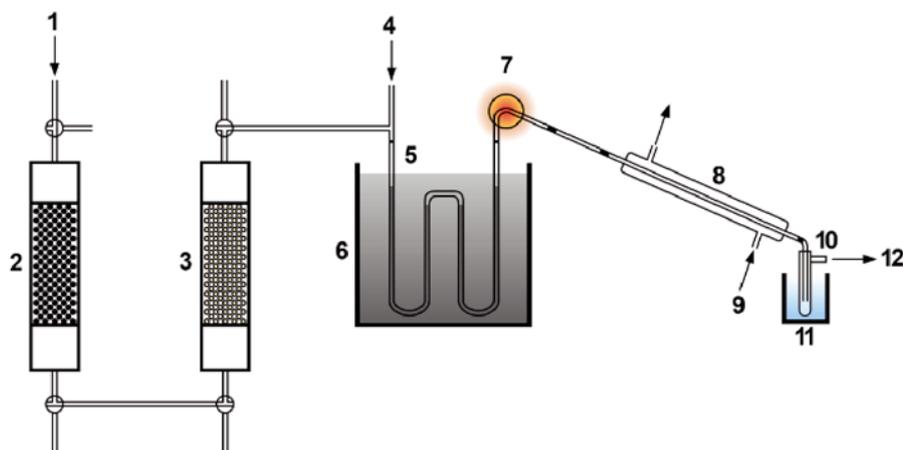

**Figure 2.** Schematic diagram of the experimental apparatus for the catalytic hydrogenation of AN to CHA in vapour phase

lysts were reduced at 330 °C for 0.5 hour under a flow of pure H<sub>2</sub> at rate of 50 l h<sup>-1</sup>. Duration of reduction of cobalt catalysts with K<sub>2</sub>CO<sub>3</sub> and Cs<sub>2</sub>CO<sub>3</sub> loadings was in final step at 330 °C 1.5 and 2.5 hour respectively, because of effect cation radius of alkali metal carbonate promoters on the rate of reduction of the cobalt catalyst precursor<sup>23–25</sup>. The both cobalt precursors, *i.e.* Co<sub>3</sub>O<sub>4</sub> and CoCO<sub>3</sub>·Co(OH)<sub>2</sub> are completely transformed to active cobalt only in hexagonal-closed packed (hcp) phase under the aforesaid reduction conditions<sup>26</sup>. Specific surface area of cobalt Co<sup>0</sup> originating from Co<sub>3</sub>O<sub>4</sub> reduction is 5.0 m<sup>2</sup> g<sup>-1</sup>, and from CoCO<sub>3</sub>·Co(OH)<sub>2</sub>, 6.7 m<sup>2</sup> g<sup>-1</sup>. Thereupon, after reduction, the hydrogenation of AN over a 14.5 g of cobalt catalyst was carried at temperature 165 °C, atmospheric pressure, molar ratio of AN/H<sub>2</sub> of 0.09 and feed of AN of 6–15 g<sub>AN</sub> h<sup>-1</sup>, *i.e.* catalyst contact time of 2.42–0.97 g<sub>cat</sub>/(g<sub>AN</sub> h<sup>-1</sup>). The samples of reaction mixtures were analysed by a GC technique with FI detector.

### Temperature programmed desorption

The aniline and cyclohexylamine temperature programmed desorptions (TPD) were performed on AutoChem II 2920 (Micromeritics) equipped with TC detector. 90 mg of cobalt catalyst was filled in a quartz tubular U-reactor and *in situ* reduced at 260 °C for 3 hours under a flow of H<sub>2</sub> at rate of 50 ml min<sup>-1</sup>. Then temperature was increased to 330 °C and reduction continues for 0.5 hour under a flow of H<sub>2</sub> at rate of 50 ml min<sup>-1</sup>. After the temperature was cooled down to 150 °C, on the surface of catalyst was pulse dosed AN or CHA (1.60 kPa) through the loop (5 ml), pulse frequency 1 pulse min<sup>-1</sup> (overall 30 pulses), under a flow of He at rate of 30 ml min<sup>-1</sup>. In the next step, the flow rate of He was increased to 50 ml min<sup>-1</sup> to remove physically adsorbed amine for 1.5 hour at 150 °C. Finally, the catalyst was heated from 150 to 600 °C with a heating rate of 10 °C per min in flow of He (50 ml min<sup>-1</sup>) and the desorbed species were detected.

### Analytical

Quantitative GC analyses of chemicals and samples of reaction mixtures were performed using a Shimadzu GC-2010 chromatograph with FI detector. Using a Rxi®-624Sil MS column (30 m x 0.25 mm x 1.40 μm) and He as a carrier gas. The column temperature regime was set as follows: Initial temperature 80 °C for 2 min,

heating with the temperature ramp of 15 °C per min up to the temperature of 210 °C. The injector and detector temperatures were set to 250 °C. The reaction products were identified by GC standards.

The concentration of water in samples of aniline was determined by the coulometric Karl-Fischer titration on Titrator C 30 Mettler Toledo.

### Data processing

The results of GC analyses, *i.e.* area percent units (area %) were converted to mass fractions (wt%) and subsequently to mole fractions (mol%). The reaction system of hydrogenation of AN was characterized by conversion of AN and reaction (percentage) selectivity, which are defined by Eqs. 1 and 2.

$$X_{AN} = \left[ \frac{x_{AN,in} - x_{AN,out}}{x_{AN,in}} \right] \cdot 100 \quad (1)$$

$$S_i = \left[ \frac{x_{i,out}}{x_{AN,in} - x_{AN,out}} \right] \cdot 100 \quad (2)$$

Here  $X_{AN}$  is conversion of aniline,  $x_{AN}$  molar fraction of AN,  $S_i$  reaction (percentage) selectivity of species  $i$  and  $x_i$  molar fraction of species  $i$ . The catalytic activity of each cobalt catalyst for hydrogenation of AN to CHA was evaluated by comparative, simplified kinetic method at the constant conversion of AN expressed as follows:

$$\text{rel. } a_w = \left[ \frac{(W/F_{AN})_{ref}}{(W/F_{AN})_{X_{AN}}} \right] \cdot \text{rel. } a_{w,ref} \quad (3)$$

where  $\text{rel. } a_w$  corresponds to relative (weight) activity,  $W$  to weight of the catalyst,  $F_{AN}$  to mass flow rate of aniline and the  $\text{rel. } a_{w,ref}$  is the reference relative (weight) activity which is equal to one. It means, the greater value of  $\text{rel. } a_w$  the more active is catalyst sample. The catalysts performance was also described by value of the relative selectivity, which is defined by following Eq. 4.


$$\text{rel. } S = \left[ \frac{(x_i)_{ref}}{x_i} \right]_{X_{AN}} \cdot \text{rel. } S_{ref} \quad (4)$$

Here  $\text{rel. } S$  is the relative selectivity of catalyst towards the main product (CHA), but from the perspective of formation of by-products. As in the case of previous case, the greater the value of  $\text{rel. } S$  the catalyst is more selective towards CHA.

## RESULTS AND DISCUSSION

### Catalytic activity of $\text{Me}_2\text{CO}_3$ promoted $\text{Co}/\text{CaCO}_3$ catalysts in aniline hydrogenation

It was studied the catalytic activity of each prepared  $\text{Co}/\text{CaCO}_3$  and  $\text{Co}/\text{CaCO}_3\text{-Me}_2\text{CO}_3$  ( $\text{Me} = \text{Li}, \text{Na}, \text{K}$  and  $\text{Cs}$ ) catalysts (henceforward abbreviated as  $\text{Co}$  and  $\text{Co-Me}$ ) for the hydrogenation of AN to CHA. Figure 3 shows that the activity of cobalt catalysts drops stepwise with increasing alkali metal cation of  $\text{Me}_2\text{CO}_3$  promoter. The highest activity for hydrogenation of aniline has unpromoted cobalt catalyst. Then the catalytic activity decreases abruptly. In the first instance, the  $\text{Co-Li}$  and then  $\text{Co-Na}$  cat. Both cobalt catalysts with promoters  $\text{K}_2\text{CO}_3$  and  $\text{Cs}_2\text{CO}_3$  are entirely inactive for the hydrogenation of AN. Table 1 summarized the results of performance of each cobalt catalyst through the values of relative (weight) reactivity with the  $\text{Co}$  as reference catalyst. The values of relative (weight) reactivity were evaluated at the constant conversion of AN of 57.1, 69.5, 83.2 and 91.5% and the obtained results made into arithmetic mean. The  $\text{Co-Li}$  catalyst reaches only half of the activity of the reference cobalt catalyst free of  $\text{Me}_2\text{CO}_3$  promoter for the AN hydrogenation. Whereas the activity of  $\text{Co-Na}$  catalyst for the self-same hydrogenation reaction is 83% lower than in the case of reference  $\text{Co}$  catalyst.

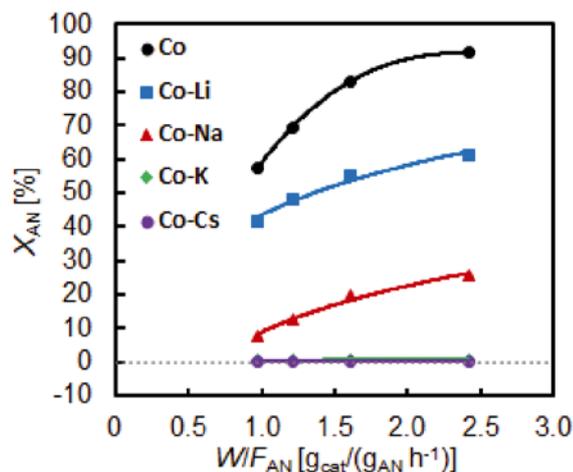


**Figure 3.** The effect of alkali metal carbonate doping of cobalt catalyst on its activity for hydrogenation of AN to CHA

Catalyst	rel. $a_w$ [-]
Co	1.00
Co-Li	0.50
Co-Na	0.17
Co-K	<0.01
Co-Cs	<0.01

**Table 1.** Comparison of catalytic activity of used cobalt catalysts for hydrogenation of AN

According to TPD results of the AN adsorption the alkali metal carbonate promoters significantly affects the chemisorption of AN on the cobalt catalysts surface. It was further discovered that the AN is partially transformed to benzene and ammonia under the conditions of TPD. From Table 1 can be seen that the activity of cobalt catalysts for the AN hydrogenation dropped in accordance with addition of alkali metal carbonate promoters, which can be further explained by the TPD results. As can be

seen in Figure 4, at the temperature range of 450–600 °C occurs desorption of species of the TPD of aniline. With the promotion of cobalt catalysts by alkali metal carbonates decreased AN adsorption, which resulted in a decrease of relative concentration rel.c of chemisorbed species (amount in area %) in reference to unpromoted  $\text{Co}$  catalyst (Table 2) whence implies the resultant low hydrogenation activity. Possible explanation may be the geometric effect of the alkali metal of  $\text{Me}_2\text{CO}_3$  molecule. The hydrogenation activity of catalysts is in the order  $\text{Co} > \text{Co-Li} > \text{Co-Na} > \text{Co-K} \sim \text{Co-Cs}$  because the larger alkali metal cations may impede the adsorption of AN on the cobalt catalyst surface. An interesting finding is that the desorption peak maximum of AN-TPD for the  $\text{Co-Li}$  and  $\text{Co-Cs}$  catalysts is considerably dissimilar (*ca.* 541 °C for  $\text{Co-Li}$  and 501 °C for  $\text{Co-Cs}$ ) from the rest of used cobalt catalysts (*ca.* 512–520 °C). Explanation of this observed phenomenon may lie in the aspect of the electronic effect, *i.e.* polarization of  $\text{Li}^+$  ion, which is the strongest among the rest of alkali metal ions due to its higher electronegativity compared to rest of the alkali metals. From this viewpoint the  $\text{Li}^+$  ion results in boosting electron density at interface between active  $\text{Co}$  and  $\text{Li}_2\text{CO}_3$  and thus affect the adsorption of AN, which makes a stronger interaction of AN with catalyst surface<sup>27, 28</sup>. Compared to that, the  $\text{Cs}$  has the lowest electronegativity amongst the alkali metals and for this reason, there is weaker bonding of AN on the  $\text{Co-Cs}$  catalyst surface.

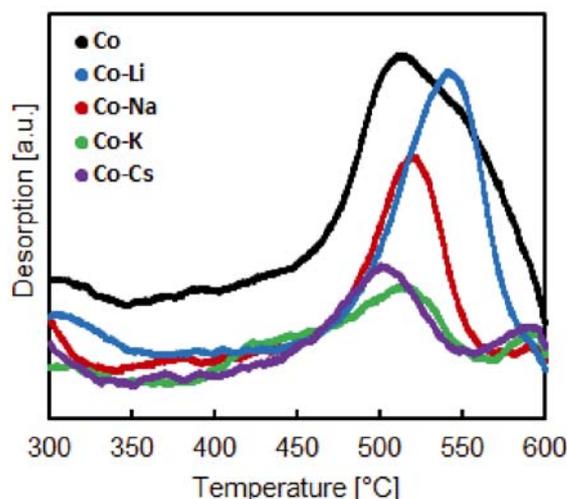

**Figure 4.** AN-TPD profiles of various cobalt catalysts after reduction

### Catalytic selectivity of $\text{Me}_2\text{CO}_3$ promoted $\text{Co}/\text{CaCO}_3$ catalysts in aniline hydrogenation


Conjointly with the activity of cobalt and alkali metal-doped cobalt catalysts, their efficiency for the formation of the main product CHA and undesirable by-products DCHA, NPCHA and NCCHA was studied. Nevertheless, selectivity was evaluated only for  $\text{Co}$ ,  $\text{Co-Li}$  and  $\text{Co-Na}$  catalysts due to the poor activity of  $\text{Co-K}$  and  $\text{Co-Cs}$  catalysts for AN hydrogenation. To reliably compare each cobalt catalyst in the perspective of selectivity, it was chosen  $\text{Co}$  as reference catalyst. The values of relative selectivity and reaction (percentage) selectivity were evaluated at the constant conversion of AN of 50% (for the  $\text{Co-Na}$  cat. the composition of the reaction mixture at the

**Table 2.** Summary of data obtained from temperature programmed desorption of AN



Catalyst	Temperature maximum		Area % <sup>a</sup>	rel.c [-]
	T <sub>1</sub> [°C]	T <sub>2</sub> [°C]		
Co	512	–	0.1039	1.00
Co-Li	541	–	0.0876	0.84
Co-Na	520	590	0.0446	0.43
Co-K	514	596	0.0231	0.22
Co-Cs	501	590	0.0243	0.23

<sup>a</sup>Sum of the desorbed amount (T<sub>1</sub> + T<sub>2</sub>).

conversion of 50 % was obtained by extrapolation (Fig. 5–7). The results of relative selectivity of each catalyst and reaction (percentage) selectivity are summarized in Table 3. In absence of Me<sub>2</sub>CO<sub>3</sub>, AN is in small extent converted to both secondary amines DCHA (*ca.* 0.6% selectivity at conv. 50%) and NPCHA (*ca.* 0.5% selectivity at conv. 50%). However, when alkali metal carbonates were added, the consecutive reactions leading to DCHA and NPCHA were suppressed. As shown in Table 3, Co-Na catalyst has superior catalytic selectivity because AN is converted almost just to CHA. It may be steric hindrance by Me<sub>2</sub>CO<sub>3</sub> for the formation of DCHA and NPCHA, which is the reason for improved selectivity towards CHA<sup>II</sup>. Nevertheless, it's interesting that the addition of Li<sub>2</sub>CO<sub>3</sub> slightly worsens the selectivity of cobalt catalyst towards CHA, *i.e.* promotes the formation of NCCCHA (*ca.* 2.3% selectivity at conv. 50%).

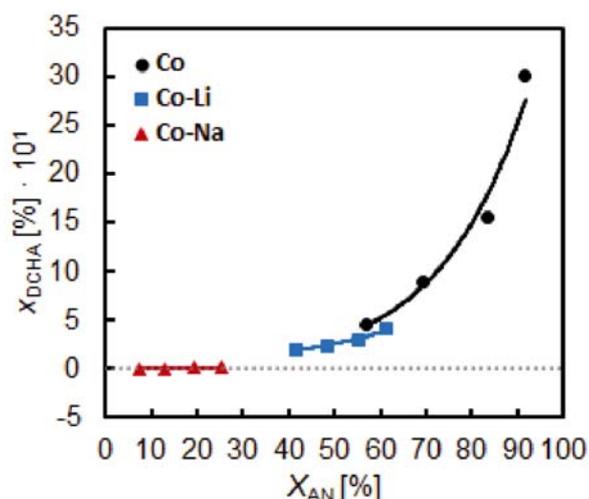**Figure 5.** Concentration profiles of DCHA (mol%) during the AN hydrogenation over a cobalt catalysts

As in the case of the previous chapter, results of the effect of alkali metal carbonate promoters on selectivity were supported by TPD measurement (Fig. 8). It was discovered that the TPD of adsorbed CHA over Co, Co-Li and Co-Na resulted in conversion to aniline (and subsequently to benzene and ammonia) under the condition of TPD of CHA. As can be seen in Figure 8, the addition of alkali metal carbonate promoters, especially Na<sub>2</sub>CO<sub>3</sub>, limits the adsorbed amount of CHA. Interesting finding is that TPD results of adsorption of AN

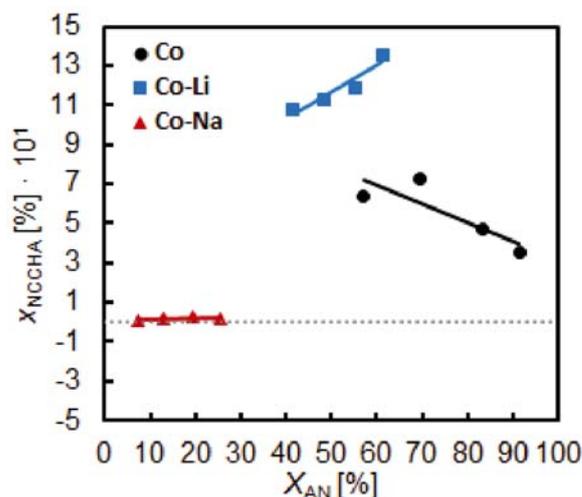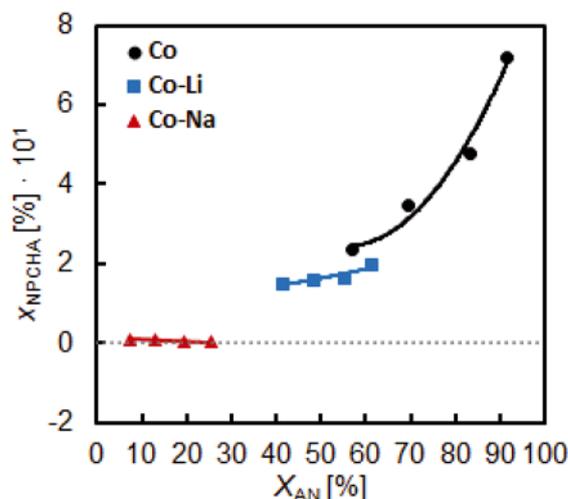**Figure 6.** Concentration profiles of NCCCHA (mol%) during the AN hydrogenation over a cobalt catalysts**Figure 7.** Concentration profiles of NPCHA (mol%) during the AN hydrogenation over a cobalt catalysts


and CHA over Co and Co-Na catalysts share the almost the same values of temperature maxima of desorption peaks (Table 2, Table 4), however, this is not the case of Co-Li catalyst. From the adsorption of CHA, the temperature maximum of desorption peak of product is now 491 °C which is differs by 50 °C. In the case of both AN-TPD and CHA-TPD the reproducibility of experiments, *i.e.* peak temperature maxima is 5%. Most certainly, Li<sub>2</sub>CO<sub>3</sub> loading supply additional active sites

**Table 3.** Effect of alkali metal carbonate promoter on the selectivity of cobalt catalysts and distribution of major by-products

Catalyst	DCHA		NCCCHA		NPCHA	
	rel.S [-]	S [%]	rel.S [-]	S [%]	rel.S [-]	S [%]
Co	1.00	0.62	1.00	1.56	1.00	0.51
Co-Li	1.19	0.52	0.67	2.33	1.56	0.33
Co-Na	11.42	0.05	24.02	0.07	50.49	0.01

At the constant conversion of AN of 50%.

to the cobalt catalyst<sup>29</sup> or affects the properties of the active sites of cobalt catalyst itself. It's a possible that the CHA preferably adsorbs on these active sites, but with increasing temperature of TPD measurement the desorbed CHA, more precisely desorbed species does not re-adsorbs on the surface of cobalt catalyst.

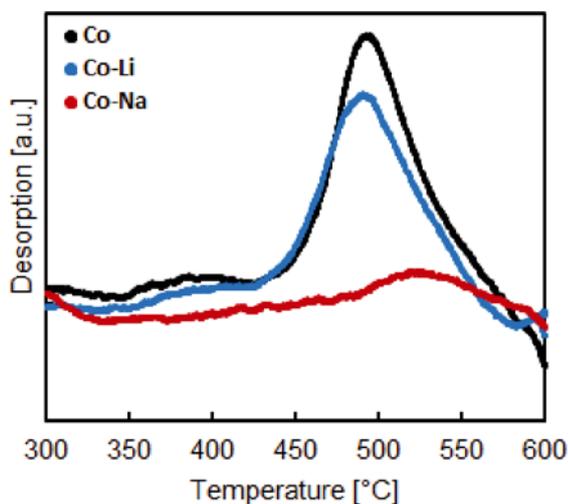

**Figure 8.** CHA-TPD (AN-TPD) profiles of various cobalt catalysts after reduction

**Table 4.** Summary of data obtained from temperature programmed desorption of CHA

Catalyst	Temp. max.	Area %	rel.c [-]
	T [°C]		
Co	495	0.0630	1.00
Co-Li	491	0.0456	0.72
Co-Na	524	0.0124	0.20

## CONCLUSION

In summary, a series of Co/CaCO<sub>3</sub> catalysts promoted by various alkali metal (Li, Na, K and Cs) carbonates were prepared by physical mixing. The cobalt catalysts were evaluated for direct hydrogenation of aniline to cyclohexylamine in vapour phase. The results show that the Li<sub>2</sub>CO<sub>3</sub> loading leading only to 50% of catalytic activity of alkali free Co/CaCO<sub>3</sub> catalyst and Na<sub>2</sub>CO<sub>3</sub> loading merely to 17% of catalytic activity of the reference catalyst. Besides, introduction of K<sub>2</sub>CO<sub>3</sub> and Cs<sub>2</sub>CO<sub>3</sub> in matrix of cobalt catalyst results in utter loss of catalytic activity for hydrogenation of aniline. As a result, gradual loss of catalytic activity is consistent with the experiments of temperature programmed desorption of aniline, which exhibited that with the presence of Me<sub>2</sub>CO<sub>3</sub> promoters there is a decrease of adsorbed amount of aniline on the surface of cobalt catalyst. It is noteworthy that the addition of Na<sub>2</sub>CO<sub>3</sub> into cobalt catalyst exceedingly enhances the selectivity towards desired product cyclohexylamine. The Na<sub>2</sub>CO<sub>3</sub>-promoted cobalt catalyst significantly inhibits the consecutive reactions of cyclohexylamine to *N*-cyclohexylidencyclohexylamine (selectivity of 0.07%), dicyclohexylamine (selectivity of 0.05%) and *N*-phenylcyclohexylamine (selectivity of 0.01%). This work can provide guidance for the design of cobalt catalysts to modulate balance between the catalytic activity and selectivity for the hydrogenation reactions in vapour phase similar to hydrogenation of aniline.

## ACKNOWLEDGMENT

This work was supported from the grant of Specific university research – grant No A1\_FCHT\_2022\_010.

## LITERATURE CITED

- Chaudhari, Ch., Sato, K., Ikeda, Y., Terada, K., Abe, N. & Nagaoka, K. (2021). One-pot synthesis of cyclohexylamine and *N*-aryl pyrroles via hydrogenation of nitroarenes over the Pd<sub>0.5</sub>Ru<sub>0.5</sub>-PVP catalyst. *New. J. Chem.* 45, 9743–9746. DOI: 10.1039/D1NJ00922B.
- Araki, S., Nakanishi, K., Tanaka, A. & Kominami, H. (2020). A ruthenium and palladium bimetallic system superior to a rhodium co-catalyst for TiO<sub>2</sub>-photocatalyzed ring hydrogenation of aniline to cyclohexylamine. *J. Catal.* 389, 212–217. DOI: 10.1016/j.jcat.2020.05.035.
- Ásgeirsson, B., Markússon, S., Hlynsdóttir, S.S., Helldand, R. & Hjörleifsson, J.G. (2020). X-ray crystal structure of *Vibrio* alkaline phosphatase with the non-competitive inhibitor cyclohexylamine. *Biochem. Biophys. Rep.* 24, 100830–100840. DOI: 10.1016/j.bbrep.2020.100830.
- Ranjbar, S., Soltanabadi, A. & Fakhri, Z. (2016). Experimental and Computational Studies of Binary Mixtures of Isobutanol + Cyclohexylamine. *J. Chem. Eng. Data.* 61(9), 3077–3089. DOI: 10.1021/acs.jced.6b00158.
- Senthil, K., Elangovan, K., Senthil, A. & Vinitha, G. (2021). Synthesis, growth, optical, mechanical, thermal, dielectric and third order nonlinear optical properties of cyclohexylamine derivative single crystals. *Spectrochim. Acta. A: Mol. Biomol. Spectrosc.* 247, 119063–119071. DOI: 10.1016/j.saa.2020.119063.
- Beepala, S.K., Mitta, H., Sk, H., Balla, P. & Komandur, V.R.Ch. (2022). Reductive amination of cyclohexanol/cyclohexanone to cyclohexylamine using SBA-15 supported copper catalysts. *J. Indian. Chem. Soc.* 99(6), 100451–100458. DOI: 10.1016/j.jics.2022.100451.
- Churro, R., Mendes, F., Araújo, P., Ribeiro, F., Peres, J. & Madeira, L.M. (2021). Statistical modelling of the amination reaction of cyclohexanol to produce cyclohexylamine over a commercial Ni-based catalyst. *Chem. Eng. Res. Des.* 170, 189–200. DOI: 10.1016/j.cherd.2021.03.029.
- Wen, J., You, K., Liu, X., Jian, J., Zhao, F., Liu, P., Ai, Q. & Luo, H. (2019). Highly selective one-step catalytic amination of cyclohexene to cyclohexylamine over HZSM-5. *Catal. Commun.* 127, 64–68. DOI: 10.1016/j.catcom.2019.05.007.
- Kowalewski, E., Krawczyk, M., Słowik, G., Kocik, J., Pieta, I.S., Chernyayeva, O., Lisovytskiy, D., Matus, K. & Śrębowata, A. (2021). Continuous-flow hydrogenation of nitrocyclohexane toward value-added products with CuZnAl hydrotalcite derived materials. *Appl. Catal. A: Gen.* 618, 118134–118145. DOI: 10.1016/j.apcata.2021.118134.
- Axet, M.R., Conejero, S. & Gerber, I.C. (2018). Ligand Effects on the Selective Hydrogenation of Nitrobenzene to Cyclohexylamine Using Ruthenium Nanoparticles as Catalysts. *Appl. Nano. Mater.* 1(10), 5885–5894. DOI: 10.1021/acsanm.8b01549.
- Li, X., Wang, Z., Mao, S., Chen, Y., Tang, M., Li, H. & Wang, Y. (2018). Insight into the Role of Additives in Catalytic Synthesis of Cyclohexyl-amine from Nitrobenzene. *Chin. J. Chem.* 36, 1191–1196. DOI: 10.1002/cjoc.201800380.
- Chatterjee, M., Sato, M., Kawanami, H., Ishizaka, T., Yokoyama, T. & Suzuki, T. (2011). Hydrogenation of aniline to cyclohexylamine in supercritical carbon dioxide: Significance of phase behaviour. *Appl. Catal. A: Gen.* 396, 186–193. DOI: 10.1016/j.apcata.2011.02.016.
- Greenfield, H. (1964). Hydrogenation of Aniline to Cyclohexylamine with Platinum Metal Catalysts. *J. Org. Chem.* 29(10), 3082–3084. DOI: 10.1021/jo01033a512.
- Yin, Z., Zeng, H., Wu, J., Zheng, S. & Zhang, G. (2016). Cobalt-Catalyzed Synthesis of Aromatic, Aliphatic, and Cyclic

Secondary Amines via a “Hydrogen-Borrowing” Strategy. *ACS Catal.* 6(10), 6546–6550. DOI: 10.1021/acscatal.6b02218.

15. Valeš, R., Dvořák, B. & Krupka, J. (2021). Thermodynamic analysis on disproportionation process of cyclohexylamine to dicyclohexylamine. *Pol. J. Chem. Tech.* 23(3), 63–48. DOI: 10.2478/pjct-2021-0029.

16. Hagihara, H. & Etsuro, E. (1965). The Catalytic Hydrogenation of Aniline. *Bull. Chem. Soc. Jpn.* 38(12), 2094–2100. DOI: 10.1246/bcsj.38.2094.

17. Mink, G. & Horváth, L. (1998). Hydrogenation of aniline to cyclohexylamine on NaOH-promoted or lanthana supported nickel. *React. Kinet. Catal. Lett.* 65, 59–65. DOI: 10.1007/BF02475316.

18. Roose, P., Eller, K., Henkes, E., Rossbacher, R. & Höke, H. (2015). Amines, Aliphatic. In *Ullmann's Encyclopedia of Industrial Chemistry*. Weinheim, Germany: Wiley-VCH Verlag GmbH & Co. KGaA. DOI: 10.1002/14356007.a02\_001.pub2.

19. Narayanan, K. & Unnikrishnan, R.P. (1997). Comparison of hydrogen adsorption and aniline hydrogenation over coprecipitated Co/Al<sub>2</sub>O<sub>3</sub> and Ni/Al<sub>2</sub>O<sub>3</sub> catalysts. *J. Chem. Soc., Faraday Trans.* 93(10), 2009–2013. DOI: 10.1039/A608074J.

20. Nishimura, S., Yutaka, K., Yoshiharu, O. & Yoshio, F. (1971). The Ruthenium-Catalyzed Hydrogenation of Aromatic Amines Promoted by Lithium Hydroxide. *Bull. Chem. Soc. Jpn.* 44(1), 240–243. DOI: 10.1246/bcsj.44.240.

21. Nishimura, S., Shu, T., Hara, T. & Takagi, Y. (1966). The Hydroxide-Blacks of Ruthenium and Rhodium as Catalysts for the Hydrogenation of Organic Compounds. II. The Effects of Solvents and Added Alkalis in the Hydrogenation of Aniline. *Bull. Chem. Soc. Jpn.* 39(2), 329–333. DOI: 10.1246/bcsj.39.329.

22. Valeš, R., Dvořák, B. & Krupka, J. (2021). The effect of water and substituents of aromatic ring on its hydrogenation

over a cobalt catalyst. Revealed in Reference: 8<sup>th</sup> International Conference on Chemical Technology, 3-5 May 2021 (pp. 98–103). Prague, Czech Republic: Czech Society of Industrial Chemistry. ebook: 978-80-88307-08-2.

23. Díaz, A., Acosta, D.R., Odriozola, J.A. & Montes, M. (1997). Characterization of Alkali-Doped Ni/SiO<sub>2</sub> Catalysts. *J. Phys. Chem. B.* 101(10), 1782–1790. DOI: 10.1021/jp963145u.

24. Dvořák, B. & Pašek, J. (1967). Einfluss der Zusammensetzung, der Herstellungsbedingungen und der Struktur des Kobaltkatalysators auf seine katalytische Aktivität für die Anilinhydrierung in der Gasphase. *Collect. Czech. Chem. Commun.* 32(10), 3476–3492. DOI: 10.1135/cccc19673476.

25. Strojcová, D. (2008). *Effect of alkali metals carbonates on reduction rate of Co<sub>3</sub>O<sub>4</sub> and strength of interactions between hydrogen and cobalt metal*. Published bachelor thesis, University of Chemistry and Technology, Prague, Czech Republic.

26. Veselá, D. (2016). *Study of selected properties of cobalt catalysts*. Published doctoral dissertation, University of Chemistry and Technology, Prague, Czech Republic.

27. Li, D., Ichikuni, N., Shimazu, S. & Uematsu, T. (1998). Catalytic properties of sprayed Ru/Al<sub>2</sub>O<sub>3</sub> and promoter effects of alkali metals in CO<sub>2</sub> hydrogenation. *Appl. Catal. A: Gen.* 172(2), 351–358. DOI: 10.1016/S0926-860X(98)00139-2.

28. Shi, H., Yang, H., Gao, P., Chen, X., Liu, H., Zhong, L., Wang, H., Wei, W. & Sun, Y. (2018). Effect of alkali metals on the performance of CoCu/TiO<sub>2</sub> catalysts for CO<sub>2</sub> hydrogenation to long-chain hydrocarbons. *Chin. J. Catal.* 39(8), 1294–1302. DOI: 10.1016/S1872-2067(18)63086-4.

29. Pradeep, S.M., Weibin, L., Yijiao, J. & Huang, J. (2021). Cu-Based Nanocatalysts for CO<sub>2</sub> Hydrogenation to Methanol. *Energy Fuels.* 35(10), 8558–8584. DOI: 10.1021/acs.energyfuels.1c00625.