

# OPTIMIZATION OF CUTTING FORCES DURING PLUNGE TURNING OF HARDENED 18CrMo4 STEEL

**Bogusław Pytlak**

## Summary

The paper investigates the influence of cutting parameters ( $v_c$ ,  $f$ ,  $m$ ) on the main cutting force  $F_c$  and the feed force  $F_f$  during finish plunge hard turning of hardened 18CrMo4 steel with the use of Cubical Boron Nitride (CBN) inserts. The experimental research was conducted according to the Taguchi methodology. On the basis of the research results obtained, optimal values of cutting parameters were determined, for which the cutting forces  $F_c$  and  $F_f$  are minimal. Next, the analysis of variance ANOVA was performed in order to determine the significance of the impact of particular cutting parameters on the optimized criteria. Verification tests which were carried out confirm the conclusions drawn that the greatest influence on cutting forces  $F_c$  and  $F_f$  has the cutting speed  $v_c$  which should be the greatest and feed  $f$  which should be the lowest.

**Keywords:** plunge hard turning, cutting forces, optimization, Taguchi method

## Optimalizacja sił skrawania podczas wgnębnego toczenia zahartowanej stali 18CrMo4

### Streszczenie

W pracy określono wpływ parametrów skrawania ( $v_c$ ,  $f$ ,  $m$ ) na składową główną siłę skrawania  $F_c$  i składową posuwową  $F_f$  podczas wykończeniowego wgnębnego toczenia na twardo stali 18CrMo4 w stanie zahartowanym. Stosowano płytki z regularnego azotku boru (CBN). Badania eksperymentalne prowadzono przy użyciu metodyki Taguchi'ego. Analiza uzyskanych wyników badań była podstawą do ustalenia optymalnych wartości parametrów skrawania, dla których siły skrawania  $F_c$  i  $F_f$  przyjmują wartości najmniejsze. Wykonano również analizę wariancji ANOVA w celu określenia istotności wpływu poszczególnych parametrów skrawania na optymalizowane kryteria. Prowadzono badania weryfikujące, których wyniki potwierdziły przyjętą hipotezę, że największy wpływ na siły skrawania  $F_c$  i  $F_f$  ma prędkość skrawania  $v_c$ . Stąd należy stosować dużą prędkość skrawania, natomiast minimalny posuw.

**Słowa kluczowe:** wgnębne toczenie na twardo, siły skrawania, optymalizacja, metoda Taguchi'ego

## 1. Introduction

The increase in popularity of hard turning in recent years has brought many interesting variations of the plunge turning method [1]. The most important advantage of this machining method is the reduction of machining time of approx. 75-90% as compared to straight hard turning, even using the Wiper geometry

---

Address: Bogusław PYTLAK PhD, Eng., University of Bielsko-Biała, Department of Manufacturing Technology and Automation, 43-309 Bielsko-Biała, Willowa 2, Poland, phone: (0-48, 33) 82 79 213, fax: (0-48, 33) 82 79 300, e-mail: bpytlak@ath.bielsko.pl

inserts. This is a significant advantage in the current pressure to reducing the manufacturing time and production costs. Another advantage of hard turning with plunge feed is distribution of the cutting process over a considerable length of the cutting edge of the insert, which in combination with the short contact time of the stock with the tool results in extension of the tool life [2, 3]. Other benefits include the elimination of coolant and helical machining marks. Of course, hard turning with plunge feed has several drawbacks. The main one is the occurrence of increased cutting forces resulting from the distribution of the cutting process over a considerable length of the cutting edge. In addition, the quality of the finish, as well as the strength of the cutting edge of the insert must be high [2].

The width of the machined surface during plunge turning is limited to the length of the cutting edge of the insert. However, if the machining surfaces mating with sealing rings, this restriction is not an obstacle, because the contact of the sealing ring with the shaft surface occurs on a very small width. The results of preliminary research presented in paper [4] indicate that the surface of the steel 18CrMo4 after plunge hard turning perfectly meets the requirements for suitable geometrically-dimensional accuracy and surface layer properties [5-7]. Chromium-manganese steel 18CrMo4 is a common material for gear parts, for example for toothed shafts mating with the sealing rings. So far, the most common in industrial practice as finishing operation of surfaces mating with the sealing rings is used plunge grinding with a sufficiently long time of sparking-out, recommended by most manufacturers sealing rings. The problem of alternative methods of finishing surfaces mating with the sealing rings was raised, among others in the papers [8-10].

## 2. Methodology

The paper investigates the influence of the cutting speed  $v_c$ , plunge feed  $f$  and displacement  $m$  on the criteria of the main cutting force  $F_c$  and feed force  $F_f$ . The following measurements were performed during the research: mean values of the main cutting force  $F_{c\,avg}$  and the feed force  $F_{f\,avg}$ , maximal values of this forces  $F_{c\,max}$  and  $F_{f\,max}$ . The mean value of cutting forces  $F_{c\,avg}$  and  $F_{f\,avg}$  was determined only for the time period in which the values of these forces exceed the level of at least 50 N. The displacement parameter  $m$  consists in a small movement of the insert along its cutting edge, the purpose of which is the elimination of the effects of profile roughness of the cutting edge on the machined surface [2]. It occurs after the completion of the plunge feed movement of the cutting insert.

The experimental study was performed with the use of the Taguchi methodology. This methodology allows a simple, efficient, and systematic improvement of product quality and/or a reduction of its machining costs by using experimental research. Traditional designs of the experiment are complicated and difficult to use. Additionally, when the number of input parameters increases it is necessary to perform a large number of experiments [11]. Orthogonal arrays

designed by Taguchi allow for simultaneous and independent assessment of the influence of two or more input parameters on the output parameter when the minimal number of experiments is performed. In the Taguchi methodology, the lost function is defined which is the difference between the desired value and the experimental value. In turn, the lost function can be transformed to the signal-to-noise  $S/N$  ratio, which, depending on the characteristic of the examined quantity can be: the smaller-the better, the bigger-the better, and the nominal-the better. Values of the signal-to-noise  $S/N$  ratio for the cutting forces  $F_c$  and  $F_f$  were calculated adopting the smaller the better criterion (SB), with the use of the following equation:

$$S/N_{SB} = -10 \log \left( \frac{1}{n} \sum_{i=1}^n y_i^2 \right) \quad (1)$$

where:  $n$  – number of the measurements for a given layout of the experimental design,  $y_i$  – measured value of the investigated parameter. Regardless of the type of the optimized size, the largest value of the  $S/N$  coefficient corresponds to the optimal levels of the cutting parameters.

Three setting values of the cutting parameters were used in the experimental research  $v_c = 100, 200, 300$  m/min,  $f = 0.02, 0.04, 0.06$  mm/rev and  $m = 0, 0.025, 0.05$  mm, successively referred to as level 1, 2 and 3. The experimental research was conducted according to the experimental design based on the orthogonal array  $L_9$  (Table 1). For each layout of the experimental design 3 repetitions were performed. During the research, the following initial levels of the cutting parameter are assumed  $v_c = 200$  m/min,  $f = 0.02$  mm/rev,  $m = 0.025$  mm labeled as:  $v_c2, f1, m2$ .

Table 1. Setting levels and the corresponding values of the cutting parameters for particular layouts of the experimental design based on the orthogonal array  $L_9$

Layout No.	$v_c$	$f$	$m$	$v_c, \text{m/min}$	$f, \text{mm/rev}$	$m, \text{mm}$
1	$v_{c1}$	$f1$	$m1$	100	0.02	0
2	$v_{c1}$	$f2$	$m2$	100	0.04	0.025
3	$v_{c1}$	$f3$	$m3$	100	0.06	0.05
4	$v_{c2}$	$f1$	$m2$	200	0.02	0.025
5	$v_{c2}$	$f2$	$m3$	200	0.04	0.05
6	$v_{c2}$	$f3$	$m1$	200	0.06	0
7	$v_{c3}$	$f1$	$m3$	300	0.02	0.05
8	$v_{c3}$	$f2$	$m1$	300	0.04	0
9	$v_{c3}$	$f3$	$m2$	300	0.06	0.025

For each attempt at a final stage of the machining, a dwell is performed which is equal to two shaft rotations, aimed at assuring adequate dimensional accuracy

of the machined surface. The research was conducted on the shaft having dimensions of  $\varnothing 60 \times 300$  mm, made from 18CrMo4 steel. 27 grooves were cut on the shaft with dimensions of  $4 \times 4$  mm, which created 27 cylindrical surfaces with the width 6 mm (9 layouts of the design  $\times$  3 repetitions), used in the course of the research. In the next step, the shaft underwent the following thermo-chemical treatments: carburizing to the depth of 2 mm, hardening and tempering to the hardness of  $60 \pm 2$ HRC. The machining was carried out on the CNC lathe TUG 56-MN. Monolithic inserts TNGX1103085S-R-WZ of CBN100 grade which consisted of 50% CBN (grain size  $2 \mu\text{m}$ ) and 50% TiC used as the binder were used for finishing hard turning. The inserts were clamped in the tool holder CTJNR 2525 M11. During the research, a 0.2 mm-thick layer of the material was removed for each attempt. The test stand with the fixed testing shaft is shown in Figure 1.



Fig. 1. View of the test stand

The measurements of cutting forces  $F_c$  and  $F_f$  were performed using a Kistler dynamometer type 9272 connected to the charge amplifier, type 5070. The measured data were acquired using an A/C card type 2855A4 and software DynoWare. Statistical analysis of the results was performed using the software package Statistica v.12.

### 3. Results and their analysis

Values obtained from the measurements (mean from 3 repetitions) of the main cutting forces  $F_{c\text{ avg}}$ ,  $F_{c\text{ max}}$  and feed cutting forces  $F_{f\text{ avg}}$  and  $F_{f\text{ max}}$  with the



$F_{c\ avg}$ ,  $F_{c\ max}$  and  $F_{f\ avg}$ ,  $F_{f\ max}$ . In addition, these tables comprise the difference between maximum and minimum value of the  $S/N_{SB\ max} - S/N_{SB\ min}$  ratio calculated for each cutting parameter and the total mean value  $\eta$  of the  $S/N_{SB}$  ratio.

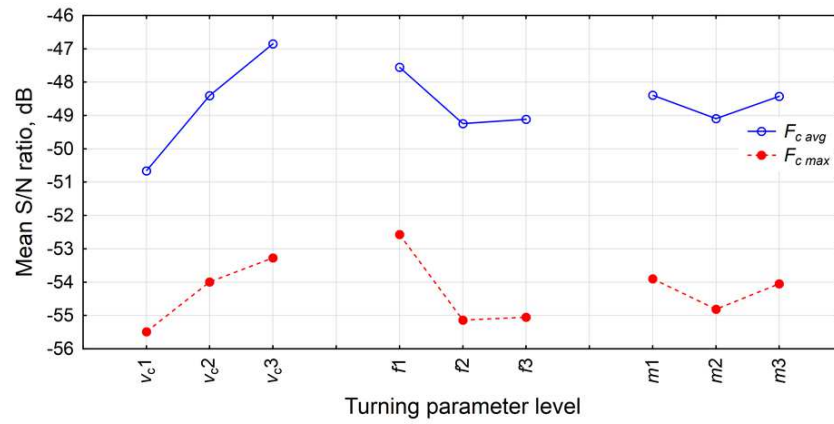


Fig. 2. The graph of mean values of the  $S/N_{SB}$  ratio for mean value  $F_{c\ avg}$  and maximum value  $F_{c\ max}$  of the main cutting force

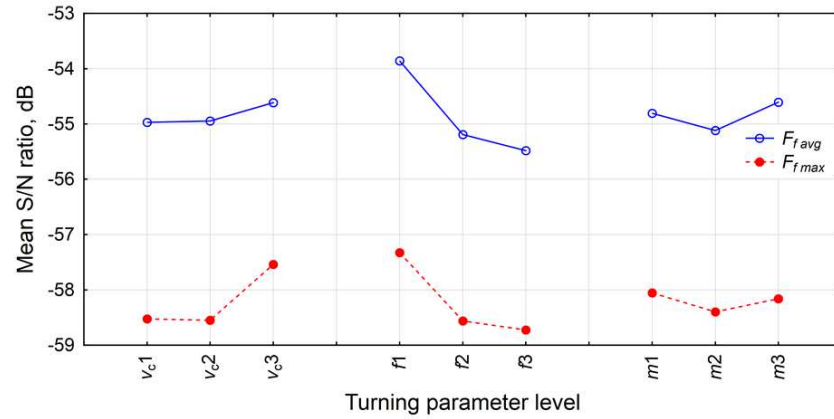


Fig. 3. The graph of mean values of the  $S/N_{SB}$  ratio for mean value  $F_{f\ avg}$  and maximum value  $F_{f\ max}$  of the feed cutting force

Analysis of Tables 3 and 4 and Fig. 2 and 3 shows that in most cases the optimal levels of cutting parameters (the highest values of  $S/N_{SB}$ ) are as follows:  $v_3, f_1, m_1$ . Only for  $F_{f\ avg}$  the optimal value of displacement  $m$  is at a level of  $m_3$ , i.e.  $m = 0.05$  mm. Summarizing the above experimental results, the most significant effect on the components of the cutting force  $F_c$  and  $F_f$  is the cutting speed  $v_c$  and feed  $f$  (the largest differences of the  $S/N_{SB\ max} - S/N_{SB\ min}$ ). The increase

in the cutting speed  $v_c$ , and the decrease in the feed  $f$  value reduces the components of cutting force. The displacement  $m$  has practically no effect on the value of the components of the cutting force, because it does not change the cut of an undeformed chip. This is confirmed by the smallest differences between  $S/N_{SB\ max} - S/N_{SB\ min}$  for this parameter.

Figure 4 shows an example chart of the main component  $F_c$  and the feed component  $F_f$  of the cutting force for the optimal values of the cutting parameters:  $v_c = 300$  m/min,  $f = 0.02$  mm/rev,  $m = 0$  mm.

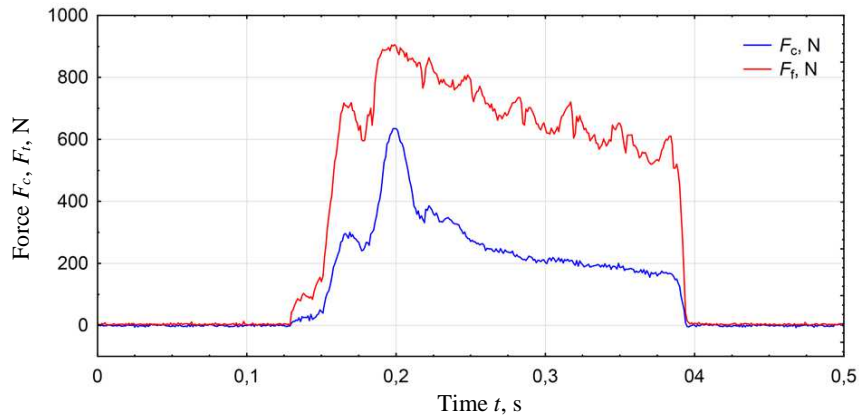


Fig. 4. An example chart of the main component  $F_c$  and feed component  $F_f$  of cutting force for the optimal values of the cutting parameters:  $v_c = 300$  m/min,  $f = 0.02$  mm/rev,  $m = 0$  mm

An almost 2-times higher value of the feed cutting force  $F_f$  (Fig. 4, Table 2) results from the fact that the insert TNGX1103085S-R-WZ has a protective chamfer of the cutting edge with a width of 0.1 mm, an angle of  $20^\circ$  relative to the rake face. Thus, the whole cutting process takes place within the chamfer.

At the next stage of the research, analysis of variance ANOVA was performed to determine which particular cutting parameters  $v_c$ ,  $f$ ,  $m$  significantly influences the components of the cutting force  $F_c$  and  $F_f$ . The analysis was performed at the significance level of 1% (99% confidence level). The results of the ANOVA for the cutting forces  $F_{c\ avg}$ ,  $F_{c\ max}$  and  $F_{f\ avg}$ ,  $F_{f\ max}$  are given in Tab. 5 and 6.

Analysis of variance ANOVA for the mean value of the main cutting force  $F_{c\ avg}$  (Table 5) indicates the greatest impact is the cutting speed  $v_c - 77.41\%$ , followed by the feed  $f - 18.61\%$ . However, as regards the maximum value of the main cutting force  $F_{c\ max}$ , the feed  $f - 58.11\%$  has the greatest influence, and next the cutting speed  $v_c - 34.94\%$ . Reasons for this situation should be sought in a large negative angle of the rake face of the insert (working in the area of protective chamfer) and in the fact that the maximum value of the force determines only the

highest and usually short-lasting moment of the cutting force (Fig. 4) which occurs the moment the insert enters the stock, and therefore the impact of the feed  $f$  is more important. Consideration of the mean value of the main cutting force  $F_{c\ avg}$  gives a more general picture of the participation of each cutting parameter in the total variance of this force. Therefore, the final conclusion should be drawn that the cutting speed  $v_c$  has a greater impact on the main cutting force  $F_c$ , than the feed  $f$ . Analysis of variance ANOVA for the feed cutting force  $F_f$  (Table 6) in both cases of the mean value  $F_{f\ avg}$  and the maximum value  $F_{f\ max}$  reveals that the feed  $f$  has the greatest impact on this force. This contribution amounts to 85.89% and 61.22%, respectively. Next is the cutting speed  $v_c$ , which accounts for 4.48% and 34.86% of total variance of the feed cutting force  $F_f$ , respectively. While the displacement parameter  $m$  for the cutting force  $F_c$  and  $F_f$  has minimum impact. The contribution of the order of a few percent in practice should be considered negligible.

Table 5. Results of the analysis of variance ANOVA for the mean value  $F_{c\ avg}$  and the maximum value  $F_{c\ max}$  of the main cutting force

Cutting parameter	Degrees of freedom	$F_{c\ avg}$				$F_{c\ max}$			
		Sum of squares	Mean square	$F$	Contribution, %	Sum of squares	Mean square	$F$	Contribution, %
$v_c$	2	22.039	11.019	115.453	77.41	7.688	3.844	76.935	34.94
$f$	2	5.300	2.650	27.763	18.61	12.787	6.394	127.964	58.11
$m$	2	0.943	0.471	4.938	3.31	1.429	0.714	14.300	6.49
Error	2	0.191	0.095		0.67	0.100	0.050		0.45
Total	8	28.472			100.00	22.005			100.00

Table 6. Results of the analysis of variance ANOVA for the mean value  $F_{f\ avg}$  and the maximum value  $F_{f\ max}$  of the feed cutting force

Cutting parameter	Degrees of freedom	$F_{f\ avg}$				$F_{f\ max}$			
		Sum of squares	Mean square	$F$	Contribution, %	Sum of squares	Mean square	$F$	Contribution, %
$v_c$	2	0.235	0.117	2.197	4.48	1.991	0.995	49.551	34.86
$f$	2	4.502	2.251	42.102	85.89	3.496	1.748	87.037	61.22
$m$	2	0.398	0.199	3.719	7.59	0.184	0.092	4.576	3.22
Error	2	0.107	0.053		2.04	0.040	0.020		0.70
Total	8	5.242			100.00	5.711			100.00

After determining the optimal levels of the cutting parameters, in the next step, a verification experiment is performed that in a practical way confirms the improvement of the optimized criteria. For optimal values of cutting parameters due to the cutting forces, the value of the  $S/N$  ratio was determined labeled as  $\eta_{opt}$  [12]:



$$\eta_{opt} = \eta + \sum_{i=1}^n (\eta_i - \eta) \quad (2)$$

where:  $\eta_i$  – value of the  $S/N$  ratio for the optimal level of the cutting parameter,  $i$  – number of parameters affecting the optimized criterion in a significant way.

Table 7 shows the results of the confirmation experiment using the optimal cutting parameters based on the criteria of cutting forces.

Table 7. The results of the confirmation experiment for the optimal values of the cutting parameters based on the criteria of cutting forces

	Initial cutting parameters		Optimal cutting parameters	
			Prediction	Experiment
Force	Level	$v_{c2}, f1, m2$	$v_{c3}, f1, m1$	$v_{c3}, f1, m1$
	$F_{c\ avg}$ , N	263		215
	$F_{c\ max}$ , N	397		415
	$F_{f\ avg}$ , N	543		508
	$F_{f\ max}$ , N	827		720
	$VB_B$ , $\mu\text{m}$	152		148
$F_{c\ avg}$	$S/B$ ratio, dB	-48.419	-45.520	-46.649
	Improvement of $S/B$ ratio, dB		1.750	
$F_{c\ max}$	$S/B$ ratio, dB	-51.976	-51.232	-52.361
	Improvement of $S/B$ ratio, dB		-0.385	
$F_{f\ avg}$	$S/B$ ratio, dB	-54.696	-53.594	-54.117
	Improvement of $S/B$ ratio, dB		0.579	
$F_{f\ max}$	$S/B$ ratio, dB	-58.350	-56.514	-57.147
	Improvement of $S/B$ ratio, dB		1.203	

Table 7 shows, that the average improvement in the  $S/N$  ratio is 0.787 dB. Thus, a change in the cutting of the initial level to the optimal level allowed a visible reduction of the value of the cutting forces. It should be noted that the optimal value of the cutting speed  $v_c$  for optimization criteria is 300 m/min. As a final optimal cutting parameters values are proposed  $v_c = 300$  m/min,  $f = 0.02$  mm/rev,  $m = 0.025$  mm ( $v_{c3}, f1, m2$ ), as this will allow the reduction of cutting forces by 20%. This, in turn, will provide more stable cutting conditions, minimizing the chance of vibrations, which have a very damaging effect on the CBN inserts. The proposed displacement level  $m2$  has no significant impact on the value of cutting forces.

For the proposed optimal cutting parameter levels  $v_{c3}, f1, m2$ , parameters of surface roughness were measured, which are as follows:  $Ra = 0.058$   $\mu\text{m}$ ,  $Rz = 0.42$

$\mu\text{m}$ ,  $R_{max} = 0.61 \mu\text{m}$ . These parameters fulfill the requirements for the properties of the surface layer as recommended by manufacturers of sealing rings.

#### 4. Conclusions

The paper presents the results of the optimization of cutting parameters due to the criteria of occurring cutting forces  $F_c$  and  $F_f$  using the Taguchi methodology. This made it possible to reduce the number of experiments carried out to determine the optimal levels of cutting parameters ( $v_c$ ,  $f$ ,  $m$ ). Summarizing the above results, the following conclusions can be drawn:

- On the basis of the mean value of the  $S/N$  ratio, the optimal cutting parameters levels for cutting forces  $F_c$  and  $F_f$  –  $v_c3$ ,  $f1$ ,  $m1$  ( $v_c = 300$  m/min,  $f = 0.02$  mm/rev,  $m = 0$  mm) can be determined.
- On the basis of a subsequent analysis of variance ANOVA, it can be seen that the cutting speed  $v_c$  accounts for 77.41%, and the feed  $f$  – for 18.61% of total variance of the main cutting force  $F_{c\text{ avg}}$ . For the feed cutting force  $F_f$ , in both cases, and  $F_{f\text{ avg}}$  and  $F_{f\text{ max}}$  revealed a greater impact feed  $f$ , this proportion is 85.89% and 61.22%, respectively. The contribution of the cutting speed  $v_c$ , amounts to 4.48% and 34.86%, respectively. Displacement  $m$  for cutting forces has a practically negligible impact on these quantities.
- For optimal cutting parameter levels, the results of the confirming experiments confirmed the above conclusions. It was possible to obtain a decrease in cutting forces by 20%, as compared to the initial cutting parameters.
- The proposed final optimal cutting parameters levels are as follows:  $v_c3$ ,  $f1$ ,  $m2$  ( $v_c = 300$  m/min,  $f = 0.02$  mm/rev,  $m = 0.025$  mm).

#### References

- [1] J.P. DAVIM Editor: Machining of hard materials. Springer-Verlag, London 2011.
- [2] M. FLEMING: Advanced concepts for hard turning gears. Gear Product News, Seco Tools, 2006, 22-27
- [3] D. HUDDLE: Taking the plunge. *Cutting Tool Engineering*, **54**(2002)2, 38-40.
- [4] B. PYTLAK: The surface texture of hardened 18CrMo4 steel after turning with plunge feed. *Advances in Manufacturing Science and Technology*, **38**(2014)1, 53-62.
- [5] DIN 3760: 1996: Rotary shaft lip type seals.
- [6] DIN 3761: 1984: Rotary shaft lip type seals for automobiles.
- [7] ISO 6194: 1990: Rotary shaft lip type seals.
- [8] R. FLITNEY: Seals and Sealing Handbook (5th Edition). Elsevier Ltd., Oxford 2007.
- [9] T. KUNSTFELD, W. HAAS: Shaft surface manufacturing methods for rotary shaft lip seals. *Sealing Technology*, **7**(2005), 5-9.
- [10] R. VOGT, H. METZNER: Machining of Shaft Surfaces for Radial Shaft Seals. Information materials of Freudenberg Simrit GmbH & Co. KG.

- [11] G. TAGUCHI: Introduction to quality engineering. Asian Productivity Organization (APO), Tokyo1990.
- [12] T.R. LIN: Optimization technique for face milling stainless steel with multiple performance characteristics. *Int. Journal of Advanced Manufacturing Technology*, **19**(2002)5, 330-335.

*Received in February 2015*