

# A novel trapezoidal profile of optimized diffraction grating for light trapping in thin silicon solar cells

MAHYAR DEHDAST<sup>1\*</sup>, ALI BAHRAMI<sup>2</sup>, SHAHRAM MOHAMMADNEJAD<sup>1</sup>

<sup>1</sup>Electrical and Electronics Engineering Department, Nanoptronics Research Center, Iran University of Science and Technology, Tehran, Iran

<sup>2</sup>Department of Electrical Engineering, Sahand University of Technology, Tabriz, Iran

\*Corresponding author: mahyardehdast@alumni.iust.ac.ir

In this paper, we propose a new design and comprehensive optimization process for improving the diffraction gratings used as the back reflector of silicon solar cells. For this process, the optimum refractive index and its corresponding available material which can be used as the grating material has been chosen as 1.57 and SiO<sub>2</sub>, respectively. Also, all of geometric parameters which affect the performance of the grating, such as periodicity, height and depth of grating profiles have been studied and the appropriate values for each of them have been proposed. In order to optimize the profile of grating, a transition from triangular to rectangular structure has been considered and finally a specific trapezoidal profile has been chosen as the optimized grating back reflector which enhances the cell efficiency up to 6%. Simulation results show that the different grating profiles have the same duty cycle and therefore use the same amounts of materials.

Keywords: diffraction grating, light trapping, quantum efficiency, solar cell.

## 1. Introduction

Higher thickness of an active layer in silicon solar cells increases the carrier recombination, resistivity and manufacturing costs. Therefore, although decreasing the active layer of silicon solar cells decreases the absorption probability of incident photons, the recent cells move toward ultra-thin silicon solar cells (UTSSC) [1]. On the other hand, the effective absorption region of the photons will be reduced by degrading the thickness. Hence, there will be a requirement for the light trapping techniques in order to enhance the absorption probability by increasing the optical path length (OPL). The various light trapping methods which have been recently suggested are included in texturing [2, 3], plasmonics [4, 5], layered media [6–8], diffractions [9] and so on. Also the third-generation photovoltaics have been investigated in order to increase the total cell efficiency [10–12]. Among these methods, the periodic structures are commonly used due to greater control on geometric parameters of structure and higher effect on light trapping. Diffraction gratings are one of the periodic structures which result in an improvement in the absorption and cell efficiency with increasing the OPL of photons [13]. These

structures can be used as the back reflector structure of solar cells, scatter the incident light in the different directions and enhance the quantum efficiency (QE) and therefore total efficiency of the cell. The effective parameters in the operation of diffraction gratings are included in the material and geometry of grating.

In this paper, we propose a new design of the diffraction grating back reflector and optimize different parameters in order to achieve the highest achievable light trapping. A grating structure has been designed and optimized in order to return the non-absorbed photons of a specified bandwidth into the silicon medium. The optimum refractive index and its corresponding available material which can be used as the grating material will be chosen. Also, all of geometric parameters which affect the performance of the grating, such as periodicity, height and depth of grating profiles have been studied and the appropriate values for each of them have been proposed, which results in an increase of 6% of cell's efficiency.

A brief theoretical background of diffraction gratings and the design parameters of the proposed structure will be presented in Section 2. In Section 3, different effective parameters of grating will be optimized. Finally, the effect of the optimized back reflector structure on the cell's electrical and optical characteristics will be discussed in Section 4.

## 2. Design

Diffraction grating is a periodic structure which scatters the incident light beam in different angles. The diffraction angles can be defined as [14]

$$\sin(\theta_m) = \frac{m\lambda}{nd} \quad (1)$$

where  $m$ ,  $\lambda$ ,  $n$  and  $d$  are diffraction order, incident wavelength, refractive index and period of grating, respectively. In periodic structures, the effective intensity of light inside the structure is increased by  $4n^2$ . Therefore, the optical absorption of the structure can be calculated as [15]

$$A = 1 - \frac{1}{1 + 4n^2 \alpha T_c} \quad (2)$$

where  $\alpha$  and  $T_c$  are the absorption coefficient and thickness of the absorber layer, respectively. This effect results in the corresponding increment of quantum efficiency. Increasing the quantum efficiency (QE) enhances the short circuit current as follows [9]:

$$I_{sc} = \frac{q}{hc} \int_{\lambda_{min}}^{\lambda(E_g)} \lambda \text{QE}(\lambda) S(\lambda) d\lambda \quad (3)$$

where  $q$ ,  $h$ ,  $c$  and  $S(\lambda)$  are elementary charge, Planck's constant, light speed and the solar spectrum, respectively. Therefore, an optimized light trapping structure can in-

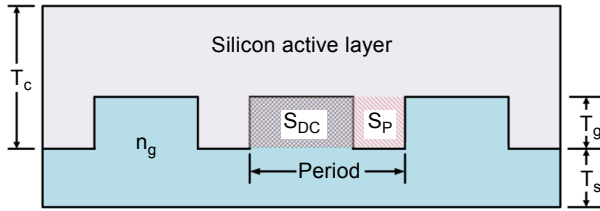


Fig. 1. Schematic structure of proposed grating.

roduce an extensive enhancement on the short circuit current and increase the total cell efficiency. The schematic structure of the grating back reflector is depicted in Fig. 1.

As can be seen in Fig. 1, the important parameters which can affect the performance of the grating structure are shown in Fig. 1. The duty cycle (DC) of grating can be calculated with dividing its area on the total area of period (P) equal to  $S_{DC}/S_P$ . The profile of grating can be enhanced with optimizing the refractive index, duty cycle and period of grating. For the first step, the most suitable material should be chosen.

Rigorous coupled wave analysis (RCWA) has been utilized in order to simulate the light profile in proposed periodic structures (diffraction grating) and verify the performance of the structure under the defined circumstances. This method provides an absorption spectrum of the whole structure to complete the modeling process of the solar cell. In the calculation of RCWA method, we assumed a two-dimensional structure which is periodic in the horizontal direction. However, we have considered just one period for simulation. In fact, the considered simulation region which is just one of the infinite periods is the worst case.

So, the efficiency of the silicon solar cell has been calculated for different refractive indices of grating. The effect of refractive index variations on the cell efficiency is shown in Fig. 2.

As can be seen in Fig. 2, the optimum refractive index of grating is achieved as 1.57. There are some available materials such as  $Al_2O_3$  and  $SiO_2$  with the refractive indices

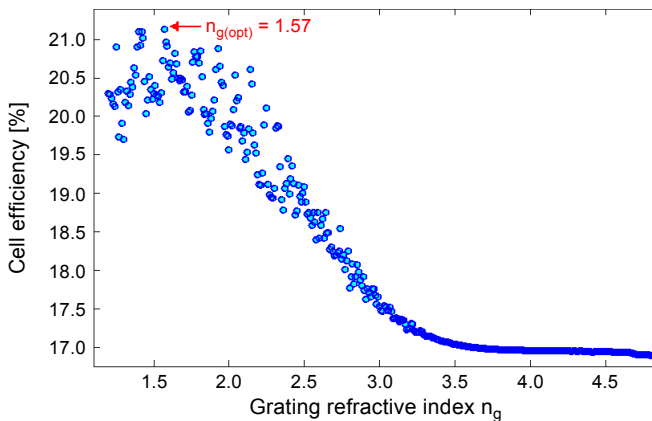


Fig. 2. The curve of cell efficiency versus grating refractive index.

near the optimum value. In this paper, the  $\text{SiO}_2$  has been chosen as the most suitable material of the proposed grating-based back reflector. In next sections, the  $\text{SiO}_2$  proposed structure will be optimized.

### 3. Optimization procedure

From Figure 1, with considering  $\text{SiO}_2$  as the material used, the duty cycle and period of grating should be optimized. For a typical range of the period, the duty cycle of grating can be changed from zero to 100%. The effects of grating duty cycle, period, depth  $T_g$  and sub-thickness  $T_s$  variations on the cell efficiency are presented in Fig. 3.

Figure 3a shows the effect of the duty cycle and the period of grating on the efficiency of the silicon cell. The optimum combination of the period and duty cycle of grating has been obtained as point *A* with the values of 796 nm and 60%, respectively. With utilizing these values for the period and duty cycle of grating, the depth and sub-thickness of grating has been optimized and the results of simulation are depicted in

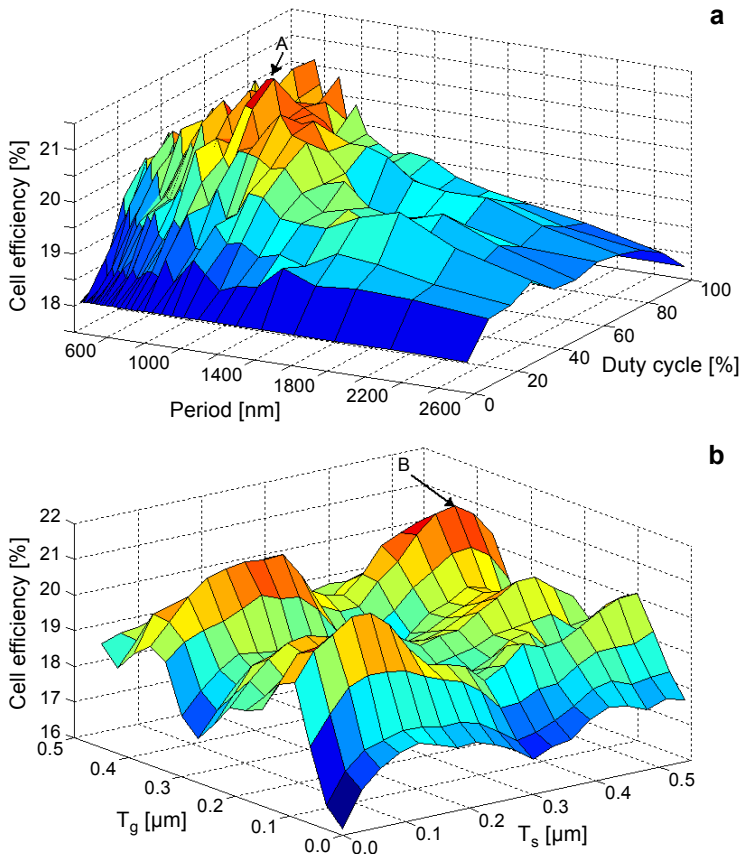


Fig. 3. The effects of grating geometry variation on the cell efficiency: variations of period and duty cycle (a), and variations of depth  $T_g$  and sub-thickness  $T_s$  (b).

Fig. 3b. The optimum values for depth and sub-thickness of grating which can be referred to point B are 360 and 480 nm, respectively.

The achieved values for different parameters of grating have been calculated for the conventional rectangular profile. This profile can be modified to a more optimized structure with increasing the  $W_b$  from Period  $\times$  DC to Period and decreasing  $W_t$  from Period  $\times$  DC to zero. Therefore, the profile of grating can be varied from a rectangular to triangular structure. The proposed structure of the grating back reflector is presented in Fig. 4.

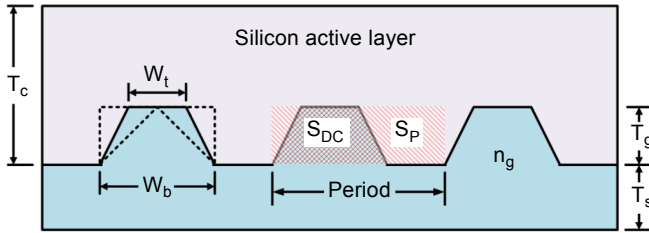


Fig. 4. Proposed profile of grating back reflector.

The duty cycle of grating which has been optimized to 60% presents the percentage of material used for a grating profile. Hence, it seems that the duty cycle (and therefore the amount of material used) should be constant for different grating profiles. The effect of changing  $W_t$  and  $W_b$  on the performance of the proposed structure has been simulated and shown in Fig. 5.

As can be seen in Fig. 5, the optimum combination of parameters  $W_t$  and  $W_b$  are obtained as 298 and 597 nm, respectively. It is obvious that the corresponding structure of grating will be a trapezoidal profile which can extremely enhance the performance of the solar cell. The new duty cycle corresponding to a trapezoidal profile is calculated

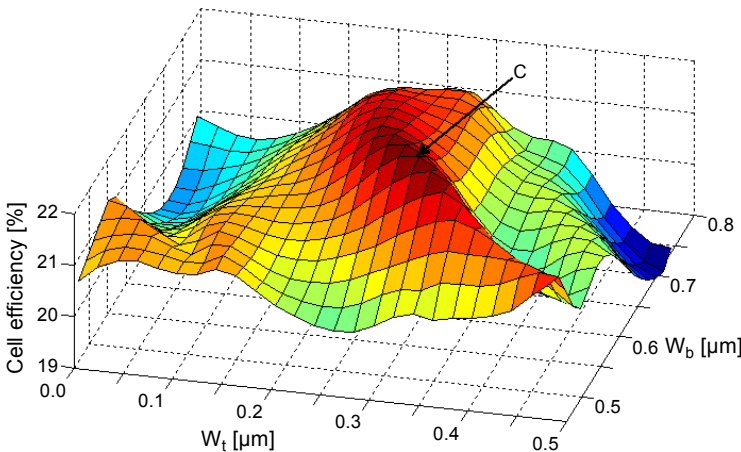


Fig. 5. The curve of cell efficiency versus  $W_t$  and  $W_b$ .

as 56%. Therefore, it can be concluded that different grating profiles present the similar duty cycle.

#### 4. Discussion

After the optimization procedure, all of the grating physical parameters are chosen. These parameters which construct the configuration of the proposed back reflector are given in the Table. Besides the grating structure with utilizing  $\text{SiO}_2$  as the available material, the proposed structure has been simulated and optimized for the ideal structure with the refractive index of 1.57. The optimum values for physical parameters which have been achieved for the ideal refractive index of 1.57 are also presented in the Table.

The trapezoidal grating structure has been utilized as the back reflector of silicon solar cell. The absorption spectrum and quantum efficiency of silicon solar cell without

T a b l e. The obtained values of optimum grating structure.

Material	Duty cycle [%]	Period [nm]	$T_g$ [nm]	$T_s$ [nm]	$W_t$ [nm]	$W_b$ [nm]	Current density [mA/cm <sup>2</sup> ]	Cell efficiency [%]
$n_g = 1.57$	55	644	100	100	214	474	34	22.35
$\text{SiO}_2$	60	796	360	480	298	597	33.6	22.1

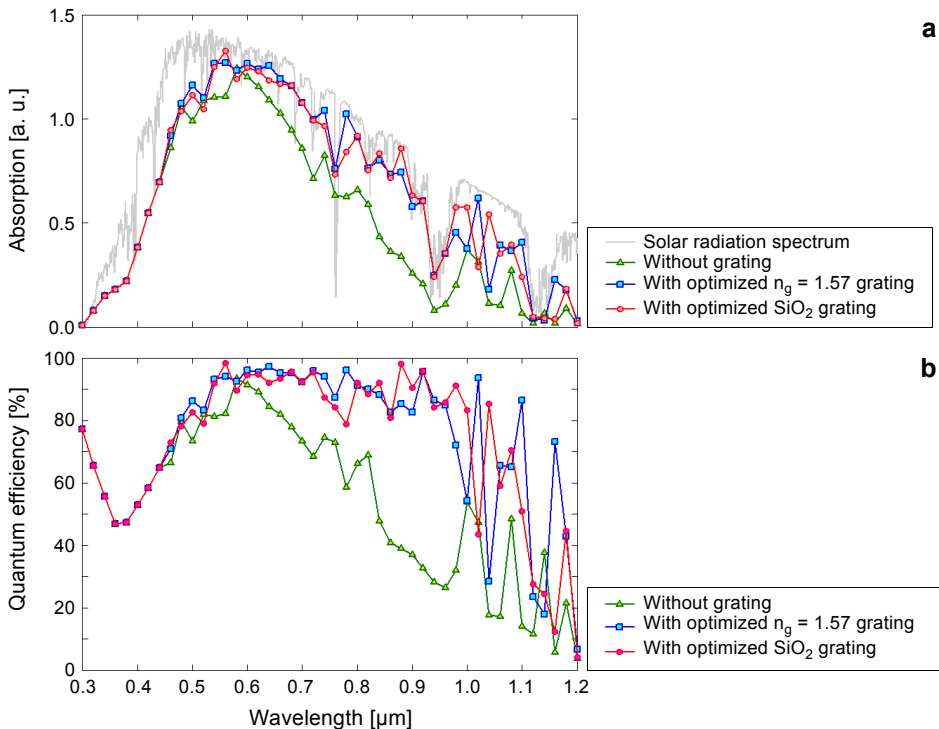


Fig. 6. The absorption spectrum (a), and quantum efficiency (b) of silicon solar cell.

and with optimized grating back reflector (ideal and SiO<sub>2</sub> grating structure) are shown in Fig. 6.

Figures 6a and 6b emphasize that the back reflector structure has the lowest impact on the device performance in lower wavelengths. Therefore, the optimized diffractive back reflectors remarkably affect the performance of silicon solar cell in the range of solar spectrum peak (650 nm). The design wavelength  $\lambda$  in our calculations has been assumed as 650 nm and we designed the grating structure for this wavelength. Also, it can be seen that the back reflector with utilizing SiO<sub>2</sub> shows almost the same behavior as the ideal refractive index. The current-voltage characteristics of silicon solar cell with optimized gratings can be seen in Fig. 7.

The comparison of current-voltage curves for silicon solar cell with and without utilizing optimized gratings show a current density enhancement of 9.4 mA/cm<sup>2</sup> for the best case. The simulation results about absorption and short circuit current shows a good coincidence with Eqs. (2) and (3). It should be noticed that the proposed structures are utilized as the back reflector of typical silicon solar cell with the cell thickness

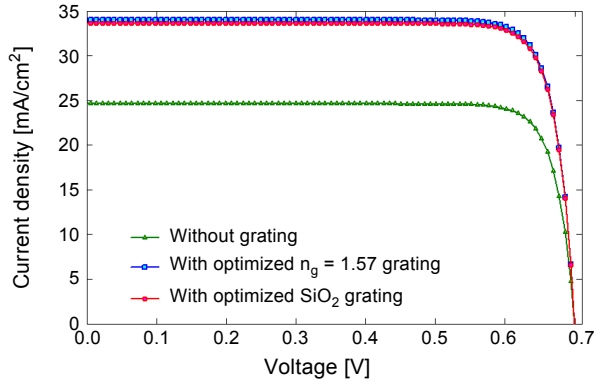


Fig. 7. The current-voltage curve of silicon solar cell with proposed optimized gratings.

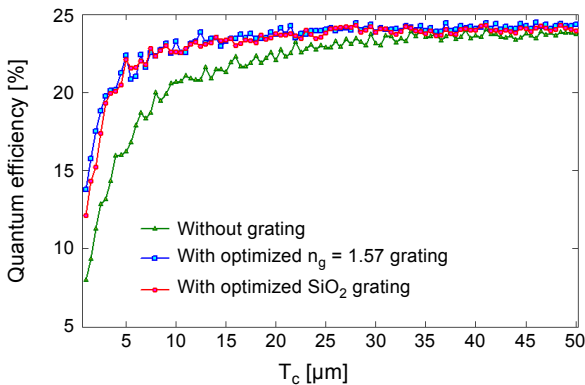


Fig. 8. The curve of cell efficiency *versus* the variations of cell thickness for two cases: with and without optimized gratings.

of 5  $\mu\text{m}$ . The thickness of the absorber layer affects the device performance and changes the dependence of device performance on the back reflector structure. The curve of cell efficiency *versus* the thickness of the absorber layer is shown in Fig. 8. for two cases: with and without optimized gratings.

As can be understood from Fig. 8, the performance of solar cells with lower absorber layer thicknesses shows the higher enhancement for the case of utilizing the optimized reflector structure.

## 5. Conclusion

We proposed a new trapezoidal profile for the grating back reflector with optimized geometrical parameters in order to be used in thin silicon solar cells. For conventional binary grating, the optimum refractive index of 1.57 corresponds to the available material of  $\text{SiO}_2$  which can be used as the grating material. Also, all of geometric parameters which affect the performance of the grating, such as periodicity, height and depth of grating profiles have been studied and the appropriate values for each of them have been proposed. In order to optimize the profile of grating, a transition from triangular to rectangular structure has been considered and finally a specific trapezoidal profile has been chosen as the optimized grating back reflector which enhances the cell efficiency up to 6%. The same duty cycle which has been achieved from the simulations of different grating profiles emphasizes that the amount of materials used for all of grating structures will be constant.

## References

- [1] MALLICK S.B., AGRAWAL M., PEUMANS P., *Optimal light trapping in ultra-thin photonic crystal crystalline silicon solar cells*, Optics Express **18**(6), 2010, pp. 5691–5706.
- [2] BAHRAMI A., MOHAMMADNEJAD S., SOLEIMANINEZHAD S., *Photovoltaic cells technology: principles and recent developments*, Optical and Quantum Electronics **45**(2), 2013, pp. 161–197.
- [3] BASORE P.A., *Numerical modeling of textured silicon solar cells using PC-ID*, IEEE Transactions on Electron Devices **37**(2), 1990, pp. 337–343.
- [4] FERRY V.E., VERSCHUUREN M.A., HONGBO B.T LI, VERHAGEN E., WALTERS R.J., SCHROPP R.E.I., ATWATER H.A., POLMAN A., *Light trapping in ultrathin plasmonic solar cells*, Optics Express **18**(S2), 2010, pp. A237–A245.
- [5] PILLAI S., CATCHPOLE K.R., TRUPKE T., GREEN M.A., *Surface plasmon enhanced silicon solar cells*, Journal of Applied Physics **101**(9), 2007, article ID 093105.
- [6] PARK Y., DROUARD E., EL DAIF O., LETARTRE X., VIKTOROVITCH P., FAVE A., KAMINSKI A., LEMITI M., SEASSAL C., *Absorption enhancement using photonic crystals for silicon thin film solar cells*, Optics Express **17**(16), 2009, pp. 14312–14321.
- [7] ZENG L., BERMEL P., YI Y., ALAMARIU B.A., BRODERICK K.A., LIU J., HONG C., DUAN X., JOANNOPOULOS J., KIMERLING L.C., *Demonstration of enhanced absorption in thin film Si solar cells with textured photonic crystal back reflector*, Applied Physics Letters **93**(22), 2008, article ID 221105.
- [8] BERMEL P., CHIYAN LUO, LIRONG ZENG, KIMERLING L.C., JOANNOPOULOS J.D., *Improving thin-film crystalline silicon solar cell efficiencies with photonic crystals*, Optics Express **15**(25), 2007, pp. 16986–17000.



- [9] DEWAN R., KNIPP D., *Light trapping in thin-film silicon solar cells with integrated diffraction grating*, Journal of Applied Physics **106**(7), 2009, article ID 074901.
- [10] TEKEREK S., KUDRET A., ALVER Ü., *Dye-sensitized solar cells fabricated with black raspberry, black carrot and rosella juice*, Indian Journal of Physics **85**(10), 2011, pp. 1469–1476.
- [11] SAHA S., MANIK N.B., *Enhancement of efficiency of phenosafranin based organic photovoltaic devices using nano particles*, Indian Journal of Physics **86**(7), 2012, pp. 605–611.
- [12] SAHA S., MANIK N.B., *Effect of different concentration of TiO<sub>2</sub> nanoparticles in phenosafranin dye-based organic photovoltaic device*, Indian Journal of Physics **89**(9), 2015, pp. 907–913.
- [13] GAIGE ZHENG, LINHUA XU, MIN LAI, YUNYUN CHEN, YUZHU LIU, XIANGYIN LI, *Enhancement of optical absorption in amorphous silicon thin film solar cells with periodical nanorods to increase optical path length*, Optics Communications **285**(10–11), 2012, pp. 2755–2759.
- [14] NOVOTNY L., HECHT B., *Principles of Nano-Optics*, Cambridge University Press, 2012.
- [15] KEN XINGZE WANG, ZONGFU YU, VICTOR LIU, YI CUI, SHANHUI FAN, *Absorption enhancement in ultrathin crystalline silicon solar cells with antireflection and light-trapping nanocone gratings*, Nano Letters **12**(3), 2012, pp. 1616–1619.

*Received April 5, 2016  
in revised form July 20, 2016*