

ANALYSIS OF MODE I CONDUCTING CRACK IN PIEZO-ELECTRO-MAGNETO-ELASTIC LAYER

B. ROGOWSKI

Department of Mechanics of Materials
 Technical University of Lodz
 Al. Politechniki 6, 93-590 Łódź, POLAND
 E-mail: bogdan.rogowski@p.lodz.pl

Within the theory of linear magnetoelasticity, the fracture analysis of a magneto – electrically dielectric crack embedded in a magnetoelastic layer is investigated. The prescribed displacement, electric potential and magnetic potential boundary conditions on the layer surfaces are adopted. Applying the Hankel transform technique, the boundary – value problem is reduced to solving three coupling Fredholm integral equations of second kind. These equations are solved exactly. The corresponding semi – permeable crack – face magnetoelastic boundary conditions are adopted and the electric displacement and magnetic induction of crack interior are obtained explicitly. This field inside the crack is dependent on the material properties, applied loadings, the dielectric permittivity and magnetic permeability of crack interior, and the ratio of the crack length and the layer thickness. Field intensity factors are obtained as explicit expressions.

Key words: magneto electro elastic layer, Penny –shaped crack, dielectric crack, field intensity factors, exact solution.

1. Introduction

Materials having magnetoelastic coupling effects have found increasing applications in engineering structures, particularly in smart materials intelligent structures. The effects of magnetoelastic coupling have been observed in single phase materials where simultaneous magnetic and electric ordering coexists and in two phase composites where the participating phases are piezoelectric and piezomagnetic. These “smart” materials are extensively used as electric packaging, sensors and actuators, magnetic field probes, acoustic and ultrasonic devices, hydrophones and transducers with the responsibility of electromechanical energy conversion. When subjected to mechanical, magnetic and electrical loads in service, these magnetoelastic composites can fail prematurely due to some defects, namely cracks, holes and others, arising during their manufacturing processes. Therefore, it is of great importance to study the magnetoelastic interaction and fracture behaviours of magnetoelastic materials. On the other hand, composites consisting of piezoelectric and piezomagnetic components have found their ways increasingly in applications in engineering structures. This is because these composites have some new properties of magnetoelectricity with the secondary piezoelectric effects which are not found in single phase piezoelectric or piezomagnetic materials. In some cases, the magnetoelectric effect of piezoelectric / piezomagnetic composites can be obtained by a hundred times longer than that of a single phase magnetoelectric material. Recently, Chen *et al.* (2004) derived a general solution for a transversely isotropic electromagnetoelastic material. In consequence, the components of the coupled field are expressed by five mono harmonic functions. More recently, a penny shaped crack in a magnetoelastic material has been considered. For example, Zhao *et al.* (2006) analyzed a penny shaped crack in a magnetoelastic medium. Niraula and Wang (2006) derived an exact closed form solution for a penny shaped crack in a magnetoelastic material in a temperature field. The electro magnetic field inside the crack was taken into account and closed form solutions were derived for an impermeable and permeable crack (Rogowski, 2011). Wang and Mai (2007) and Rogowski (2007) discussed the different

electromagnetic boundary conditions on the crack- faces in PEMO – elastic materials. On the other hand, Zhong and Li (2007; 2008), Rogowski (2007), Zhong (2009) extended the semi permeable crack face electric boundary conditions proposed by Hao and Shen (1994) to analyze the PEMO elastic fields induced by dielectric cracks. However, all of the studies considered only infinite body and numerical procedures were used to obtained the results of approximate type. To the best of the author's knowledge, the penny shaped crack problems for the layer and limited permeable cracks have not been addressed yet, in an exact form. Motivated by this the author of this paper investigates a PEMO elastic layer, with an electrically and magnetically conducting crack under prescribed displacement, electric potential and magnetic potential boundary loading, to show exact solutions. Such solutions depend on a large number of material parameters, in our analysis it is seventeen, making any solution other than explicit analytical ones impractical.

2. Basic equations in magnetoelastic theory

The constitutive equations within the framework of the linearly magnetoelastic theory, in an axially symmetric problem, can be written as

$$\begin{bmatrix} \sigma_r \\ \sigma_\theta \\ \sigma_z \\ D_z \\ B_z \end{bmatrix} = \begin{bmatrix} c_{11} & c_{12} & c_{13} & e_{31} & q_{31} \\ c_{12} & c_{11} & c_{13} & e_{31} & q_{31} \\ c_{13} & c_{13} & c_{33} & e_{33} & q_{33} \\ e_{31} & e_{31} & e_{33} & -\varepsilon_{33} & -d_{33} \\ q_{31} & q_{31} & q_{33} & -d_{33} & -\mu_{33} \end{bmatrix} \begin{bmatrix} u_{r,r} \\ u_r / r \\ u_{z,z} \\ \varphi_{,z} \\ \psi_{,z} \end{bmatrix},$$

$$\begin{bmatrix} \sigma_{rz} \\ D_r \\ B_r \end{bmatrix} = \begin{bmatrix} c_{44} & c_{44} & e_{15} & q_{15} \\ e_{15} & e_{15} & -\varepsilon_{11} & -d_{11} \\ q_{15} & q_{15} & -d_{11} & -\mu_{11} \end{bmatrix} \begin{bmatrix} u_{r,z} \\ u_{z,r} \\ \varphi_{,r} \\ \psi_{,r} \end{bmatrix} \quad \psi_{,r} = \frac{\partial \psi}{\partial r}, \quad (2.1)$$

$$E_r = -\varphi_{,r}, \quad E_z = -\varphi_{,z}, \quad H_r = -\psi_{,r}, \quad H_z = -\psi_{,z}$$

where u_r , u_z , φ , ψ are the elastic displacement, electric potential and magnetic potential, respectively; σ_r , σ_θ , σ_z , σ_{rz} , D_r , D_z , B_r , B_z , E_r , E_z , H_r , H_z are the components of stress, electric displacement, magnetic induction, electric field and magnetic field, respectively; e_{kl} , q_{kl} and d_{kl} are the piezoelectric, piezomagnetic and magnetoelectric constants, respectively; c_{kl} , ε_{kl} and μ_{kl} are the elastic stiffness, the dielectric permittivities and the magnetic permeabilities, respectively.

Moreover, from the equations of equilibrium

$$\begin{aligned} \sigma_{r,r} + \sigma_{rz,z} + (\sigma_r - \sigma_\theta)/r &= 0, \\ \sigma_{rz,r} + \sigma_{z,z} + (\sigma_{rz})/r &= 0, \\ D_{r,r} + D_{z,z} + (D_r)/r &= 0, \\ B_{r,r} + B_{z,z} + (B_r)/r &= 0, \quad B_{r,r} = \frac{\partial B_r}{\partial r}, \end{aligned} \quad (2.2)$$

the elastic displacements, electric potential and magnetic potential will satisfy the basic governing equations as follows

$$\begin{aligned}
c_{11}B_1u_r + c_{44}D^2u_r + (c_{13} + c_{44})D\frac{\partial u_z}{\partial r} + (e_{31} + e_{15})D\frac{\partial \phi}{\partial r} + (q_{31} + q_{15})D\frac{\partial \psi}{\partial r} &= 0, \\
c_{44}B_0u_z + c_{33}D^2u_z + (c_{13} + c_{44})D\frac{\partial [ru_r]}{r\partial r} + (e_{15}B_0 + e_{33}D^2)\phi + (q_{15}B_0 + q_{33}D^2)\psi &= 0, \\
(e_{31} + e_{15})D\frac{\partial [ru_r]}{r\partial r} + (e_{15}B_0 + e_{33}D^2)u_z - (\varepsilon_{11}B_0 + \varepsilon_{33}D^2)\phi - (d_{11}B_0 + d_{33}D^2)\psi &= 0, \\
(q_{31} + q_{15})D\frac{\partial [ru_r]}{r\partial r} + (q_{15}B_0 + q_{33}D^2)u_z - (d_{11}B_0 + d_{33}D^2)\phi - (\mu_{11}B_0 + \mu_{33}D^2)\psi &= 0
\end{aligned} \tag{2.3}$$

where the following differential operators are introduced

$$B_k = \frac{\partial^2}{\partial r^2} + \frac{1}{r} \frac{\partial}{\partial r} - \frac{k}{r^2}; \quad k = 0, 1; \quad D = \frac{\partial}{\partial z}; \quad D^2 = \frac{\partial^2}{\partial z^2}. \tag{2.4}$$

The general solution of Eqs (2.3) are as follows

$$\begin{aligned}
u_r(r, z) &= \sum_{i=1}^4 a_{1i} \lambda_i \frac{\partial \phi_i(r, z_i)}{\partial r}, \\
u_z(r, z) &= \sum_{i=1}^4 \frac{a_{2i}}{\lambda_i} \frac{\partial \phi_i(r, z_i)}{\partial z}, \\
\phi(r, z) &= - \sum_{i=1}^4 \frac{a_{3i}}{\lambda_i} \frac{\partial \phi_i(r, z_i)}{\partial z}, \\
\psi(r, z) &= - \sum_{i=1}^4 \frac{a_{4i}}{\lambda_i} \frac{\partial \phi_i(r, z_i)}{\partial z}.
\end{aligned} \tag{2.5}$$

The functions $\phi_i(r, z_i)$ ($i = 1, 2, 3, 4$) satisfy the following mono harmonic equations

$$\left(\frac{\partial^2}{\partial r^2} + \frac{1}{r} \frac{\partial}{\partial r} + \frac{1}{\lambda_i^2} \frac{\partial^2}{\partial z^2} \right) \phi_i(r, z_i) = 0, \quad (i = 1, 2, 3, 4) \tag{2.6}$$

where $z_i = \lambda_i z$ and λ_i , satisfying $\text{Re}(\lambda_i) > 0$, are the four eigenvalues of the characteristic equation which is an eight degree polynomial

$$a\lambda^8 + b\lambda^6 + c\lambda^4 + d\lambda^2 + e = 0. \tag{2.7}$$

The material parameters a , b , c , d and e are defined in the Appendix by Eq.(A1). The parameters a_{ji} ; $j = 1, 2, 3, 4$; $i = 1, 2, 3, 4$ are given as follows

$$a_{ji} = \frac{a_j \lambda_i^6 + b_j \lambda_i^4 + c_j \lambda_i^2 + d_j}{a_2 \lambda_i^6 + b_2 \lambda_i^4 + c_2 \lambda_i^2 + d_2} \quad (2.8)$$

where a_j, b_j, c_j, d_j are given in the Appendix by Eq.(A2). Note that $a_{2i} \equiv 1$.

Then from Eqs (2.1) together with (2.5) the components of stress, electric displacement and magnetic induction can be derived.

We have

$$\begin{aligned} \sigma_r &= -\sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} \frac{\partial^2 \varphi_i}{\partial z^2} - (c_{11} - c_{12}) \frac{u_r}{r}, \\ \sigma_\theta &= -\sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} \frac{\partial^2 \varphi_i}{\partial z^2} - (c_{11} - c_{12}) \frac{\partial u_r}{\partial r}, \\ \sigma_z &= \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i^3} \frac{\partial^2 \varphi_i}{\partial z^2}, & \sigma_{rz} &= \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} \frac{\partial^2 \varphi_i}{\partial r \partial z}, \\ D_r &= \sum_{i=1}^4 a_{6i} \lambda_i \frac{\partial^2 \varphi_i}{\partial r \partial z}, & D_z &= \sum_{i=1}^4 \frac{a_{6i}}{\lambda_i} \frac{\partial^2 \varphi_i}{\partial z^2}, \\ B_r &= \sum_{i=1}^4 a_{7i} \lambda_i \frac{\partial^2 \varphi_i}{\partial r \partial z}, & B_z &= \sum_{i=1}^4 \frac{a_{7i}}{\lambda_i} \frac{\partial^2 \varphi_i}{\partial z^2} \end{aligned} \quad (2.9)$$

where

$$\begin{aligned} a_{5i}(q_{31} + q_{15}) &= c_{44}q_{31} - c_{13}q_{15} + (c_{44}q_{31}\lambda_i^2 + c_{11}q_{15})a_{li} + (e_{31}q_{15} - e_{15}q_{31})a_{3i}, \\ a_{6i}(d_{11} - d_{33}\lambda_i^2) &= d_{11}e_{33} - e_{15}d_{33} - (e_{15}d_{33}\lambda_i^2 + e_{31}d_{11})a_{li} + (\varepsilon_{33}d_{11} - \varepsilon_{11}d_{33})a_{3i}, \\ a_{7i}(\mu_{11} - \mu_{33}\lambda_i^2) &= \mu_{11}q_{33} - q_{15}\mu_{33} - (q_{15}\mu_{33}\lambda_i^2 + q_{31}\mu_{11})a_{li} + (\mu_{11}d_{33} - \mu_{33}d_{11})a_{3i}. \end{aligned} \quad (2.10)$$

It should be noted that the general solutions given by Eqs (2.5) and (2.9) are valid for the cases when the eigenvalues λ_i ($i=1,2,3,4$) are distinct. In this paper, equal roots (the special cases) are viewed as the limiting case of the distinct roots. For a pure piezoelectric medium we have $a_{7i} \equiv 0$ and $a_{4i} \equiv 0$ and

$$\begin{aligned} a_{3i}(e_{31} + e_{15}) &= c_{13} + c_{44} - (c_{11} - c_{44}\lambda_i^2)a_{li}, \\ a_{5i}(e_{31} + e_{15}) &= c_{44}e_{31} - c_{13}e_{15} + (c_{11}e_{15} + c_{44}e_{31}\lambda_i^2)a_{li}, \\ a_{6i}(\varepsilon_{11} - \varepsilon_{33}\lambda_i^2) &= e_{33}\varepsilon_{11} - e_{15}\varepsilon_{33} - (e_{31}\varepsilon_{11} + e_{15}\varepsilon_{33}\lambda_i^2)a_{li}. \end{aligned} \quad (2.11)$$

It is easily verified, by direct substitution, that the equilibrium Eqs (2.2)_{1,2}, electric and magnetic charge conservation Eqs (2.2)_{3,4} are satisfied by general solution (2.9).

3. Penny shaped dielectric and magnetic crack in the PEMO elastic layer

Consider a penny shaped dielectric and assume that a magnetic crack is located in the middle plane of a transversely isotropic PEMO elastic layer as shown in Fig.1a. The cylindrical coordinate system (r, θ, z) is used with the poling axis as the z axis. It is further assumed that the crack is centrally situated at the circle $r \leq a$ and the width of a layer is $2h$. A constant displacement δ_0 , electric potential φ_0 and magnetic potential ψ_0 are imposed on the layer surfaces, namely

$$u_z(r, \pm h) = \pm \delta_0; \quad \varphi(r, \pm h) = \mp \varphi_0; \quad \psi(r, \pm h) = \mp \psi_0. \quad (3.1)$$

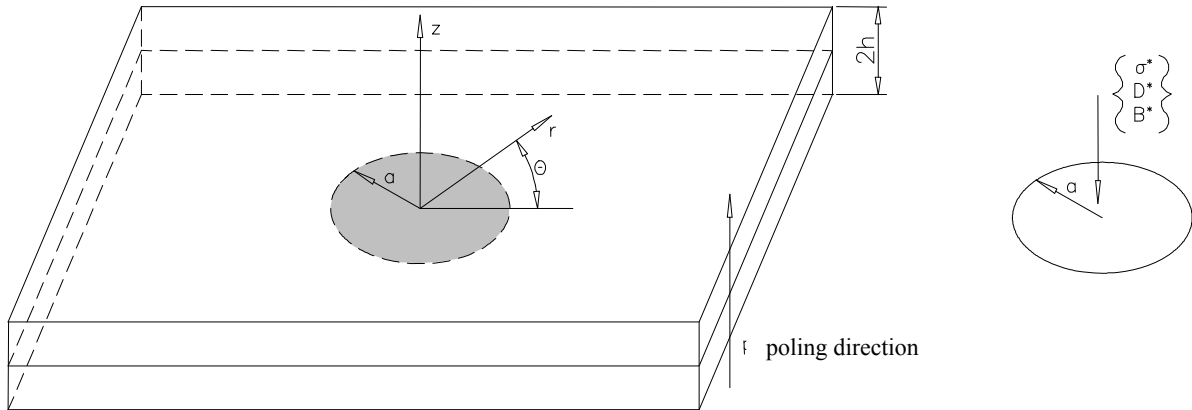


Fig.1a. Geometry of a magnetoelectroelastic layer with a penny shaped crack; the quantities σ^* , D^* and B^* are in the circular region $r \leq a$ in a plate without a crack.

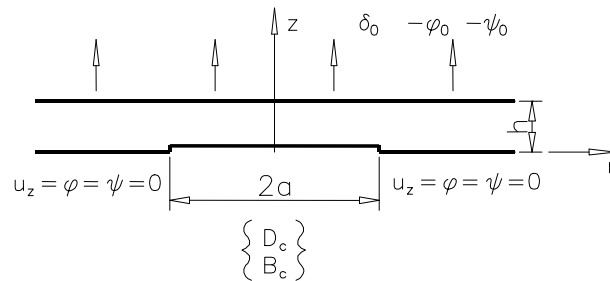


Fig.1b. The illustration of the boundary conditions; the following should be added to the crack surface: $-\sigma^*$, $-D^*$ and $-B^*$; $\sigma_{zr} = 0$ at $z = 0$.

Equations (3.1) indicate that the top and bottom surfaces of the layer, $y = \pm h$, are sliding clamped and displaced along the z direction by an amount of 2δ and there is a constant electric potential difference $-2\varphi_0$ and a constant magnetic potential difference $-2\psi_0$ between the top and bottom surfaces. These equations give, in the layer without the crack, the particular solution

$$u_z(r, z) = \frac{\delta_0 z}{h}; \quad \varphi(r, z) = -\frac{\varphi_0 z}{h}; \quad \psi(r, z) = -\frac{\psi_0 z}{h},$$

$$u_r(r, z) = -\frac{c_{13}}{c_{11} + c_{12}} \frac{\delta_0 r}{h} = -\nu_{rz} \frac{\delta_0 r}{h},$$

$$\begin{aligned}
\sigma_r = \sigma_\theta = 0, \\
\sigma_z(r, z) = \left(c_{33} - \frac{2c_{13}^2}{c_{11} + c_{12}} \right) \frac{\delta_0}{h} - e_{33} \frac{\Phi_0}{h} - q_{33} \frac{\Psi_0}{h} = \tilde{E}_z \frac{\delta_0}{h} - e_{33} \frac{\Phi_0}{h} - q_{33} \frac{\Psi_0}{h}, \\
D_z = \left(e_{33} - \frac{2c_{13}}{c_{11} + c_{12}} e_{31} \right) \frac{\delta_0}{h} + \varepsilon_{33} \frac{\Phi_0}{h} + d_{33} \frac{\Psi_0}{h} = (e_{33} - \nu_{rz} e_{31}) \frac{\delta_0}{h} + \varepsilon_{33} \frac{\Phi_0}{h} + d_{33} \frac{\Psi_0}{h}, \quad (3.2) \\
B_z = \left(q_{33} - \frac{2c_{13}}{c_{11} + c_{12}} q_{31} \right) \frac{\delta_0}{h} + d_{33} \frac{\Phi_0}{h} + \mu_{33} \frac{\Psi_0}{h} = (q_{33} - \nu_{rz} q_{31}) \frac{\delta_0}{h} + d_{33} \frac{\Phi_0}{h} + \mu_{33} \frac{\Psi_0}{h}, \\
\sigma_{rz} = 0; \quad E_z = \frac{\Phi_0}{h}; \quad H_z = \frac{\Psi_0}{h}
\end{aligned}$$

where \tilde{E}_z is the Young modulus in the z direction.

By superposition principle the crack problem is equivalent to the perturbation problem under the applied loading on the crack surface and condition of symmetry on the plane $z=0$ outside the crack region.

$$\sigma_z(r, 0) = -\sigma^*; \quad D_z(r, 0) = D_c - D^*; \quad B_z(r, 0) = B_c - B^*; \quad r < a, \quad (3.3)$$

$$\sigma_{zr}(r, 0) = 0; \quad r \geq 0, \quad (3.4)$$

$$u_z(r, 0) = 0; \quad \varphi(r, 0) = 0; \quad \psi(r, 0) = 0; \quad r \geq a \quad (3.5)$$

where σ^* , D^* , B^* are constant which from Eq.(3.2) are given by formulae

$$\begin{aligned}
\sigma^* &= \tilde{E}_z \frac{\delta_0}{h} - e_{33} \frac{\Phi_0}{h} - q_{33} \frac{\Psi_0}{h}, \\
D^* &= (e_{33} - \nu_{rz} e_{31}) \frac{\delta_0}{h} + \varepsilon_{33} \frac{\Phi_0}{h} + d_{33} \frac{\Psi_0}{h}, \\
B^* &= (q_{33} - \nu_{rz} q_{31}) \frac{\delta_0}{h} + d_{33} \frac{\Phi_0}{h} + \mu_{33} \frac{\Psi_0}{h}.
\end{aligned} \quad (3.6)$$

In the above equations \tilde{E}_z and ν_{rz} are the Young modulus and Poisson's ratio in the principal direction of anisotropy, the z axis. In Eq.(3.3) D_c and B_c are normal components of the electric displacement and the magnetic induction, respectively, on the crack faces and inside the crack region, which for semi permeable crack face magnetoelectric boundary conditions are expressed as follows

$$D_c = -\varepsilon_c \frac{\Delta\varphi}{\Delta u_z}; \quad B_c = -\mu_c \frac{\Delta\psi}{\Delta u_z}; \quad r \leq a \quad (3.7)$$

where $\varepsilon_c = \varepsilon_r \varepsilon_0$ ($\varepsilon_0 = 8,85 \times 10^{-12} F/m$ the dielectric permittivity of air) and $\mu_c = \mu_r \mu_0$ ($\mu_0 = 4\pi \times 10^{-7} N/A^2$ - the magnetic permeability of air) are the electric permittivity and magnetic

permeability of the medium inside the crack; $\Delta\varphi$, $\Delta\psi$ and Δu_z are the jumps of the electric potential, magnetic potential and crack opening displacement, respectively, across the crack. Especially, one can see that the crack reduces to an air when $\varepsilon_r = 1$ and $\mu_r = 1$. If the crack is filled by silicone oil, then $\varepsilon_r = 2,5$; in the case of water $\varepsilon_r = 81$.

4. Solution method

To solve the mixed boundary value problem on the crack plane, we express the solution for mono harmonic functions $\varphi_i(r, \lambda_i z)$ as the following Hankel integrals

$$\varphi_i(r, \lambda_i z) = \int_0^\infty \xi^{-1} A_i(\xi) \frac{\cosh[-\lambda_i \xi(z-h)]}{\sinh(\lambda_i \xi h)} J_0(\xi r) d\xi \tag{4.1}$$

where $A_i(\xi)$ are the unknowns ($i = 1, 2, 3, 4$) to be obtained from the boundary conditions and $J_0(\xi r)$ is the Bessel function of the first kind and zero order, and λ_i are the roots of the characteristic Eq.(2.7). Since $\pm\lambda_i$ are the roots of the characteristic Eq.(2.7) it should be pointed out that the roots satisfying $\text{Re}(\lambda_j) > 0$ are only chosen and used in Eq (4.1) to satisfy the regularity condition at infinity.

Then from Eq.(2.9) the components of displacements u_r and u_z , potentials φ and ψ , stresses σ_r , σ_θ , σ_z , σ_{rz} , electric displacement D_r and D_z and magnetic induction B_r , B_z can be derived. We have

$$u_r(r, z) = -\sum_{i=1}^4 a_{1i} \lambda_i \int_0^\infty A_i(\xi) \frac{\cosh[-\lambda_i \xi(z-h)]}{\sinh(\lambda_i \xi h)} J_1(\xi r) d\xi - \nu_{rz} \frac{\delta_0}{h} r, \tag{4.2}$$

$$\begin{bmatrix} u_z(r, z) \\ \varphi(r, z) \\ \psi(r, z) \end{bmatrix} = \sum_{i=1}^4 \begin{bmatrix} -I \\ a_{3i} \\ a_{4i} \end{bmatrix} \int_0^\infty A_i(\xi) \frac{\sinh[-\lambda_i \xi(z-h)]}{\sinh(\lambda_i \xi h)} J_0(\xi r) d\xi + \begin{bmatrix} \frac{\delta_0}{h} z \\ -\frac{\Phi_0}{h} z \\ -\frac{\Psi_0}{h} z \end{bmatrix}, \tag{4.3}$$

$$\begin{bmatrix} \sigma_r(r, z) \\ \sigma_\theta(r, z) \\ \sigma_z(r, z) \\ D_z(r, z) \\ B_z(r, z) \end{bmatrix} = \sum_{i=1}^4 \begin{bmatrix} -a_{5i} \lambda_i \\ -a_{5i} \lambda_i \\ a_{5i} / \lambda_i \\ a_{6i} \lambda_i \\ a_{7i} \lambda_i \end{bmatrix} \int_0^\infty \xi A_i(\xi) \frac{\cosh[-\lambda_i \xi(z-h)]}{\sinh(\lambda_i \xi h)} J_0(\xi r) d\xi + \begin{bmatrix} (c_{11} - c_{12}) \left(\frac{u_r}{r} + \nu_{rz} \frac{\delta_0}{h} \right) \\ (c_{11} - c_{12}) \left(\frac{\partial u_r}{\partial r} + \nu_{rz} \frac{\delta_0}{h} \right) \\ 0 \\ 0 \\ 0 \end{bmatrix} + \begin{bmatrix} 0 \\ 0 \\ \sigma^* \\ D^* \\ B^* \end{bmatrix}, \tag{4.4}$$

$$\begin{bmatrix} \sigma_{rz}(r, z) \\ D_r(r, z) \\ B_r(r, z) \end{bmatrix} = \sum_{i=1}^4 \begin{bmatrix} a_{5i} \\ a_{6i}\lambda_i^2 \\ a_{7i}\lambda_i^2 \end{bmatrix} \int_0^\infty \xi A_i(\xi) \frac{\sinh[-\lambda_i \xi(z-h)]}{\sinh(\lambda_i \xi h)} J_1(\xi r) d\xi. \quad (4.5)$$

The resulting expressions and boundary conditions (3.3), (3.4) and (3.5) are

$$\begin{bmatrix} \sigma_z(r, 0) \\ D_z(r, 0) \\ B_z(r, 0) \end{bmatrix} = \sum_{i=1}^4 \begin{bmatrix} a_{5i}/\lambda_i \\ a_{6i}\lambda_i \\ a_{7i}\lambda_i \end{bmatrix} \int_0^\infty \xi A_i(\xi) \coth(\lambda_i \xi h) J_0(\xi r) d\xi = \begin{bmatrix} -\sigma^* \\ D_c - D^* \\ B_c - B^* \end{bmatrix}; \quad r < a, \quad (4.6)$$

$$\sigma_{rz}(r, 0) = \sum_{i=1}^4 a_{5i} \int_0^\infty \xi A_i(\xi) J_1(\xi r) d\xi = 0; \quad r \geq 0, \quad (4.7)$$

$$\begin{bmatrix} u_z(r, 0) \\ \varphi(r, 0) \\ \Psi(r, 0) \end{bmatrix} = \sum_{i=1}^4 \begin{bmatrix} -I \\ a_{3i} \\ a_{4i} \end{bmatrix} \int_0^\infty A_i(\xi) J_0(\xi r) d\xi = 0; \quad r \geq a. \quad (4.8)$$

On the plane $z = h$ we have satisfied the boundary conditions (3.1) and $\sigma_{rz}(r, h) \equiv 0$ and in addition

$$u_r(r, h) = -\sum_{i=1}^4 a_{1i}\lambda_i \int_0^\infty A_i(\xi) \frac{I}{\sin(\lambda_i \xi h)} J_1(\xi r) d\xi - \nu_{rz} \frac{\delta_0}{h} r, \quad (4.9)$$

$$\sigma_z(r, h) = \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} \int_0^\infty \xi A_i(\xi) \frac{I}{\sinh(\lambda_i \xi h)} J_0(\xi r) d\xi + \sigma^*.$$

The boundary conditions (3.1), which give the boundary values (4.9), are of sliding clamped type with prescribed axial displacement δ_0 and electric, and magnetic potentials φ_0 and Ψ_0 , respectively.

For convenience, we introduce three new functions $U(\xi)$, $\Phi(\xi)$ and $\Psi(\xi)$, such that

$$\sum_{i=1}^4 \begin{bmatrix} I \\ a_{3i} \\ a_{4i} \\ a_{5i} \end{bmatrix} A_i(\xi) = \begin{bmatrix} U(\xi) \\ \Phi(\xi) \\ \Psi(\xi) \\ 0 \end{bmatrix}. \quad (4.10)$$

Then the unknowns $A_i(\xi)$ can be written as

$$\begin{bmatrix} A_1(\xi) \\ A_2(\xi) \\ A_3(\xi) \\ A_4(\xi) \end{bmatrix} = [b_{ji}]_{4 \times 4} \begin{bmatrix} U(\xi) \\ \Phi(\xi) \\ \Psi(\xi) \\ 0 \end{bmatrix} \quad (4.11)$$

where

$$[b_{ji}]_{4 \times 4} = \begin{bmatrix} 1 & 1 & 1 & 1 \\ a_{31} & a_{32} & a_{33} & a_{34} \\ a_{41} & a_{42} & a_{43} & a_{44} \\ a_{51} & a_{52} & a_{53} & a_{54} \end{bmatrix}^{-1}, \quad (4.12)$$

and where “ -1 ” denotes the inverse matrix.

The constants $A_i(\xi)$ are obtained as follows

$$m_2 A_i(\xi) = d_i U(\xi) + l_i \Phi(\xi) + k_i \Psi(\xi) \quad (4.13)$$

where

$$m_2 = \sum_{i=1}^4 d_i = \sum_{i=1}^4 a_{3i} l_i = \sum_{i=1}^4 a_{4i} k_i. \quad (4.14)$$

We have the identities

$$\begin{aligned} \sum l_i &= \sum k_i = \sum a_{3i} d_i = \sum a_{3i} k_i = \sum a_{4i} d_i = \sum a_{4i} l_i = \\ &= \sum a_{5i} d_i = \sum a_{5i} l_i = \sum a_{5i} k_i \equiv 0 \end{aligned} \quad (4.15)$$

where sums are from 1 to 4.

The material parameters d_i , l_i , and k_i ; $i = 1, 2, 3, 4$, are

$$\begin{aligned} d_1 &= a_{52}(a_{33}a_{44} - a_{43}a_{34}) + a_{53}(a_{34}a_{42} - a_{32}a_{44}) + a_{54}(a_{32}a_{43} - a_{33}a_{42}), \\ d_2 &= a_{51}(a_{34}a_{43} - a_{33}a_{44}) + a_{53}(a_{31}a_{44} - a_{34}a_{41}) + a_{54}(a_{33}a_{41} - a_{31}a_{43}), \\ d_3 &= a_{51}(a_{32}a_{44} - a_{34}a_{42}) + a_{52}(a_{34}a_{41} - a_{31}a_{44}) + a_{54}(a_{31}a_{42} - a_{32}a_{41}), \\ d_4 &= a_{51}(a_{33}a_{42} - a_{32}a_{43}) + a_{52}(a_{31}a_{43} - a_{33}a_{41}) + a_{53}(a_{32}a_{41} - a_{31}a_{42}), \\ l_1 &= a_{52}(a_{43} - a_{44}) + a_{53}(a_{44} - a_{42}) + a_{54}(a_{42} - a_{43}), \\ l_2 &= a_{51}(a_{44} - a_{43}) + a_{53}(a_{41} - a_{44}) + a_{54}(a_{43} - a_{41}), \\ l_3 &= a_{51}(a_{42} - a_{44}) + a_{52}(a_{44} - a_{41}) + a_{54}(a_{41} - a_{42}), \\ l_4 &= a_{51}(a_{43} - a_{42}) + a_{52}(a_{41} - a_{43}) + a_{53}(a_{42} - a_{41}), \\ k_1 &= a_{52}(a_{34} - a_{33}) + a_{53}(a_{32} - a_{34}) + a_{54}(a_{33} - a_{32}), \\ k_2 &= a_{51}(a_{33} - a_{34}) + a_{53}(a_{34} - a_{31}) + a_{54}(a_{31} - a_{33}), \\ k_3 &= a_{51}(a_{34} - a_{32}) + a_{52}(a_{31} - a_{34}) + a_{54}(a_{32} - a_{31}), \\ k_4 &= a_{51}(a_{32} - a_{33}) + a_{52}(a_{33} - a_{31}) + a_{53}(a_{31} - a_{32}). \end{aligned} \quad (4.16)$$

The boundary conditions (4.6), (4.7) and (4.8) give a system of coupled integral equations for $U(\xi)$, $\Phi(\xi)$ and $\Psi(\xi)$ in the following form

$$m_2\sigma_z(r,0) = \int_0^\infty [mU(\xi) + m_6\Phi(\xi) + \tilde{m}_6\Psi(\xi)] \xi J_0(\xi r) d\xi + \\ + \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} \int_0^\infty [d_i U(\xi) + l_i \Phi(\xi) + k_i \Psi(\xi)] [\coth(\lambda_i \xi h) - 1] \xi J_0(\xi r) d\xi = -m_2\sigma^*; \quad r < a, \quad (4.17)$$

$$m_2 D_z(r,0) = \int_0^\infty [m_5 U(\xi) + m_7 \Phi(\xi) + m_8 \Psi(\xi)] \xi J_0(\xi r) d\xi + \\ + \sum_{i=1}^4 a_{6i} \lambda_i \int_0^\infty [d_i U(\xi) + l_i \Phi(\xi) + k_i \Psi(\xi)] [\coth(\lambda_i \xi h) - 1] \xi J_0(\xi r) d\xi = m_2 (D_c - D^*); \quad r < a \quad (4.18)$$

$$m_2 B_z(r,0) = \int_0^\infty [m_9 U(\xi) + m_{10} \Phi(\xi) + m_{11} \Psi(\xi)] \xi J_0(\xi r) d\xi + \\ + \sum_{i=1}^4 a_{7i} \lambda_i \int_0^\infty [d_i U(\xi) + l_i \Phi(\xi) + k_i \Psi(\xi)] [\coth(\lambda_i \xi h) - 1] \xi J_0(\xi r) d\xi = m_2 (B_c - B^*); \quad r < a \quad (4.19)$$

$$\begin{bmatrix} u_z(r,0) \\ \varphi(r,0) \\ \psi(r,0) \end{bmatrix} = \int_0^\infty \begin{bmatrix} -U(\xi) \\ \Phi(\xi) \\ \Psi(\xi) \end{bmatrix} J_0(\xi r) d\xi = 0; \quad r \geq a, \quad (4.20)$$

where

$$m = \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} d_i; \quad m_6 = \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} l_i; \quad \tilde{m}_6 = \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} k_i, \\ m_5 = \sum_{i=1}^4 a_{6i} \lambda_i d_i; \quad m_7 = \sum_{i=1}^4 a_{6i} \lambda_i l_i; \quad m_8 = \sum_{i=1}^4 a_{6i} \lambda_i k_i, \quad (4.21) \\ m_9 = \sum_{i=1}^4 a_{7i} \lambda_i d_i; \quad m_{10} = \sum_{i=1}^4 a_{7i} \lambda_i l_i; \quad m_{11} = \sum_{i=1}^4 a_{7i} \lambda_i k_i.$$

Introduce the new functions $f_i(x)$ ($i=1,2,3$) and the following Fourier integral representation of the functions $U(\xi)$, $\Phi(\xi)$ and $\Psi(\xi)$

$$\begin{bmatrix} U(\xi) \\ \Phi(\xi) \\ \Psi(\xi) \end{bmatrix} = \int_0^\infty \begin{bmatrix} f_1(s) \\ f_2(s) \\ f_3(s) \end{bmatrix} \sin(\xi s) ds; \quad f_i(0) = 0, \quad (4.22)$$

then

$$\begin{bmatrix} u_z(r, \theta) \\ \varphi(r, \theta) \\ \psi(r, \theta) \end{bmatrix} = \int_0^a \begin{bmatrix} -f_1(s) \\ f_2(s) \\ f_3(s) \end{bmatrix} ds \int_0^\infty \sin(\xi s) J_0(\xi r) d\xi \tag{4.23}$$

Recalling the following known result

$$\int_0^\infty \sin(\xi s) J_0(\xi r) d\xi = \frac{H(s-r)}{\sqrt{s^2-r^2}} \tag{4.24}$$

where $H(\cdot)$ is the Heaviside function, we find that the boundary conditions (4.20) are automatically satisfied. Moreover, the displacement, electric potential and magnetic potential on the crack plane can be expressed in terms of the introduced unknown functions as

$$\begin{bmatrix} u_z(r, \theta) \\ \varphi(r, \theta) \\ \psi(r, \theta) \end{bmatrix} = \int_r^a \begin{bmatrix} -f_1(s) \\ f_2(s) \\ f_3(s) \end{bmatrix} \frac{ds}{\sqrt{s^2-r^2}} \tag{4.25}$$

Multiplying both sides of Eqs (4.17), (4.18) and (4.19) by $r/\sqrt{s^2-r^2}$, integrating with respect to r from θ to x ($x < \theta$), respectively, and using the following identities

$$\int_0^x \frac{r J_0(\xi r)}{\sqrt{x^2-r^2}} dr = \frac{\sin(\xi x)}{\xi}, \quad \int_0^\infty \sin(\xi s) \sin(\xi x) d\xi = \frac{\pi}{2} \delta(s-x) \tag{4.26}$$

where $\delta(\cdot)$ is the Dirac delta function, Eqs (4.17), (4.18) and (4.19) can be rewritten as

$$\begin{aligned} & m f_1(x) - m_6 f_2(x) - \tilde{m}_6 f_3(x) + \\ & + \frac{2}{\pi} \sum_1^4 \frac{a_{5i}}{\lambda_i} \int_0^a [d_i f_1(s) - l_i f_2(s) - k_i f_3(s)] K_i(x, s) ds = \frac{2}{\pi} \sigma^* m_2 x, \\ & m_5 f_1(x) - m_7 f_2(x) - m_8 f_3(x) + \\ & + \frac{2}{\pi} \sum_1^4 a_{6i} \lambda_i \int_0^a [d_i f_1(s) - l_i f_2(s) - k_i f_3(s)] K_i(x, s) ds = \frac{2}{\pi} (D^* - D_c) m_2 x \\ & m_9 f_1(x) - m_{10} f_2(x) - m_{11} f_3(x) + \\ & + \frac{2}{\pi} \sum_1^4 a_{7i} \lambda_i \int_0^a [d_i f_1(s) - l_i f_2(s) - k_i f_3(s)] K_i(x, s) ds = \frac{2}{\pi} (B^* - B_c) m_2 x \end{aligned} \tag{4.27}$$

where the kernel functions $K_i(x, s)$ are defined as follows

$$K_i(x, s) = \frac{2}{\pi} \int_0^{\infty} [\coth(\lambda_i \xi h) - I] \sin(\xi s) \sin(\xi x) d\xi, \quad i = 1, 2, 3, 4. \quad (4.28)$$

Next, the solutions of electric displacement and magnetic induction inside the crack are of interest. Application of Eqs (3.7) and (4.25) leads to

$$D_c \int_r^a \frac{f_1(s)}{\sqrt{s^2 - r^2}} ds - \varepsilon_r \varepsilon_0 \int_r^a \frac{f_2(s)}{\sqrt{s^2 - r^2}} ds = 0; \quad 0 \leq r \leq a, \quad (4.29)$$

$$B_c \int_r^a \frac{f_1(s)}{\sqrt{s^2 - r^2}} ds - \mu_r \mu_0 \int_r^a \frac{f_3(s)}{\sqrt{s^2 - r^2}} ds = 0; \quad 0 \leq r \leq a.$$

Differentiating both Eqs (4.29) with respect to r and using the following rule of differentiation under integral sign

$$\frac{d}{dr} \int_r^a \frac{f(s)}{\sqrt{s^2 - r^2}} ds = -\frac{rf(a)}{a\sqrt{a^2 - r^2}} + r \int_r^a \frac{d}{ds} \left(\frac{f(s)}{s} \right) \frac{ds}{\sqrt{s^2 - r^2}}. \quad (4.30)$$

Equations (4.29) may be rewritten as follows

$$\begin{aligned} & -\frac{r}{a\sqrt{a^2 - r^2}} [D_c f_1(a) - \varepsilon_r \varepsilon_0 f_2(a)] + \\ & + r \left[D_c \int_r^a \frac{d}{ds} \left(\frac{f_1(s)}{s} \right) \frac{ds}{\sqrt{s^2 - r^2}} - \varepsilon_r \varepsilon_0 \int_r^a \frac{d}{ds} \left(\frac{f_2(s)}{s} \right) \frac{ds}{\sqrt{s^2 - r^2}} \right] = 0, \end{aligned} \quad (4.31)$$

$$\begin{aligned} & -\frac{r}{a\sqrt{a^2 - r^2}} [B_c f_1(a) - \mu_r \mu_0 f_3(a)] + \\ & + r \left[B_c \int_r^a \frac{d}{ds} \left(\frac{f_1(s)}{s} \right) \frac{ds}{\sqrt{s^2 - r^2}} - \mu_r \mu_0 \int_r^a \frac{d}{ds} \left(\frac{f_3(s)}{s} \right) \frac{ds}{\sqrt{s^2 - r^2}} \right] = 0; \quad 0 \leq r \leq a. \end{aligned}$$

The first terms in both Eqs (4.31) are singular at $r \rightarrow a - 0$, while other terms tend to zero in at this point. For the singularity to vanish at $r \rightarrow a - 0$, it must be true that

$$D_c f_1(a) - \varepsilon_r \varepsilon_0 f_2(a) = 0, \quad (4.32)$$

$$B_c f_1(a) - \mu_r \mu_0 f_3(a) = 0.$$

Equations (4.32) determine unknown quantities D_c and B_c . The relations are non linear since $f_1(a)$, $f_2(a)$ and $f_3(a)$ depend also on D_c and B_c , as shown in Eqs (4.27). Equations (4.32) form two coupling quadratic equations with respect to D_c and B_c . Those are dependent on the material properties, electric permittivity and magnetic permeability of the crack interior and applied loadings. In addition, it is found that

the kernel function $K_i(x, s; h)$ depends on the width of the layer D_c and B_c also depends on h . Moreover, although these are at most four pairs of roots of D_c and B_c according to the nonlinear Eqs (4.32) only one pair is reasonable and the other are superfluous. The acceptable D_c and B_c should be located at the range between that for a magneto electrically impermeable crack (zeroes values) and that for a magneto – electrically permeable crack (the extremally possible values). Four ideal crack face electromagnetic boundary conditions: (i) $D_c = 0$ and $B_c = 0$, (ii) $D_c \neq 0$ and $B_c = 0$, (iii) $D_c = 0$ and $B_c \neq 0$, (iv) $D_c \neq 0$ and $B_c \neq 0$ are the limiting cases of the electromagnetically semi permeable crack model (“dielectric and magnetic crack”).

5. The exact solution of Fredholm integral equation

Using the known result

$$\coth(\lambda_i \xi h) - 1 = 2 \sum_{n=1}^{\infty} e^{-2n\lambda_i \xi h}, \tag{5.1}$$

we find that the kernel function (4.28) is

$$K_i(x, s) = \sum_{n=1}^{\infty} \left(\frac{2n\lambda_i h}{(2n\lambda_i h)^2 + (x-s)^2} - \frac{2n\lambda_i h}{(2n\lambda_i h)^2 + (x+s)^2} \right). \tag{5.2}$$

Consequently, Eqs (4.27) can be rewritten as

$$\begin{aligned} & \Lambda \begin{bmatrix} f_1(x) \\ f_2(x) \\ f_3(x) \end{bmatrix} + \\ & + \frac{2}{\pi} \sum_{i=1}^4 \sum_{n=1}^{\infty} \begin{bmatrix} a_{5i} / \lambda_i \\ a_{6i} \lambda_i \\ a_{7i} \lambda_i \end{bmatrix} \int_0^a [d_i f_1(s) - l_i f_2(s) - k_i f_3(s)] \left[\frac{2n\lambda_i h}{(2n\lambda_i h)^2 + (x-s)^2} - \frac{2n\lambda_i h}{(2n\lambda_i h)^2 + (x+s)^2} \right] ds = (5.3) \\ & = \frac{2}{\pi} m_2 x \begin{bmatrix} \sigma^* \\ D^* - D_c \\ B^* - B_c \end{bmatrix}. \end{aligned}$$

This Fredholm integral equation of the second kind (5.3) can be solved explicitly. The method of consecutive iteration yields the N th approximation

$$\begin{aligned} & \begin{bmatrix} f_{1N}(x) \\ f_{2N}(x) \\ f_{3N}(x) \end{bmatrix} = \begin{bmatrix} f_{10}(x) \\ f_{20}(x) \\ f_{30}(x) \end{bmatrix} + \\ & - \sum_{i=1}^4 \sum_{n=1}^{\infty} \begin{bmatrix} a_{5i} / \lambda_i \\ a_{6i} \lambda_i \\ a_{7i} \lambda_i \end{bmatrix} [d_i f_{10}(x) - l_i f_{20}(x) - k_i f_{30}(x)] [F_{in}^1(x) - F_{in}^2(x) + F_{in}^3(x) - \dots + F_{in}^N(x)] \end{aligned} \tag{5.4}$$

where

$$\begin{bmatrix} f_{10}(x) \\ f_{20}(x) \\ f_{30}(x) \end{bmatrix} = \frac{2}{\pi} m_2 x \Lambda^{-1} \begin{bmatrix} \sigma^* \\ D^* - D_c \\ B^* - B_c \end{bmatrix},$$

$$F_{in}(x) = \frac{2}{\pi} \left(\frac{n\lambda_i h}{x} \ln \left(\frac{(2n\lambda_i h)^2 + (x-a)^2}{(2n\lambda_i h)^2 + (x+a)^2} \right) + \tan^{-1} \left(\frac{x+a}{2n\lambda_i h} \right) - \tan^{-1} \left(\frac{x-a}{2n\lambda_i h} \right) \right), \quad (5.5)$$

$$\Lambda = \begin{bmatrix} m & -m_6 & -\tilde{m}_6 \\ m_5 & -m_7 & -m_8 \\ m_9 & -m_{10} & -m_{11} \end{bmatrix},$$

and the superscript “ -1 ” denotes the inverse of a matrix Λ .

The sum of infinite geometric series converges to the solution as $N \rightarrow \infty$, giving

$$\begin{bmatrix} f_1(x) \\ f_2(x) \\ f_3(x) \end{bmatrix} = \frac{2}{\pi} m_2 x \Lambda^{-1} \begin{bmatrix} \sigma^* \\ D^* - D_c \\ B^* - B_c \end{bmatrix} +$$

$$-\sum_{i=1}^4 \sum_{n=1}^{\infty} \begin{bmatrix} a_{5i} / \lambda_i \\ a_{6i} \lambda_i \\ a_{7i} \lambda_i \end{bmatrix} \left[d_i f_{10}(x) - l_i f_{20}(x) - k_i f_{30}(x) \right] \frac{F_{in}(x)}{1 + F_{in}(x)}. \quad (5.6)$$

The range of convergence is given by the inequality

$$|F_{in}(x)| < 1, \quad (5.7)$$

and is satisfied for all of $0 \leq x \leq a$ and a/h . For the limiting case of an infinite magnetoelastic space $F_{in}(x, a/h) \rightarrow 0$ as $h \rightarrow \infty$. On the other hand, for a very thin plate $F_{in}(x, a/h)$ tends to unity since $h \rightarrow 0$. To check the above results, it is natural to consider the special case where a dielectric crack is embedded in an infinite magnetoelastic material, i.e., $h \rightarrow \infty$. One can find that the solution may be solved explicitly. This solution is given in Appendix B.

6. Analysis of field intensity factors

Defining the field intensity factors as follows

$$K_q = \lim_{r \rightarrow a^+} \sqrt{2\pi(r-a)} q(r) \quad (6.1)$$

where q stands for σ_z , D_z and B_z , respectively, we then find that the intensity factors of stress, electric displacement and magnetic induction can be expressed as

$$\begin{aligned} \begin{bmatrix} K_\sigma \\ K_D \\ K_B \end{bmatrix} &= \frac{2}{\pi} \sqrt{\pi a} \left\{ \begin{bmatrix} \sigma^* \\ D^* - D_c \\ B^* - B_c \end{bmatrix} + \right. \\ &\left. - \frac{\Lambda}{m_2} \sum_{i=1}^4 \sum_{n=1}^{\infty} \begin{bmatrix} a_{5i} / \lambda_i \\ a_{6i} \lambda_i \\ a_{7i} \lambda_i \end{bmatrix} \left[d_i f_{10}(a) - l_i f_{20}(a) - k_i f_{30}(a) \right] \frac{2}{\pi} \frac{\tan^{-1}(\alpha_{in}) - \frac{I}{\alpha_{in}} \ln(I + \alpha_{in}^2)}{I + \frac{2}{\pi} \left(\tan^{-1}(\alpha_{in}) - \frac{I}{\alpha_{in}} \ln(I + \alpha_{in}^2) \right)} \right\} \end{aligned} \quad (6.2)$$

where

$$\alpha_{in} = \frac{a}{\lambda_i n h}. \quad (6.3)$$

The first closed form solutions, for an infinite medium, are identical with the known result given by Zhong and Li (2007) through a different approach. Similarly, the field intensity factors associated with the crack opening displacement $u_z(r)$, electric potential $\varphi(r)$ and magnetic potential $\psi(r)$ across the crack near the crack front are defined and easily derived from Eqs (4.25) as

$$\begin{aligned} K_{COD} &\stackrel{\Delta}{=} \lim_{r \rightarrow a^-} \sqrt{\frac{\pi}{2(a-r)}} u_z(r) = \sqrt{\pi a} \frac{f_1(a)}{a}, \\ K_\varphi &\stackrel{\Delta}{=} \lim_{r \rightarrow a^-} \sqrt{\frac{\pi}{2(a-r)}} \varphi(r) = \sqrt{\pi a} \frac{f_2(a)}{a}, \\ K_\psi &\stackrel{\Delta}{=} \lim_{r \rightarrow a^-} \sqrt{\frac{\pi}{2(a-r)}} \psi(r) = \sqrt{\pi a} \frac{f_3(a)}{a}. \end{aligned} \quad (6.4)$$

Figures 2 and 3 show the variation of the functions $f(\alpha)$ and $f(\alpha)/(I + f(\alpha))$, respectively.

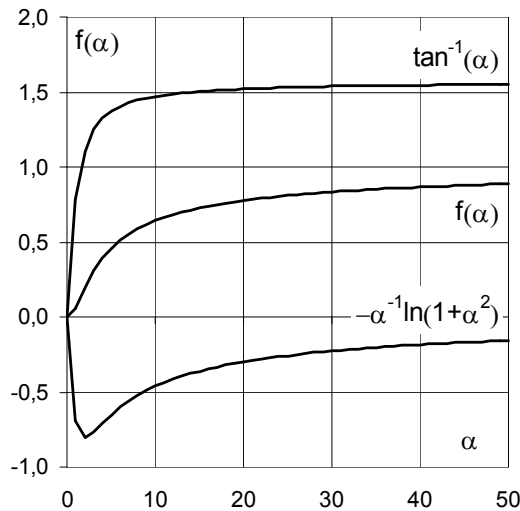


Fig.2. The variation of the function $f(\alpha) = \frac{2}{\pi} \left[\tan^{-1}(\alpha) - \alpha^{-1} \ln(I + \alpha^2) \right]$ with α .

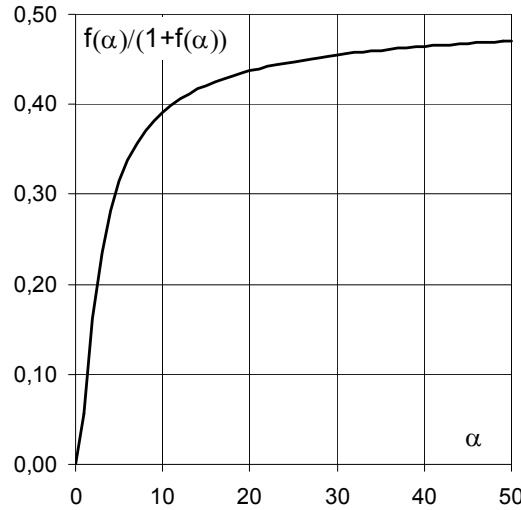


Fig.3. The variation of the function $f(\alpha)/(1+f(\alpha))$ with α .

These field intensity factors can be presented explicitly

$$\begin{bmatrix} K_{COD} \\ K_{\varphi} \\ K_{\psi} \end{bmatrix} = \frac{2}{\pi} \sqrt{\pi a m_2} \Lambda^{-1} \begin{bmatrix} \sigma^* \\ D^* - D_c \\ B^* - B_c \end{bmatrix} + \left. - \sum_{i=1}^4 \sum_{n=1}^{\infty} \begin{bmatrix} a_{5i} / \lambda_i \\ a_{6i} \lambda_i \\ a_{7i} \lambda_i \end{bmatrix} \left[d_i f_{10}(a) - l_i f_{20}(a) - k_i f_{30}(a) \right] \frac{2}{\pi} \frac{\tan^{-1}(\alpha_{in}) - \frac{I}{\alpha_{in}} \ln(I + \alpha_{in}^2)}{I + \frac{2}{\pi} \left(\tan^{-1}(\alpha_{in}) - \frac{I}{\alpha_{in}} \ln(I + \alpha_{in}^2) \right)} \right\} \quad (6.5)$$

Note that

$$\begin{bmatrix} K_{\sigma} \\ K_D \\ K_B \end{bmatrix} = \frac{\Lambda}{m_2} \begin{bmatrix} K_{COD} \\ K_{\varphi} \\ K_{\psi} \end{bmatrix} \quad (6.6)$$

where the matrix Λ / m_2 may be partitioned as

$$\begin{bmatrix} \text{elastic stiffness} & \text{piezoelectric} & \text{piezomagnetic} \\ \text{piezoelectric} & \text{dielectric} & \text{magnetoelectric} \\ \text{piezomagnetic} & \text{magnetoelectric} & \text{magnetic} \end{bmatrix}.$$

For the piezoelectric barium titanate BaTiO_3 and piezomagnetic cobalt iron oxide CoFe_2O_4 composite (roughly 50:50 percent) we have

$$\begin{bmatrix} 62,5 \times 10^9 \text{ N / m}^2 & 14,3 \text{ C / m}^2 & 7,0 \times 10^3 \text{ N / Am} \\ 14,3 \text{ C / m}^2 & -17,0 \times 10^{-9} \text{ C / Vm} & -16,7 \times 10^{-9} \text{ C / Am} \\ 7,0 \times 10^3 \text{ N / Am} & -16,7 \times 10^{-9} \text{ C / Am} & -8,2 \times 10^{-6} \text{ N / A}^2 \end{bmatrix}.$$

The non zero magnetoelectric constant $d_{11}^* = -16,7 \times 10^{-9} C / Am$ exists only in the piezoelectric / piezomagnetic composite as a significant new feature.

The electric displacement D_c and magnetic induction B_c inside the crack are obtained from Eqs (4.32), i.e.,

$$D_c = \epsilon_r \epsilon_0 f_2(a) / f_1(a), \tag{6.7}$$

$$B_c = \mu_r \mu_0 f_3(a) / f_1(a)$$

where

$$\begin{bmatrix} f_1(a) \\ f_2(a) \\ f_3(a) \end{bmatrix} = \frac{2}{\pi} m_2 a \Lambda^{-1} \begin{bmatrix} \sigma^* \\ D^* - D_c \\ B^* - B_c \end{bmatrix} + \sum_{i=1}^4 \sum_{n=1}^{\infty} \begin{bmatrix} a_{5i} / \lambda_i \\ a_{6i} \lambda_i \\ a_{7i} \lambda_i \end{bmatrix} \left[d_i f_{10}(a) - l_i f_{20}(a) - k_i f_{30}(a) \right] \frac{2}{\pi} \frac{\tan^{-1}(\alpha_{in}) - \frac{1}{\alpha_{in}} \ln(I + \alpha_{in}^2)}{I + \frac{2}{\pi} \left(\tan^{-1}(\alpha_{in}) - \frac{1}{\alpha_{in}} \ln(I + \alpha_{in}^2) \right)}. \tag{6.8}$$

7. Magnetoelectrically permeable crack

For a magnetoelectrically permeable crack case both electric and magnetic potentials are continuous across the crack surfaces. Thus the problem can be reduced to the following Fredholm integral equation of the second kind

$$m f_1(x) + \frac{2}{\pi} \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} d_i \int_0^a f_1(s) K_i(x, s, \lambda_i, h) ds = \frac{2}{\pi} \sigma^* m_2 x; \quad x < a, \tag{7.1}$$

and $f_2(x) = 0$; and $f_3(x) = 0$.

The solution of the integral equation is given explicitly

$$f_1(x) = \frac{2}{\pi} \sigma^* x \frac{m_2}{m} \left[I - \sum_{i=1}^4 \sum_{n=1}^{\infty} \frac{a_{5i}}{\lambda_i} d_i \frac{F_{in}(x)}{I + F_{in}(x)} \right]. \tag{7.2}$$

The field intensity factors can finally be expressed as

$$K_{COD} = \frac{2}{\pi} \sigma^* \frac{m_2}{m} \sqrt{\pi a} \left[I - \sum_{i=1}^4 \sum_{n=1}^{\infty} \frac{a_{5i}}{\lambda_i} d_i \frac{\frac{2}{\pi} \left(\tan^{-1}(\alpha_{in}) - \frac{1}{\alpha_{in}} \ln(I + \alpha_{in}^2) \right)}{I + \frac{2}{\pi} \left(\tan^{-1}(\alpha_{in}) - \frac{1}{\alpha_{in}} \ln(I + \alpha_{in}^2) \right)} \right], \tag{7.3}$$

$$K_{\sigma} = \frac{m}{m_2} K_{COD}; \quad K_D = \frac{m_5}{m_2} K_{COD}; \quad K_B = \frac{m_9}{m_2} K_{COD}; \quad K_{\varphi} = 0; \quad K_{\psi} = 0.$$

Equations (7.3) indicate that the four field intensity factors of COD, stress, electric displacement and magnetic induction depend on one another through material constants and thickness of the layer. In addition, D_c and B_c have no effect on these field intensity factors. For the barium titanate cobalt iron oxide composite material the elastic stiffness m/m_2 piezoelectric coefficient m_5/m_2 and piezomagnetic coefficient m_9/m_2 are obtained as follows: $62,5 \times 10^9 \text{ N/m}^2$; $14,3 \text{ C/m}^2$; $7,0 \times 10^3 \text{ N/Am}$.

Appendix A

The material parameters in the characteristic Eq.(2.7) are as follows

$$\begin{aligned}
 a &= c_{44} \left[\mu_{33} e_{33}^2 + \varepsilon_{33} q_{33}^2 + c_{33} \mu_{33} \varepsilon_{33} - d_{33} (c_{33} d_{33} + 2e_{33} q_{33}) \right], \\
 b &= \mu_{33} \left\{ (e_{31} + e_{15}) [2c_{13} e_{33} - c_{33} (e_{31} + e_{15})] + 2c_{44} e_{33} e_{31} - c_{11} e_{33}^2 - c_{33} c_{44} \varepsilon_{11} \right\} + \\
 &+ \varepsilon_{33} \left\{ (q_{31} + q_{15}) [2c_{13} q_{33} - c_{33} (q_{31} + q_{15})] + 2c_{44} q_{33} q_{31} - c_{11} q_{33}^2 - c_{33} c_{44} \mu_{11} \right\} + \\
 &- \mu_{33} \varepsilon_{33} \tilde{c}^2 - (e_{31} + e_{15})^2 q_{33}^2 - (q_{31} + q_{15})^2 e_{33}^2 - c_{44} \mu_{11} e_{33}^2 - c_{44} \varepsilon_{11} q_{33}^2 + \\
 &+ 2e_{33} q_{33} (q_{31} + q_{15}) (e_{31} + e_{15}) + d_{33}^2 \tilde{c}^2 + 2c_{33} d_{33} (e_{31} + e_{15}) (q_{31} + q_{15}) + \\
 &+ 2c_{44} c_{33} d_{11} d_{33} + 2e_{33} q_{33} (c_{44} d_{11} + c_{11} d_{33}) - 2d_{33} (c_{13} + c_{44}) [e_{33} (q_{31} + q_{15}) + q_{33} (e_{31} + e_{15})], \\
 c &= \mu_{33} \left\{ 2e_{15} [c_{11} e_{33} - c_{13} (e_{31} + e_{15})] + c_{44} e_{31}^2 + \varepsilon_{11} \tilde{c}^2 \right\} + \\
 &+ \varepsilon_{33} \left\{ 2q_{15} [c_{11} q_{33} - c_{13} (q_{31} + q_{15})] + c_{44} q_{31}^2 + \mu_{11} \tilde{c}^2 \right\} + \\
 &+ c_{33} c_{44} \mu_{11} \varepsilon_{11} + c_{11} c_{44} \mu_{33} \varepsilon_{33} + 2(c_{13} + c_{44}) (q_{31} + q_{15}) (d_{11} e_{33} + d_{33} e_{15} - q_{33} \varepsilon_{11}) + \\
 &+ 2(c_{13} + c_{44}) (e_{31} + e_{15}) (d_{11} q_{33} + d_{33} q_{15} - e_{33} \mu_{11}) + \\
 &+ (q_{31} + q_{15})^2 (c_{33} \varepsilon_{11} + 2e_{33} e_{15}) + (e_{31} + e_{15})^2 (c_{33} \mu_{11} + 2q_{33} q_{15}) + \\
 &- 2(q_{31} + q_{15}) (e_{31} + e_{15}) (e_{33} q_{15} + q_{33} e_{15} + c_{33} d_{11} + c_{44} d_{33}) + \\
 &- 2c_{11} d_{33} (e_{33} q_{15} + q_{33} e_{15}) - 2c_{44} d_{11} (q_{33} e_{15} + e_{33} q_{15}) + \\
 &- 2c_{11} d_{11} q_{33} e_{33} - 2c_{44} d_{33} q_{15} e_{15} + 2c_{44} q_{15} q_{33} \varepsilon_{11} + 2c_{44} e_{15} e_{33} \mu_{11} + \\
 &+ c_{11} q_{33}^2 \varepsilon_{11} + c_{11} e_{33}^2 \mu_{11} - 2\tilde{c}^2 d_{33} d_{11} - c_{11} c_{44} d_{33}^2 - c_{44} c_{33} d_{11}^2, \\
 d &= -c_{11} \mu_{33} (c_{44} \varepsilon_{11} + e_{15}^2) - c_{11} \varepsilon_{33} (c_{44} \mu_{11} + q_{15}^2) - c_{44} (e_{31}^2 \mu_{11} + q_{31}^2 \varepsilon_{11}) + \\
 &- e_{31}^2 q_{15}^2 - q_{31}^2 e_{15}^2 - \mu_{11} \varepsilon_{11} \tilde{c}^2 + d_{11} \tilde{c}^2 + 2c_{11} c_{44} d_{11} d_{33} + \\
 &+ 2c_{13} q_{15} q_{31} \varepsilon_{11} + 2c_{13} e_{15} e_{31} \mu_{11} - 2c_{11} q_{15} q_{33} \varepsilon_{11} - 2c_{11} e_{15} e_{33} \mu_{11} + \\
 &+ 2c_{13} q_{15}^2 \varepsilon_{11} + 2c_{13} e_{15}^2 \mu_{11} + 2e_{31} e_{15} q_{31} q_{15} + 2c_{11} e_{15} q_{15} d_{33} + \\
 &+ d_{11} [-2c_{13} e_{15} (q_{15} + q_{31}) - 2c_{13} q_{15} (e_{15} + e_{31})] + d_{11} [2c_{11} (e_{15} q_{33} + q_{15} e_{33}) + 2c_{44} e_{31} q_{31}], \\
 e &= c_{11} \left[\mu_{11} e_{15}^2 + \varepsilon_{11} q_{15}^2 + c_{44} \varepsilon_{11} \mu_{11} - d_{11} (c_{44} d_{11} + 2e_{15} q_{15}) \right], \\
 \tilde{c}^2 &= c_{11} c_{33} - c_{13} (c_{13} + 2c_{44}).
 \end{aligned} \tag{A.1}$$

Material coefficients in Eqs (2.8)

$$\begin{aligned}
a_1 &= (c_{13} + c_{44})(\varepsilon_{33}q_{33} - e_{33}d_{33}) - (q_{31} + q_{15})(c_{33}\varepsilon_{33} + e_{33}^2) + (e_{31} + e_{15})(e_{33}q_{33} + c_{33}d_{33}), \\
b_1 &= (c_{13} + c_{44})(e_{33}d_{11} + e_{15}d_{33} - \varepsilon_{33}q_{15} - \varepsilon_{11}q_{33}) + (q_{31} + q_{15})(c_{44}\varepsilon_{33} + c_{33}\varepsilon_{11} + 2e_{33}e_{15}) + \\
&\quad - (e_{31} + e_{15})(c_{44}d_{33} + c_{33}d_{11} + q_{33}e_{15} + e_{33}q_{15}), \\
c_1 &= (c_{13} + c_{44})(\varepsilon_{11}q_{15} - e_{15}d_{11}) - (q_{31} + q_{15})(c_{44}\varepsilon_{11} + e_{15}^2) + (e_{31} + e_{15})(c_{44}d_{11} + e_{15}q_{15}), \\
d_1 &= 0, \quad a_2 = c_{44}(e_{33}d_{33} - \varepsilon_{33}q_{33}), \\
b_2 &= c_{11}(q_{33}\varepsilon_{33} - d_{33}e_{33}) + c_{44}(q_{15}\varepsilon_{33} + q_{33}\varepsilon_{11} - e_{15}d_{33} - d_{11}e_{33}) + \\
&\quad + (c_{13} + c_{44})[d_{33}(e_{31} + e_{15}) - \varepsilon_{33}(q_{31} + q_{15})] - (e_{31} + e_{15})[e_{33}(q_{31} + q_{15}) - q_{33}(e_{31} + e_{15})], \\
c_2 &= c_{44}(d_{11}e_{15} - \varepsilon_{11}q_{15}) + (c_{13} + c_{44})[\varepsilon_{11}(q_{31} + q_{15}) - d_{11}(e_{31} + e_{15})] + \\
&\quad + (e_{31} + e_{15})[e_{15}(q_{31} + q_{15}) - q_{15}(e_{31} + e_{15})] + c_{11}(d_{11}e_{33} + d_{33}e_{15} - q_{15}\varepsilon_{33} - q_{33}\varepsilon_{11}), \\
d_2 &= c_{11}(q_{15}\varepsilon_{11} - e_{15}d_{11}), \quad a_3 = c_{44}(c_{33}d_{33} + e_{33}q_{33}), \\
b_3 &= -c_{11}(c_{33}d_{33} + e_{33}q_{33}) - c_{44}(c_{44}d_{33} + e_{15}q_{33} + c_{33}d_{11} + q_{15}e_{33}) + \\
&\quad + (c_{13} + c_{44})[(c_{13} + c_{44})d_{33} + (q_{31} + q_{15})e_{33}] + (e_{31} + e_{15})[(c_{13} + c_{44})q_{33} - (q_{31} + q_{15})c_{33}], \\
c_3 &= c_{11}(c_{44}d_{33} + c_{33}d_{11} + e_{15}q_{33} + q_{15}e_{33}) + c_{44}(c_{44}d_{11} + q_{15}e_{15}) + \\
&\quad - (c_{13} + c_{44})[(c_{13} + c_{44})d_{11} + (q_{31} + q_{15})e_{15}] - (e_{31} + e_{15})[(c_{13} + c_{44})q_{15} - (q_{31} + q_{15})c_{44}], \\
d_3 &= -c_{11}(c_{44}d_{11} + e_{15}q_{15}), \quad a_4 = -c_{44}(c_{33}\varepsilon_{33} + e_{33}^2), \\
b_4 &= c_{11}(c_{33}\varepsilon_{33} + e_{33}^2) + c_{44}(c_{44}\varepsilon_{33} + c_{33}\varepsilon_{11} + 2e_{15}e_{33}) + \\
&\quad - (c_{13} + c_{44})[(c_{13} + c_{44})\varepsilon_{33} + (e_{31} + e_{15})e_{33}] - (e_{31} + e_{15})[(c_{13} + c_{44})e_{33} - (e_{31} + e_{15})c_{33}], \\
c_4 &= -c_{11}(c_{44}\varepsilon_{33} + c_{33}\varepsilon_{11} + 2e_{15}e_{33}) - c_{44}(c_{44}\varepsilon_{11} + e_{15}^2) + \\
&\quad + (c_{13} + c_{44})[(c_{13} + c_{44})\varepsilon_{11} + (e_{31} + e_{15})e_{15}] + (e_{31} + e_{15})[(c_{13} + c_{44})e_{15} - (e_{31} + e_{15})c_{44}], \\
d_4 &= c_{11}(c_{44}\varepsilon_{11} + e_{15}^2).
\end{aligned} \tag{A.2}$$

The coefficients a_4 , b_4 , c_4 , d_4 are obtained from coefficients a_3 , b_3 , c_3 , d_3 by replacement of d_{ii} by ε_{ii} and q_{kl} by e_{kl} and changing the signum.

If only a pure piezoelectric or pure piezomagnetic material is considered, then the electric or magnetic potential is defined by a polynomial of λ which is given as follows $c_{44}c_{33}\lambda^4 - [c_{11}c_{33} - c_{13}(c_{13} + 2c_{44})]\lambda^2 + c_{11}c_{44}$. This polynomial vanishes for a pure elastic transversely isotropic material without piezoelectromagnetic properties.

The roots of the characteristic Eq.(2.7) are presented by formulae

$$\begin{aligned}\lambda_1^2 &= -\frac{b}{4a} - \frac{1}{2}\sqrt{R_5 + R_6} - \frac{1}{2}\sqrt{2R_5 - R_6 + \frac{1}{4}\frac{R_7}{\sqrt{R_5 + R_6}}}, \\ \lambda_2^2 &= -\frac{b}{4a} - \frac{1}{2}\sqrt{R_5 + R_6} + \frac{1}{2}\sqrt{2R_5 - R_6 + \frac{1}{4}\frac{R_7}{\sqrt{R_5 + R_6}}}, \\ \lambda_3^2 &= -\frac{b}{4a} + \frac{1}{2}\sqrt{R_5 + R_6} - \frac{1}{2}\sqrt{2R_5 - R_6 - \frac{1}{4}\frac{R_7}{\sqrt{R_5 + R_6}}}, \\ \lambda_4^2 &= -\frac{b}{4a} + \frac{1}{2}\sqrt{R_5 + R_6} + \frac{1}{2}\sqrt{2R_5 - R_6 - \frac{1}{4}\frac{R_7}{\sqrt{R_5 + R_6}}}\end{aligned}\tag{A.3}$$

where

$$\begin{aligned}R_1 &= 2c^3 - 9bcd + 27ad^2 + 27b^2e - 72ace; \quad R_2 = c^2 - 3bd + 12ae, \\ R_3 &= \sqrt{R_1^2 - 4R_2^3}; \quad R_4 = \sqrt[3]{\frac{1}{2}(R_1 + R_3)}, \\ R_5 &= \frac{b^2}{4a^2} - \frac{2c}{3a}; \quad R_6 = \frac{R_2}{3aR_4} + \frac{R_4}{3a}; \quad R_7 = \frac{b^3}{a^3} - \frac{4bc}{a^2} + \frac{8d}{a}.\end{aligned}\tag{A.4}$$

Appendix B

Denoting

$$\begin{aligned}\tilde{d}_i &= (m_{12}d_i - m_{15}l_i - m_{18}k_i)\sigma^* - (m_{13}d_i - m_{16}l_i - m_{19}k_i)(D^* - D_c) + \\ &\quad - (m_{14}d_i - m_{17}l_i - m_{20}k_i)(B^* - B_c), \\ \tilde{m} &= mm_{12} - m_5m_{13} - m_9m_{14} = mm_{12} - m_6m_{15} - \tilde{m}_6m_{18} = m_7m_{16} - m_5m_{13} + m_8m_{19} = \\ &= m_{10}m_{17} + m_{11}m_{20} - m_9m_{14}, \\ m_{12} &= m_7m_{11} - m_8m_{10}, \quad m_{13} = m_6m_{11} - \tilde{m}_6m_{10}, \quad m_{14} = \tilde{m}_6m_7 - m_6m_8, \\ m_{15} &= m_5m_{11} - m_8m_9, \quad m_{16} = mm_{11} - \tilde{m}_6m_9, \quad m_{17} = \tilde{m}_6m_5 - mm_8, \\ m_{18} &= m_9m_7 - m_5m_{10}, \quad m_{19} = m_9m_6 - mm_{10}, \quad m_{20} = mm_7 - m_6m_5\end{aligned}\tag{B.1}$$

the physical quantities are obtained as follows

$$\begin{aligned}
u_r(r, z) &= \frac{r}{\pi \tilde{m}} \sum_{i=1}^4 a_{1i} \lambda_i \tilde{d}_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{1 + \zeta_i^2} \right) - v_{rz} \frac{\delta_0}{h} r, \\
u_z(r, z) &= \frac{2a}{\pi \tilde{m}} \sum_{i=1}^4 \eta_i \tilde{d}_i \left(1 - \zeta_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i \right) \right) + \frac{\delta_0}{h} z, \\
\varphi(r, z) &= -\frac{2a}{\pi \tilde{m}} \sum_{i=1}^4 a_{3i} \eta_i \tilde{d}_i \left(1 - \zeta_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i \right) \right) - \frac{\Phi_0}{h} z, \\
\Psi(r, z) &= -\frac{2a}{\pi \tilde{m}} \sum_{i=1}^4 a_{4i} \eta_i \tilde{d}_i \left(1 - \zeta_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i \right) \right) - \frac{\Psi_0}{h} z, \\
\sigma_{zr}(r, z) &= -\frac{2r}{\pi a \tilde{m}} \sum_{i=1}^4 a_{5i} \tilde{d}_i \frac{\eta_i}{(1 + \zeta_i^2)(\zeta_i^2 + \eta_i^2)}, \\
\sigma_{zz}(r, z) &= -\frac{2}{\pi \tilde{m}} \sum_{i=1}^4 \frac{a_{5i}}{\lambda_i} \tilde{d}_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{\zeta_i^2 + \eta_i^2} \right) + \sigma^*, \\
\sigma_{rr}(r, z) &= \frac{2}{\pi \tilde{m}} \sum_{i=1}^4 a_{5i} \lambda_i \tilde{d}_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{\zeta_i^2 + \eta_i^2} \right) - (c_{11} - c_{12}) \left(\frac{u_r}{r} + v_{rz} \frac{\delta_0}{h} \right), \\
\sigma_{\theta\theta}(r, z) &= \frac{2}{\pi \tilde{m}} \sum_{i=1}^4 a_{5i} \lambda_i \tilde{d}_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{\zeta_i^2 + \eta_i^2} \right) - (c_{11} - c_{12}) \left(\frac{\partial u_r}{\partial r} + v_{rz} \frac{\delta_0}{h} \right), \\
E_r(r, z) &= -\frac{2r}{\pi a \tilde{m}} \sum_{i=1}^4 a_{3i} \tilde{d}_i \frac{\eta_i}{(1 + \zeta_i^2)(\zeta_i^2 + \eta_i^2)}, \\
E_z(r, z) &= -\frac{2}{\pi \tilde{m}} \sum_{i=1}^4 a_{3i} \lambda_i \tilde{d}_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{\zeta_i^2 + \eta_i^2} \right) + \frac{\Phi_0}{h}, \\
H_r(r, z) &= -\frac{2r}{\pi a \tilde{m}} \sum_{i=1}^4 a_{4i} \tilde{d}_i \frac{\eta_i}{(1 + \zeta_i^2)(\zeta_i^2 + \eta_i^2)}, \\
H_z(r, z) &= -\frac{2}{\pi \tilde{m}} \sum_{i=1}^4 a_{4i} \lambda_i \tilde{d}_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{\zeta_i^2 + \eta_i^2} \right) + \frac{\Psi_0}{h},
\end{aligned} \tag{B.2}$$

$$D_r(r, z) = -\frac{2r}{\pi a \tilde{m}} \sum_{i=1}^4 a_{6i} \lambda_i^2 \tilde{d}_i \frac{\eta_i}{(1 + \zeta_i^2)(\zeta_i^2 + \eta_i^2)},$$

$$D_z(r, z) = -\frac{2}{\pi \tilde{m}} \sum_{i=1}^4 a_{6i} \lambda_i \tilde{d}_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{\zeta_i^2 + \eta_i^2} \right) + D^*,$$

$$B_r(r, z) = -\frac{2r}{\pi a \tilde{m}} \sum_{i=1}^4 a_{7i} \lambda_i^2 \tilde{d}_i \frac{\eta_i}{(1 + \zeta_i^2)(\zeta_i^2 + \eta_i^2)},$$

$$B_z(r, z) = -\frac{2}{\pi \tilde{m}} \sum_{i=1}^4 a_{7i} \lambda_i \tilde{d}_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{\zeta_i^2 + \eta_i^2} \right) + B^*.$$

The following integrals are used

$$\int_0^{\infty} \frac{d}{d\xi} \left(\frac{\sin \xi a}{\xi} \right) e^{-\xi \lambda_i z} J_0(r\xi) d\xi = -a \eta_i \left[1 - \zeta_i \left(\frac{\pi}{2} - \tan^{-1} \zeta_i \right) \right], \quad (\text{B.3})$$

$$\int_0^{\infty} \frac{d}{d\xi} \left(\frac{\sin \xi a}{\xi} \right) e^{-\xi \lambda_i z} J_1(r\xi) d\xi = -\frac{r}{2} \left(\frac{\pi}{2} - \tan^{-1} \zeta_i - \frac{\zeta_i}{1 + \zeta_i^2} \right), \quad (\text{B.4})$$

$$\int_0^{\infty} \xi \frac{d}{d\xi} \left(\frac{\sin \xi a}{\xi} \right) e^{-\xi \lambda_i z} J_0(r\xi) d\xi = -\frac{\pi}{2} + \tan^{-1} \zeta_i + \frac{\zeta_i}{\zeta_i^2 + \eta_i^2}, \quad (\text{B.5})$$

$$\int_0^{\infty} \xi \frac{d}{d\xi} \left(\frac{\sin \xi a}{\xi} \right) e^{-\xi \lambda_i z} J_1(r\xi) d\xi = -\frac{r}{a} \frac{\eta_i}{(1 + \zeta_i^2)(\zeta_i^2 + \eta_i^2)}, \quad (\text{B.6})$$

where

$$\zeta_i(r, z, a, \lambda_i) = \frac{1}{\sqrt{2a}} \sqrt{\sqrt{(r^2 + \lambda_i^2 z^2 - a^2)^2 + 4\lambda_i^2 z^2 a^2} + (r^2 + \lambda_i^2 z^2 - a^2)}, \quad (\text{B.7})$$

$$\eta_i(r, z, a, \lambda_i) = \frac{1}{\sqrt{2a}} \sqrt{\sqrt{(r^2 + \lambda_i^2 z^2 - a^2)^2 + 4\lambda_i^2 z^2 a^2} - (r^2 + \lambda_i^2 z^2 - a^2)}$$

and λ_i are the roots of Eq.(2.7) with positive real parts.

Nomenclature

a – radius of the penny – shaped crack

- B_c – magnetic induction supported by the crack gap
 B_r, B_z – magnetic induction components
 D_c – electric displacement supported by the crack gap
 D_r, D_z – electric displacement components
 E_r, E_z – electric field components
 H_r, H_z – magnetic field components
 d_{11}, d_{33} – magnetoelectric constants
 e_{15}, e_{31}, e_{33} – piezoelectric constants
 J_m – Bessel function of the first kind of order m
 K_I – mode I stress intensity factor
 K_D – electric displacement intensity factor
 K_B – magnetic induction intensity factor
 $K_I^* = (2/\pi)\sigma_0\sqrt{a}$ – the classical result
 r – radial coordinate
 q_{15}, q_{31}, q_{33} – piezomagnetic constants
 u_r, u_z – components of displacement vector
 z – vertical coordinate
 Δu_z – crack opening displacement
 $\Delta\phi$ – drop in electric potential across the crack
 $\Delta\psi$ – drop in magnetic potential across the crack
 $\epsilon_{11}, \epsilon_{33}$ – dielectric constants (permittivities)
 $\epsilon_c = \epsilon_r\epsilon_0$ – dielectric constants of the material within the crack gap
 $\epsilon_0 = 8.85 \times 10^{-12} \text{ F/m}$ – dielectric permittivity of air (or vacuum)
 μ_{11}, μ_{33} – magnetic constants (permeabilities)
 $\mu_c = \mu_r\mu_0$ – magnetic permeability of the material within the crack gap
 $\mu_0 = 4\pi \times 10^{-7} \text{ N/A}^2$ – magnetic permeability of air (or vacuum)
 $\epsilon_{rr}, \epsilon_{\theta\theta}, \dots$ – components of stress tensor
 ϕ – electric potential
 ψ – magnetic potential
 $\sigma_{rr}, \sigma_{\theta\theta}, \sigma_{zz}, \sigma_{rz}$ – components of stress tensor
 ξ – Hankel parameter
 $\lambda_i (i = 1, 2, 3, 4)$ – dimensionless roots appearing in general solution (eigenvalues defined by Eq.(2.7))

References

- Chen W.Q., Lee K.Y. and Ding H.J. (2004): *General solution for transversely isotropic magneto electro thermo elasticity and the potential theory method.* – International Journal of Engineering Sciences, vol.42, pp.1361-1379.
- Hao T.H. and Shen Z.Y. (1994): *A new electric boundary condition of electric fracture mechanics and its application.* – Engineering Fracture Mechanics, vol.47, pp.793-802.
- Niraula P.P. and Wang B L.(2006): *A magneto electro elastic material with a penny shaped crack subjected to temperature loading.* – Acta Mech., vol.187, pp.151-168.
- Rogowski B.(2007): *The limit electrical permeable crack model in linear piezoelectroelasticity.* – International Journal of Pressure, Vessel and Piping, vol.84, pp.572-581.
- Rogowski B. (2011): *The mode III crack emanating from an elliptical hole in the piezo – electro – magneto – elastic materials.* – Archives of Applied Mechanics, vol.81, pp.1607-1620.

- Wang B.L. and Mai Y.W. (2007): *Applicability of the crack – face electromagnetic boundary conditions for fracture of magnetoelastic materials.* – International Journal of Solids and Structures, vol.44, pp.387-398.
- Zhao M.H., Yang F. and Liu T. (2006): *Analysis of a penny – shaped crack in a magneto – electro – elastic medium.* – Philosophical Magazine, vol.86, pp.4397-4416.
- Zhong G.C. and Li X.F. (2007): *T – stress analysis for a Griffith crack in magnetoelastic solid.* – Archive of Applied Mechanics, vol.78, pp.117-125.
- Zhong X.C. and Li X.F. (2008): *Fracture analysis of magnetoelastic solid with a penny – shaped crack by considering the effects of the opening crack interior.* – International Journal of Engineering Science, vol.46, pp.374 – 390.
- Zhong X.C. (2009): *Analysis of a dielectric crack in a magnetoelastic layer.* – International Journal of Solids and Structures, vol., pp.4221 – 4230.

Received: December 1, 2011

Revised: September 2, 2012