

Iwona Sulima, Paweł Hyjek, Tomasz Tokarski

Influence of annealing conditions on the properties and microstructure of steel composites

Wpływ warunków wyżarzania na właściwości i mikrostrukturę kompozytów o podstawie stali austenitycznej

Abstract

Samples made of AISI 316L stainless steel reinforced with 8 vol.% TiB₂ particles were prepared using the high pressure-high temperature (HP-HT) method. Next, the composites were annealed at a temperature of 1200°C for different holding times. The influence of the annealing temperature and time on the properties and microstructure of AISI316L+8% vol.TiB₂ composites was investigated. The structural studies showed the formation of phases containing chromium, molybdenum and boron.

Key words: composites, annealing, properties, diboride titanium

Streszczenie

Głównym celem pracy było określenie wpływu temperatury oraz czasu wyżarzania na właściwości i mikrostrukturę kompozytów umacnianych ceramiką TiB₂. Proces spiekania materiałów kompozytowych o podstawie stali austenitycznej przeprowadzono przy zastosowaniu spiekania wysokociśnieniowego-wysokotemperaturowego (HP-HT). Kompozyty były wyżarzane w temperaturze 1200°C w różnych czasach. Stwierdzono, że mikrotwardość oraz odporność na ścieranie obniża się już po 30 minutach wyżarzania. Badania mikrostrukturalne wykazały powstanie dużych faz zawierających chrom, molibden oraz bor.

Słowa kluczowe: kompozyty, wyżarzanie, właściwości, dwuborek tytanu

1. Introduction

Metal matrix composites (MMCs) are currently being developed as possible structural materials, offering improved elastic modulus, strength, good properties elevated temperature and control over the coefficient of thermal expansion [1, 2]. The addition of high modulus refractory particles to a ductile metal matrix produces a material which properties are intermediate between the matrix alloy and ceramic reinforcement. However, the optimum properties of metal matrix composites depends additionally on a proper selection of the metallic matrix material, the reinforcing phase, the methods of producing and the parameters of these methods [3, 4].

The 316L austenitic stainless steel is nowadays a widely used engineering material due to its excellent corrosion and oxidation resistance and good formability. However, the application of this material is hindered by its low mechanical strength and poor anti-friction properties. Strengthening stainless steel has drawn much attention in the past decades and various approaches have been developed, such as varying its chemical compositions to induce solid solution hardening and grain refinement [5–8]. Nowadays, the TiC and TiB₂ particles are expected to be the best reinforcements for steel matrix composites because of their high thermal stability at a higher temperature, good wettability, high modulus of elasticity, low density and their relative stability with steel matrix [9]. The experiments of the authors [10–14] have shown that steel matrix composites reinforced with TiB₂ particulates have increased mechanical strength, hardness, and wear resistance. In future, such materials may find their application in the manufacturing of products and semi-products operating in changing operating conditions. In this case, the determination of the influence of temperature and the duration of heat-treatment on the properties and structure of composites is an important issue due to their further application and utilization.

In the present study, steel matrix composites reinforced with submicron-scale TiB₂ particles were fabricated by the high pressure-high temperature sintering method. The effects of annealing conditions on the microstructures and properties of composites were investigated.

2. Experimental procedure

Powders of 99.9% pure titanium diboride (H.C. Starck) and austenitic stainless steel with an average particle size of 2.5-3.5 μm, respectively, were used in this work. The composite powders were prepared by mixing in a turbula mixer for 12 hours. The composites were consolidated using the high pressure-high temperature (HP-HT) method. Figure 1 presents the scheme of the Bridgman-type HP-HT apparatus. The mixtures were preliminarily consolidated into pellets of diameter 15 mm and height 5 mm under pressure of ~200 MPa. Next, the discs were placed into the internal graphite heater in a special gasket assembly for sintering (Fig. 2). The samples were sintered at temperatures of 1000°C and 1300°C and a pressure of 7 ± 0.2 GPa for 60 seconds.

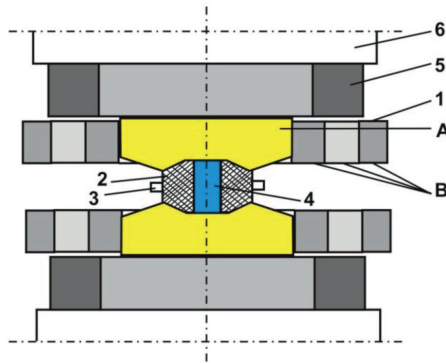


Fig. 1. Cross-section of the high pressure – high temperature Bridgman type apparatus: 1 – cell pressure (A – carbide anvil, B – set of steel rings); 2 – pyrophyllite gasket; 3 – pyrophyllite lining; 4 – assembly for sintering; 5 – carbide backing block; 6 – bottom platen [15]

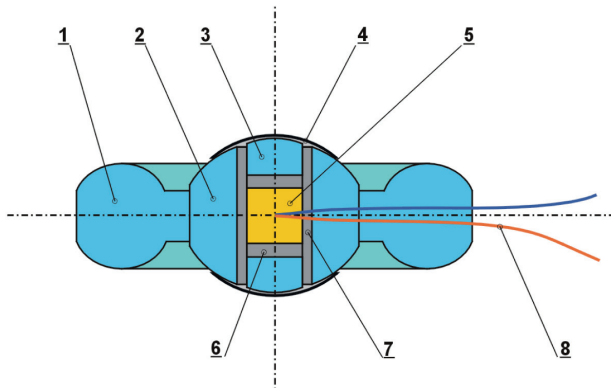


Fig. 2. Assembly for high pressure-high temperature sintering: 1 – pyrophyllite external gasket; 2 – internal gasket; 3 – ceramic plate; 4 – molybdenum plate; 5 – sintered sample; 6, 7 – graphite heaters; 8 – thermocouple (optionally) [16]

Main advantages of the HP-HT method are:

- shortening of the duration of the sintering,
- possibility of application of the sintering temperature of 2000°C and higher depending on the duration of the sintering,
- acceleration of diffusion process almost 100% degree of consolidation of sinters,
- very low porosity,
- prohibits the grain growth of materials,
- refined microstructure of sintered materials,
- possibility of sintering of a large group of materials, for example: diamond cubic boron nitride (cBN), TiB_2 ceramics, gradient materials, composite materials and others.

The densities of the sintered samples were determined by weighing in air and water using the Archimedes' method. Uncertainty of measurements was 0.02 g/cm³. Young's moduli of the composites were measured based on the velocity of the ultrasonic waves transition through the sample using ultrasonic flaw detector Panametrics Epoch III. The accuracy of calculated Young's modulus is estimated at 2%. Next, samples were polished using conventional polishing techniques. Sintered samples were prepared by lapping on a cast iron plate with diamond paste. The microhardness of the composites was tested by means of a Vickers microhardness tester (NEXUS 4000), the applied load was of 2.94 N. Standard deviations of HV0.3 values were no more than 4% of the average values.

After sintering the composites were annealed at 1200°C in a furnace for different holding times such as 0.5, 1, 2, 4, 8, 16 and 32 h. Annealing was carried out in a vacuum of about 10⁻⁴ MPa. Each sample was placed separately in a quartz tube where a vacuum was attained, next the tube was closed and put in the furnace. The heat rate was 5°C/min. After each annealing stage, the metallographic specimen was prepared. Then, microhardness was measured and the structure of the composites was observed. A JEOL JSM 6610LV scanning electron microscope with energy dispersive spectrometry (EDS) and Hitachi SU-70 with Wavelength Dispersive Spectroscopy (WDS) were used for microscopy studies of composites before and after the annealing treatment.

The tribological properties for composites were examined before and after annealing (32 h). Tribological tests were carried out at UMT-2T (producer CETR, USA) ball-on-disk tribotester. The tests were carried out without lubricant according to the ISO 20808:2004(E) standard [17]. For the ball-on-disk method the sliding contact is brought by pushing a ball on a rotating disc specimen under a constant load. The loading mechanism applies a controlled load F_n to the ball holder. The friction force was measured continuously during the test using the extensometer. For each test, a new ball was used or the ball was rotated such that a new surface was in contact with the disc. After the mounting of the ball and sample, materials were washed in ethyl alcohol and dried. The roughness of the test surface was not more than 0.1 μm R_a . The following test conditions were established: ball made of Al₂O₃ (diameter of 3.175 mm), friction track diameter 4 mm, applied load 4 N; sliding speed 0.1 m/s; total sliding distance: 200 m, test duration: 2000s; room temperature. The friction coefficient and specific wear rate were determined.

3. Results

The selected physical-mechanical properties of composites sintered at different temperatures are presented in Table 1. The composites with the addition of 8% vol. TiB₂ were characterized by a high degree of densification: 98% and 100% of the theoretical density. Also, it showed no significant effect of sintering temperature on the Young's modulus. The values of Young's modulus are a similar: of 217 GPa and 221 GPa for

a temperature of 1000°C and 1300°C, respectively. However, the microhardness decreases with increasing the sintering temperature. In case of the temperature of 1000°C and 1300°C the microhardness receives values of 385 HV0.3 and 346 HV0.3, respectively.

Table 1. The properties of composites with 8 % vol. TiB₂ before annealing at 1200°C

Composites	Sintering parameters		
AISI 316L + 8 vol.% TiB ₂	Temperature, [°C]	1000	1300
	Pressure, [GPa]	7	
	Examined properties		
	Relative density (ρ_0), [g/cm ³]	7,73	7,81
	$\frac{\rho_0}{\rho_{Teor}}$	98	100
	Poisson's ratio	0.3	0.3
	Young's modulus, [GPa]	217	221
	$\frac{E}{E_0}$ [%]	92	93
	Vickers microhardness, HV0.3	385	346

The composite materials were annealed at 1200°C in subsequent times 0.5, 1, 2, 4, 8, 16 and 32 h. After each stage of the annealing, the metallographic specimens were prepared and microhardness was determined. Besides, observations of microstructure in time of the annealing were made. The results of microhardness measurements of the composites in the function of time are presented in Figure 3. Only after 0.5 h of the annealing of the composite materials, the drop of microhardness by 40% is noted. In the case of the composite sintered at 1000°C, the microhardness decreased from 385 HV0.3 to 244 HV0.3 but in the case of the composite sintered at 1300°C it decreased from 346 HV0.3 to 185 HV0.3. Prolongation of time of subsequent annealing cycles did not influence significantly the change of microhardness of the studied materials. After 32 h of annealing, the composites sintered at 1000°C and 1300°C achieved a similar microhardness of 215 HV0.3 and 207 HV0.3, respectively.

The drop in microhardness of the studied materials is connected with the microstructure changes appearing during annealing at 1200°C. The selected microstructure images of the composite materials taken before and after the annealing process are presented for comparison in Figures 4 and 5. Figures 4a and 5a correspond to the sintered composites before annealing. The TiB₂ particles (dark particles) are distributed nearly homogeneously in the steel matrix. Such a kind of particulate distribution is an important requirement to achieve enhanced mechanical and tribological properties of the composites.

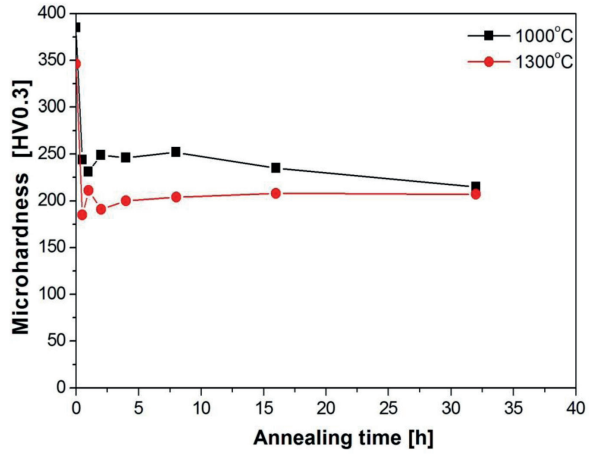


Fig. 3. Variation of microhardness with time of annealing

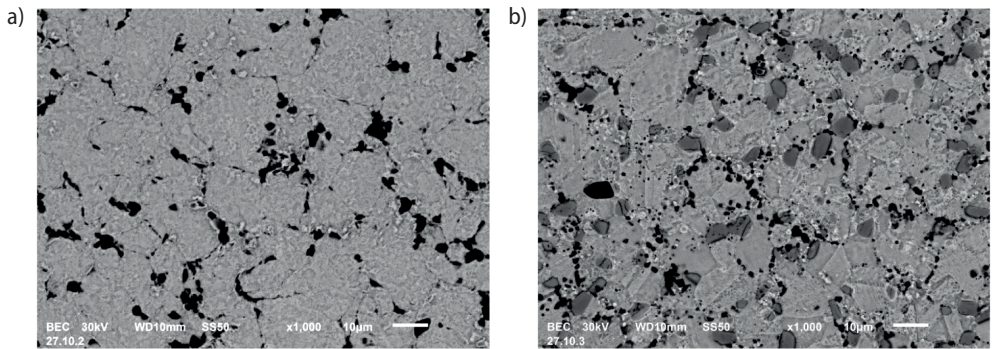


Fig. 4. The microstructure of composites sintered at 1000°C: a) before annealing; b) after annealing at 1200°C for 32 h

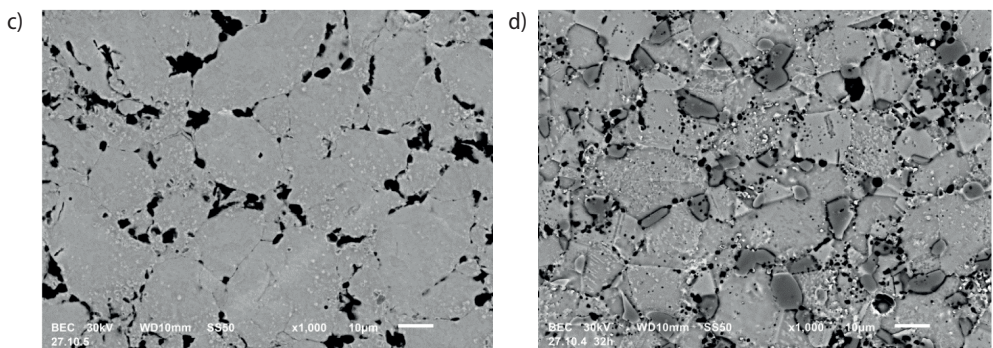


Fig. 5. The microstructure of composites (sintering temperature of 1300°C): a) before annealing; b) after annealing at 1200°C for 32 h

On the contrary, Figures 4b and 5b present the microstructure of the composite after 32 h of annealing at 1200°C. A change of morphology of TiB₂ precipitates (their refinement, coagulation and change of shape) was observed. The microstructure analysis indicated distribution of fine oval TiB₂ precipitates along the steel grain boundaries. Additionally, new large precipitates (medium-gray) with irregular shape appeared in the microstructure. It is to underline, that the observed changes in the microstructure manifested themselves only after 0.5 h of heat-treatment (Fig. 6). After the first stage of the treatment, new precipitates containing chromium, molybdenum and boron (results of point analysis by EDS are shown in Figure 6 and Table 2) form. The microstructure observations after successive cycles of treatment indicate an increase in the amount and size of the precipitates and change of the morphology of TiB₂ particles in a composite matrix. Moreover, WDS analysis (Fig. 7) confirmed the presence of chromium, molybdenum and boron in the observed precipitates. It can be suspected that during annealing, boron diffuses from ceramic TiB₂ into steel matrix followed by reaction with chromium and molybdenum, and finally forming a non-stoichiometric boride compound. The WDS analysis (Fig. 8) of the composite before annealing indicates the presence of TiB₂ precipitates only. In the case of these materials, the formation of regions rich in nickel next to TiB₂ precipitates was observed. The next stage of research will be a detailed microstructure analysis aimed at the identification of the formed precipitates.

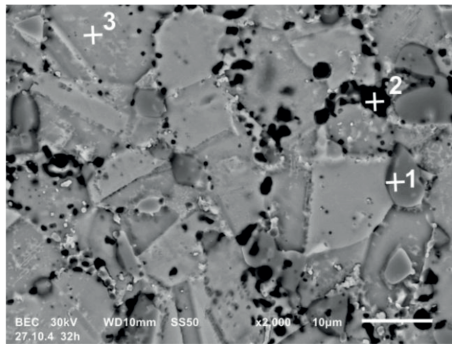


Fig. 6. The microstructure of composites (sintered at 1300°C) after annealing 0.5 h and corresponding point analysis (EDS)

Table 2. Point analysis of the analyzed composites

Point analysis	Chemical composition, [% wt.]							
	Fe	Cr	Ni	Ti	B	Mo	Mn	Si
1	41.8	50.2	2.2	0.7	0.0	3.4	0.3	0.2
2	24.9	8.2	5.0	45.3	15.4	0.7	0.1	0.4
3	56.4	17.9	12.7	1.8	0.0	1.2	0.2	0.8

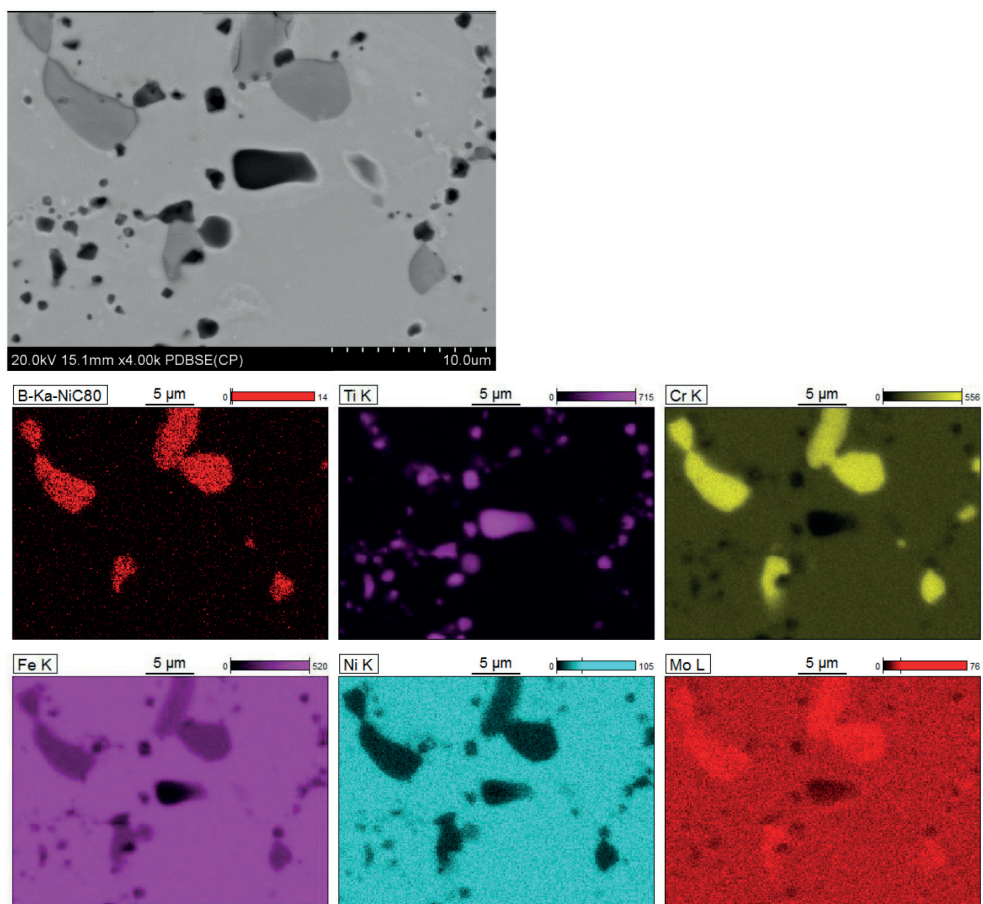


Fig. 7. The microstructure of composites (sintered at 1300°C) after annealing at 1200°C for 32 h with area analysis WDS

Next, the effect of the annealing conditions on the tribological properties of composites with 8% vol. TiB_2 were investigated. The wear rates and the friction coefficient obtained by ball-on-disk experiments are presented in Figure 9. Many hours of annealing also affected negatively the tribological properties of the composites: the friction coefficients are higher for the annealed composites (0.7–0.75) as compared to the values of the friction coefficient (0.5–0.56) of composites before the annealing (Fig. 9a). The specific wear rate is significantly higher for composites which were annealed at 1200°C. In this case, the wear rates oscillate $(648\text{--}715) \cdot 10^{-6} \text{ mm}^3/\text{Nm}$. It is evident that the applied heat treatment influences negatively wear resistance of materials. This is the result of the lower hardness and the fast wear of the steel composites.

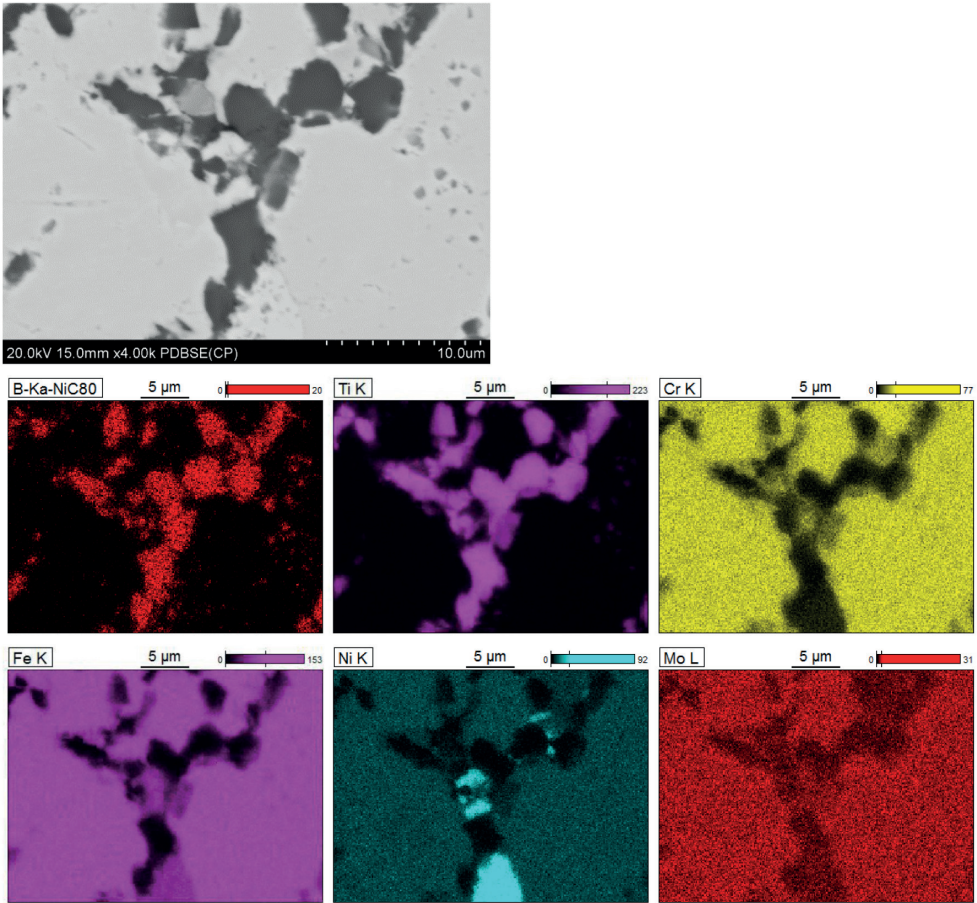


Fig. 8. The microstructure of composites (sintered at 1300°C) before annealing with area analysis WDS

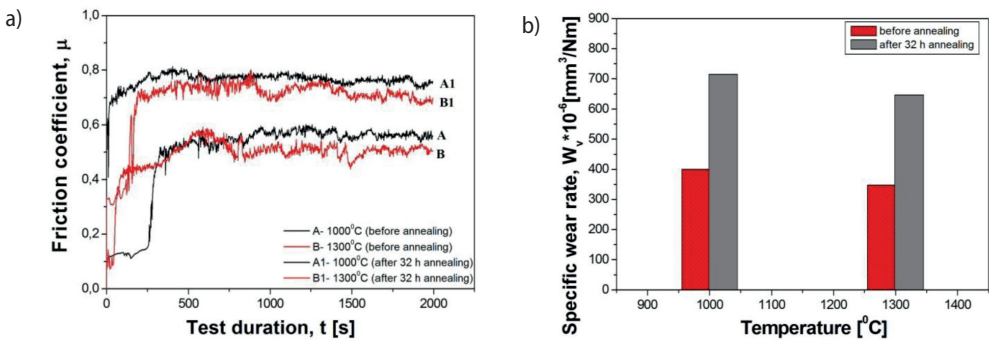


Fig. 9. The results of the: a) friction coefficient as a function of test duration; b) specific wear rate as a function of temperature

4. Conclusions

Two variants of the steel-TiB₂ composites with 8 vol.% of TiB₂ particles were investigated. The results showed that applied annealing conditions influenced negatively the steel-matrix composites. Evidently, the microhardness and wear resistance of the composites decreased when applied first annealing step (0.5 h). Prolonged time to 32 h did not affect significantly the tested properties due to the change of microstructure of the composites and the formation of phases containing chromium, molybdenum and boron.

Acknowledgements

This work was carried out with financial support through statutory funds of Pedagogical University in Cracow.

References

- [1] He P., Yue X., Zhang J.: *Hot pressing diffusion bonding of a titanium alloy to a stainless steel with an aluminum alloy interlayer*. Materials Science and Engineering A, 486 (2008), 171–176
- [2] Emadoddin E., Tajally M., Masoumi M.: *Damping behavior of Al/SiCP multilayer composite manufactured by roll bonding*. Materials & Design, 42 (2012), 334–338
- [3] Mazahery A., Shabani M.O.: *Tribological behaviour of semisolid-semisolid compocast Al–Si matrix composites reinforced with TiB₂ coated B₄C particulate*. Ceramics International, 38 (2012), 1887–1889
- [4] Nagarajan S., Dutta B.: *The effect of SiC particles on the size and morphology of eutectic silicon in cast A356/SiC composites*. Composites Science and Technology, 59 (1999), 897–902
- [5] Pelletier H., Muller D., Mille P., Cornet A., Grob J.J.: *Dose effect on mechanical properties of high-energy nitrogen implanted 316L stainless steel*. Surface and Coating Technology, 151 (2002), 377–385
- [6] Rawers J., Crogdon F., Krabbe R., Duttlinger N.: *Tensile characteristics of nitrogen enhanced powder injection moulded 316L stainless steel*. Powder Metallurgy, 39 (1996), 125–129
- [7] Ucok I., Ando T., Grant N.J.: *Property enhancement in Type 316L stainless steel by spray forming*. Materials Science and Engineering, 133A (1991), 284–287
- [8] Chen X.H., Lu J., Lu L., Lu K.: *Tensile properties of a nanocrystalline 316L austenitic stainless steel*. Scripta Materialia, 52 (2005), 1039–1044
- [9] Farid A., Guo S., Feng F.C.P., Lin T.: *TiB₂ and TiC stainless steel matrix composites*. Materials Letters, 61 (2007), 189–191
- [10] Tjong S.C., Lau K.C.: *Abrasion resistance of stainless-steel composites reinforced with hard TiB₂ particles*. Composites Science and Technology, 60 (2000), 1141–1146
- [11] Bacon D.H., Edwards L., Moffatt J.E., Fitzpatrick M.E.: *Fatigue and fracture of a 316 stainless steel metal matrix composite reinforced with 25% titanium diboride*. International Journal of Fatigue, 48 (2013), 39–47
- [12] Wang Y., Zhang Z.Q., Wang H.Y., Ma B.X., Jiang Q.C.: *Effect of Fe content in Fe–Ti–B system on fabricating TiB₂ particulate locally reinforced steel matrix composites*. Materials Science and Engineering, 422A (2006), 334–339
- [13] Sulima I., Klimczyk P., Malczewski P.: *Effect of TiB₂ particles on the tribological properties of stainless steel matrix composites*. Acta Metallurgica Sinica (English Letter), 27, 1 (2014), 12–18

- [14] Sulima I., Jaworska L., Figiel P.: *Influence of processing parameters and different content of TiB_2 ceramics on the properties of composites sintered by high temperature – high pressure (HT-HP) method*. Archives of Metallurgy and Materials, 59, 1, (2014), DOI: 10.2478/amm-2014-0033
- [15] Jaworska L.: *Ceramic cutting-edge materials*, Tooling Materials, The Institute of Advanced Manufacturing technology, Krakow, 2011
- [16] Jaworska L.: *Wysokociśnieniowe spiekanie proszków diamentowych*. Prace IOS, seria Zeszyty Naukowe, 82, Kraków, 2002
- [17] *International Standard, Fine ceramics (advanced ceramics, advanced technical ceramics) - Determination of friction and wear characteristics of monolithic ceramics by ball-on-disc method*, ISO 20808:2004(E)