

Increasing the bulk density of STPP – influence of the process parameters

Katarzyna Gorazda*, Marcin Banach, Agnieszka Makara, Zbigniew Wzorek

Institute of Chemistry and Inorganic Technology, Cracow University of Technology, ul. Warszawska 24, 31-155 Kraków, Poland, e-mail: gorazda@chemia.pk.edu.pl,

The new requirements that were placed on STPP, like high bulk density, the proper relation of Form I and Form II and suitable physicochemical properties, resulted in the development of the present production methods. The paper presents the research results on increasing the bulk density of STPP by a chemical method. In the introduced method the solid sodium phosphate from spray drying and sodium orthophosphate solution, after acid neutralization, were rubbed together. Such an operation changes the physicochemical properties of the dried sodium phosphate before calcining, which results in increasing the bulk density of STPP to a level of 0.80 kg/dm³. The dependence of STPP bulk density on process parameters such as: sodium orthophosphate solution to solid sodium phosphate mass ratio, temperature of dosed sodium orthophosphate solution, as well as the calcining temperature of mixtures were analysed.

Keywords: sodium tripolyphosphate, STPP, high bulk density.

INTRODUCTION

The detergent market is one of the most competitive in the world. Despite the presence of different forms of detergent formulas like liquids, gels or tablets, washing powders are still most often used by Polish consumers.

Sodium tripolyphosphate (STPP), because of its beneficial properties, is one of the most commonly used washing powder components in the form of an active builder¹⁻³. The development of production methods and inactive builders elimination from the washing formula initiate evolution to compact powders, concentrates and tablets manufacturing. Such products are more effective and are characterized by higher bulk density than the former ones, which reduces the washing costs and improves the economic and ecological parameters⁴.

The STPP production consists of the following stages: phosphoric acid neutralization with soda ash or caustic soda, dehydration of the obtained mixture and its calcining. Technological solutions are based on a one-stage method, where dehydration and calcining are realized in one apparatus, or a two-stage method which separates these processes³. In the two-stage method the mixture of monosodium- and disodium hydrogen phosphates obtained after the neutralization process is dried in a spray drier, where partial condensation to sodium pyrophosphates occurs and solid mixtures receive a structure of "empty shells" with low density of around 0.4 kg/dm³^{5, 10}. In the final stage the mixture of sodium ortho- and pyrophosphates is calcined in a rotary kiln, where further condensation to STPP takes place. The calcining temperature relates to the parameters of final products and is on average 350–550°C. Bulk density of the final product is increased from 0.45–0.65 kg/dm³ to nearly 0.9 kg/dm³ during further technological operations of deep milling, hydration or compactation⁵. The milling operation increases the product bulk density to 0.85 kg/dm³ but enlarging the fine-grain fraction reduces its possible use. Methods of granular STPP production, widely described in the literature, are based on the hydration process of STPP after calcining⁶⁻⁹.

The presented solutions result in higher energy consumption, hence the modification of accessible methods of raising the bulk density of STPP is well-grounded. Such

a method, in wide demand, should enable obtaining STPP with suitable and controlled quality parameters, higher concentration and reduced energy consumption.

The conducted research reveals that the bulk density of STPP can be increased by addition of water or sodium orthophosphate solution to a semi-finished product from spray drying before calcining. Such an operation results in partial dissolving of dried sodium phosphate and hydration of phosphates salts, and in effect the charge for calcining has different physicochemical characteristic, which doubles the bulk density of the product after calcining¹⁰⁻¹².

EXPERIMENTAL SECTION

The presented research series comprised the process of increasing bulk density by rubbing the mixture of solid sodium phosphates (SP), used also at our earlier investigations¹⁰⁻¹², with the solution of liquid sodium orthophosphates (LOP), both of which were semi-products from the technological plant of obtaining STPP. The P₂O₅ content of the used semi-products was respectively: 27.35% at concentrated liquid sodium orthophosphates and 51.16% at solid sodium phosphates. 15–30 g of LOP solution were added with the constant velocity 800 μl/s to 100 g of SP while rubbing the components for the constant time 120 s in a laboratory mortar. The LOP solution with the concentration of 13.36% P₂O₅ was prepared by dilution of the concentrated liquid sodium orthophosphates with water in the 1:1 mass ratio and added in the two temperatures of 30°C and 80°C. The obtained mixtures with a variable content of the LOP solution (Table 1) were then calcined in a laboratory chamber kiln at a temperature of 350°C and 550°C for 1 h.

The phase composition of the SP, mixtures, as well as products was identified with the X-ray diffraction method (Philips X'Pert diffractometer), the thermal process course was observed during the thermal analysis (2960 Simultaneous DTA-DTG TA Instruments). Both the sieve analysis and bulk density analysis of the SP and products were carried out according to a standard method^{14, 15}. The bulk density analysis was marked for constant specified grain composition: 10% fraction above 1.00 mm; 20% fraction between 0.85–1.00 mm; 5% – 0.60–0.85 mm; 58% – 0.25–0.60 mm and 7% fraction lower than 0.25 mm¹⁶.

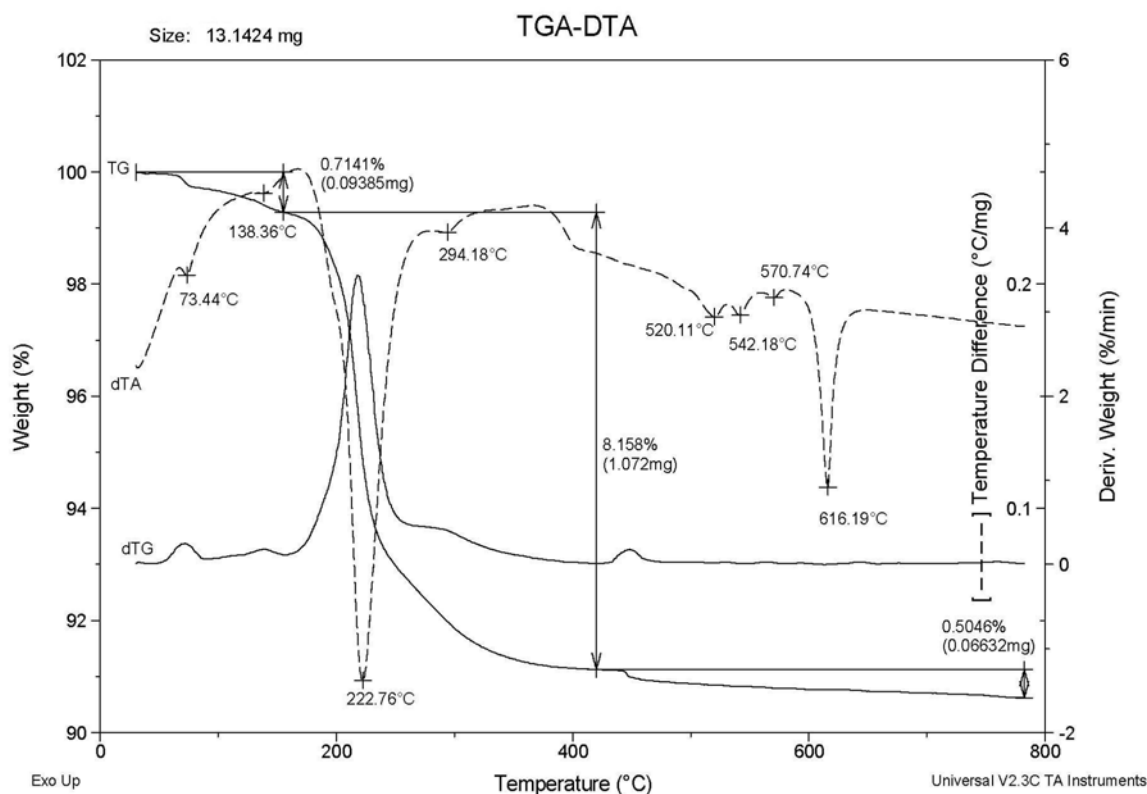


Figure 2. Thermal analysis of the dried sodium phosphates (SP)

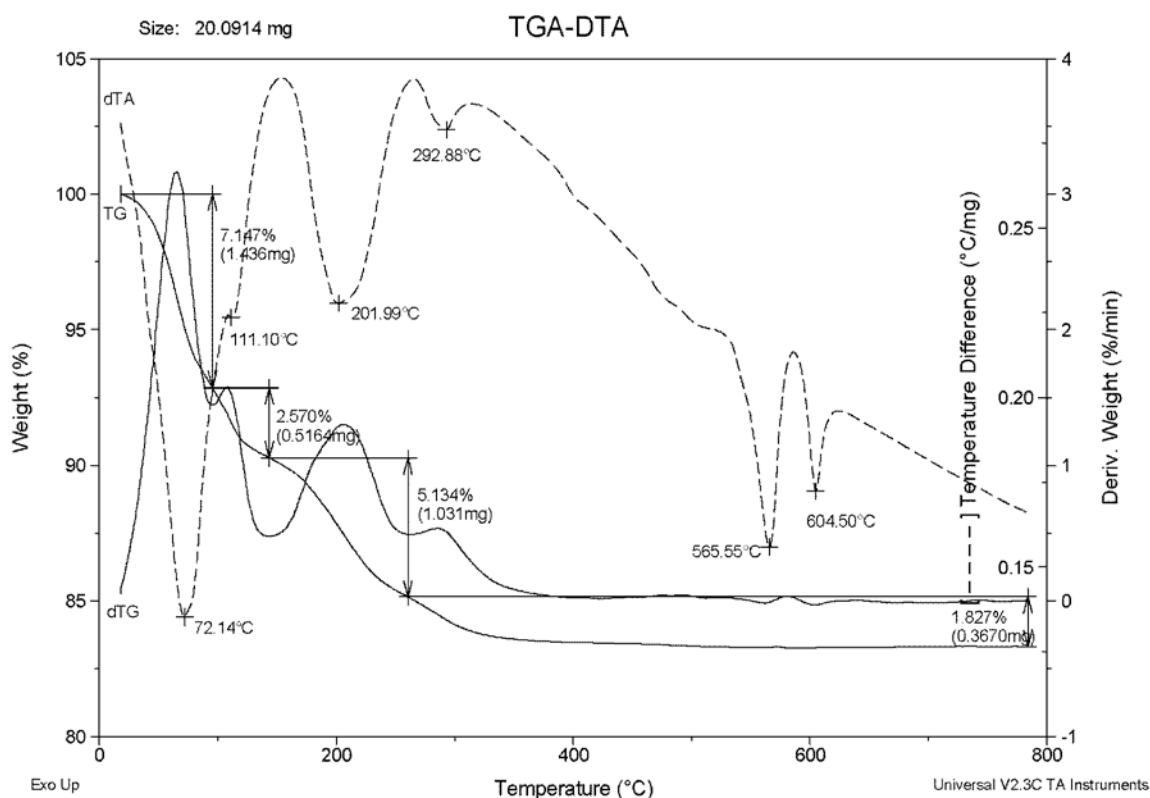


Figure 3. Thermal analysis of the mixture of dried sodium phosphates (SP) and the solution of liquid sodium orthophosphates (LOP) at the mass ratio 0.15 [g/g] – mixture 5

grains above 1.00 mm and 13.82% grains between 0.6–0.85 mm. The grained fraction smaller than 0.25 mm and the fraction between 0.85–1.00 mm had the lowest share, amounting to 5.67% and 4.87%, respectively. The material is even-grained, the different granularity coefficient is on average 2.27, and the grains equivalent diameter 0.55 mm. Calcining the SP at a temperature of 350°C results in de-

creasing the quantity of the following fractions: above 1.00 mm, 0.85–1.00 mm and 0.25–0.6 mm, and increasing the quantity of the grains between 0.6–0.85 and those smaller than 0.25 mm. The different granularity coefficient is on average 2.30 and the grains equivalent diameter 0.32 mm. A higher SP calcining temperature (550°C) increases only the fine-grain fraction up to 16.21%. The

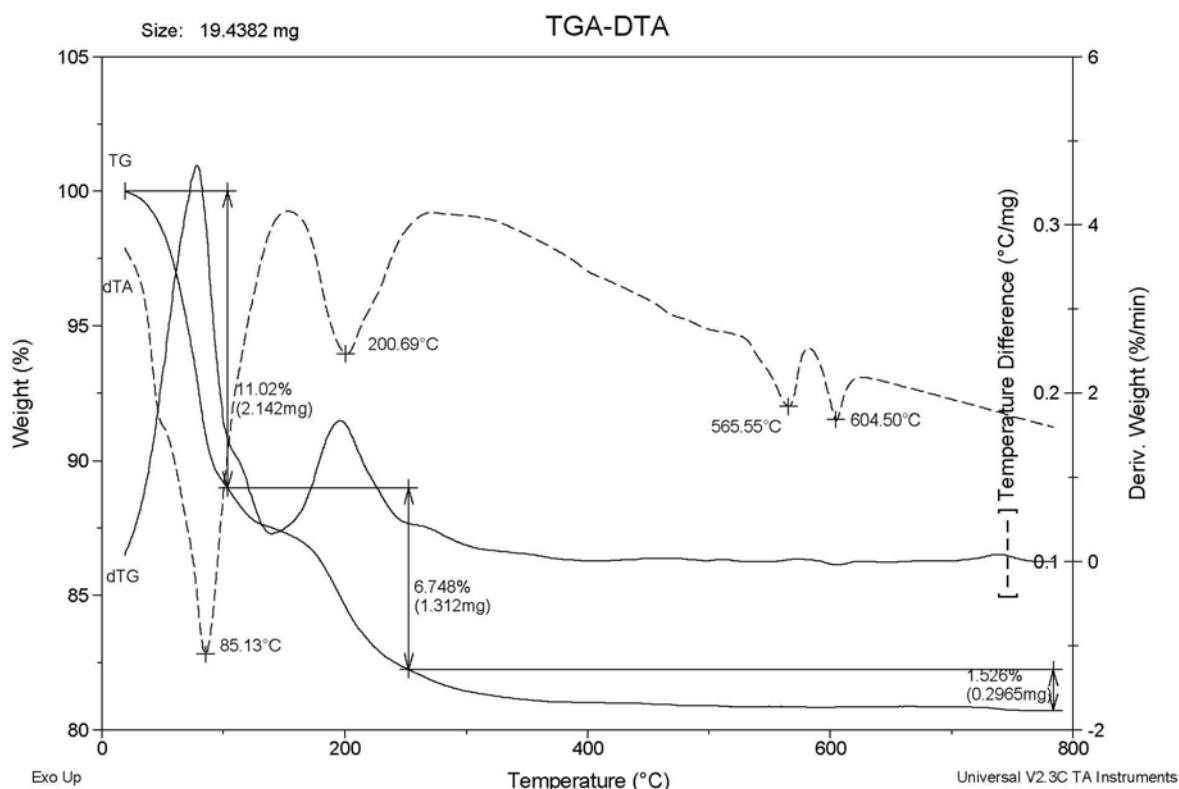


Figure 4. Thermal analysis of the mixture of dried sodium phosphates (SP) and the solution of liquid sodium orthophosphates (LOP) at the mass ratio 0.30 [g/g] – mixture 8

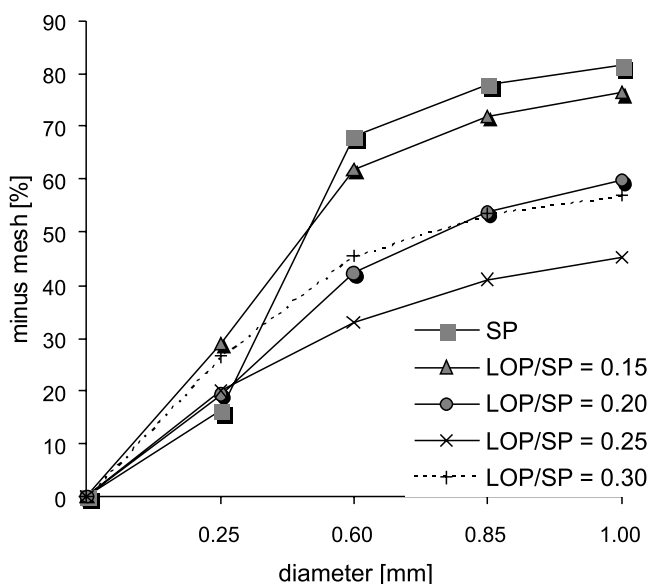


Figure 5. The curves of minus mesh of a STPP products after calcining mixtures 1 to 4 at temperature 550°C in comparison to SP

different granularity coefficient rises to 3.82 and the grains equivalent diameter to 0.47 mm on average. The addition of the LOP solution changes the physicochemical properties of the dried sodium phosphate before calcining. With the added amount of the LOP solution, mixtures consistency changes its form from a loose material to paste. As a consequence, the product received after calcining of the mixtures 1–8 was of different grains. An average different granularity coefficient increased from 6.32 (mixtures 1 and 5 with the lowest addition of the LOP solution) to 11.39 (mixtures 4 and 8). The changes in grain size distribution observed in the calcining products are character-

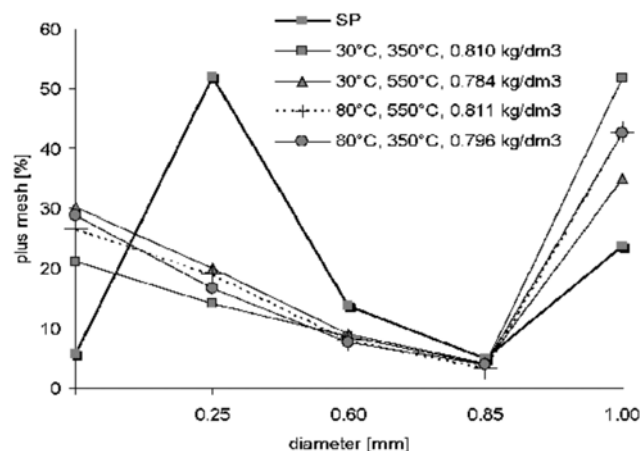


Figure 6. The curves of plus mesh of a STPP products with the highest bulk density in comparison to SP

ized by cumulative minus mesh curves (Figure 5) and plus mesh curves for the mixtures with the highest bulk density (Figure 6).

The bulk density of the calcining products strongly depends upon the amounts of the LOP solution added to the prepared mixtures. Moreover, the LOP solution temperature and the calcining temperature of mixtures also influence the bulk density of STPP products (Figures 7 and 8). With the increase in the liquid to solid phase mass ratio from 0.15 to 0.30 the bulk density of the products rises from 31% to 92% in comparison to the SP. Lesser influence is noticed for the temperature of the LOP solution added to mixtures before calcining. With dosing 15 g of the solution at a temperature of 80°C, the bulk density of STPP obtained after calcining at 550°C is 10% higher than in the case of using the same solution at a temperature of 30°C. A higher calcining temperature of mixtures

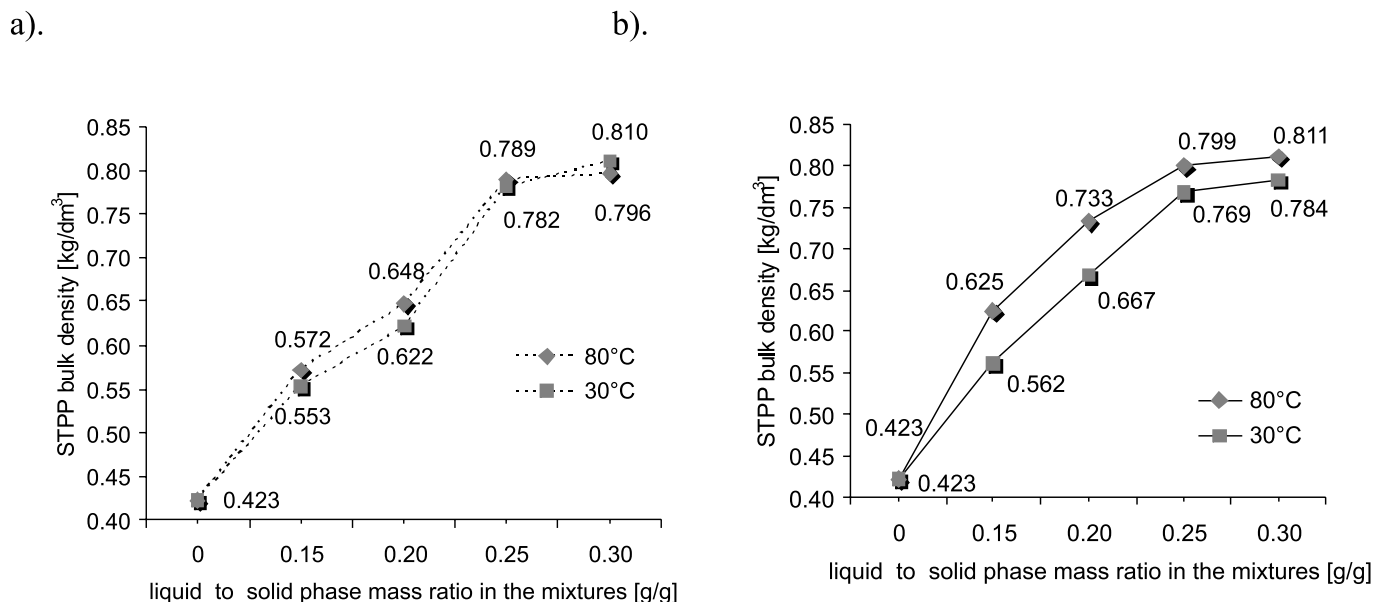


Figure 7. The influence of the mass ratio of the LOP solution to SP and the solution temperature on bulk density of STPP obtained after calcining at : a). 350°C, b). 550°C

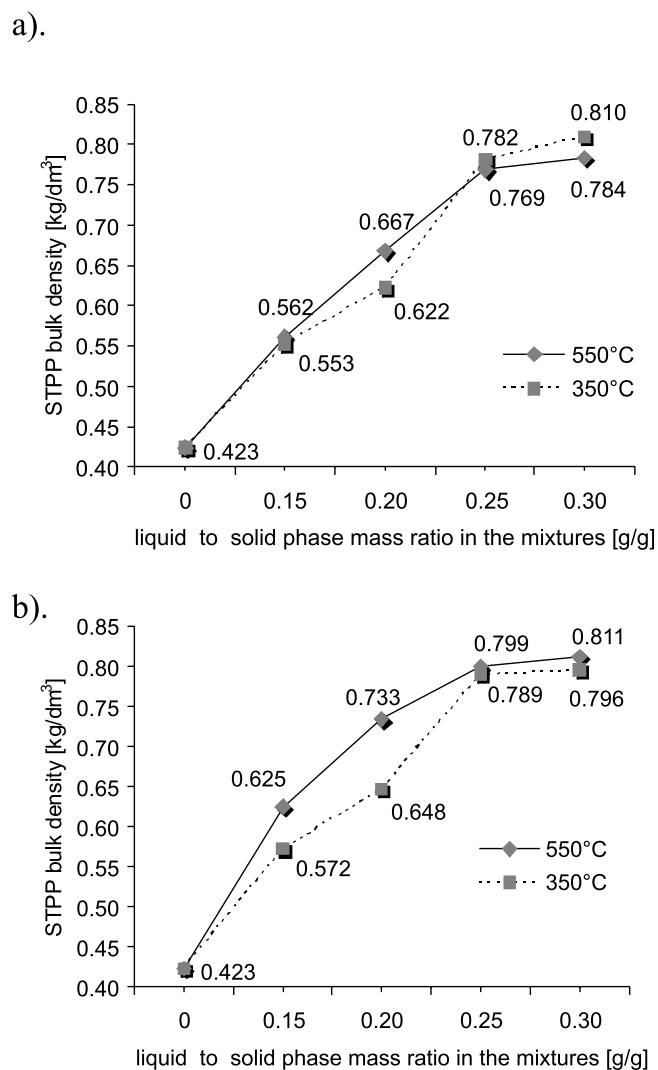


Figure 8. The influence of the mass ratio of the LOP solution to SP and the calcining temperature on bulk density of the obtained STPP when the LOP solution was dose at temperature : a). 30°C, b). 80°C

increases the bulk density of the obtained STPP only by up to 13% in the case of mass ratio 0.20 and the solution temperature 80°C.

The highest increase in bulk density was noticed for a mixture prepared by rubbing 100 g of the SP with 30 g of the LOP solution dosed at a temperature of 80°C and calcined at 550°C. The obtained form I of STPP reached the bulk density of 0.811 kg/dm³.

CONCLUSION

It was found that there is a possibility of increasing the bulk density of the STPP by the chemical method. In the introduced method the solid sodium phosphate from spray drying and sodium orthophosphate solution, after acid neutralization, can be rubbed together at a proper mass ratio. Such an operation changes the physicochemical properties of the dried sodium phosphate before calcining, which results in increasing the bulk density of STPP to over 0.80 kg/dm³.

The bulk density of the calcining products strongly depends upon the amounts of the liquid orthophosphates solution added to the prepared mixtures. The bulk density of the products rises 92% in comparison to the SP when the 0.30 liquid to solid phase mass ratio was applied. Other analysed parameters like temperature of dosed sodium orthophosphate solution and calcining temperature of mixtures have lesser influence on bulk density of the obtained STPP.

This method allows producing the granular STPP phase I with the bulk density 0.811 kg/dm³ when 100 g of the SP is rubbed with 30 g of the LOP solution dosed at a temperature of 80°C and then calcined at 550°C. The process parameters optimisation is an object of our further research.

Acknowledgement

This study was supported by the research grant 0163/B/H03/2008/34.

LITERATURE CITED

1. Broze, G., (1999). *Handbook of Detergents, Part A: Properties*, CRC Press.
2. CEEP (2007, July). *Function of phosphates in detergents*. Retrieved July 14, 2008, from <http://www.ceep-phosphates.org>.
3. Kowalski, Z., Kijkowska R., Pawłowska-Kozińska, D. & Wzorek, Z. (2002). Sodium tripolyphosphate and others condensed sodium phosphates production methods. *Pol. J. Chem. Tech.* 4(3), 27–33.
4. CEEP (2008, July). Press releases concerning phosphates and detergents was performance. Retrieved July 14, 2008, from <http://www.ceep-phosphates.org>.
5. Kijkowska, R., Kowalski, Z., Pawłowska-Kozińska, D., Wzorek, Z., & Gorazda, K. (2008). Tripolyphosphate made from Wet-process Phosphoric Acid with the use of a rotary kiln. *Ind. Eng. Chem. Res.* 47, 6821–6827. DOI: 10.1021/ie800412q
6. Dyer, J.N., Post, L.B. & Rosen, H.J. (1972). US Patent No. 3,650,685. Washington, D.C.: U.S. Patent and Trademark Office.
7. Hensler, P.L., Church, D.F. & Beger, R.W. (1981). US Patent No. 4,255,274. Washington, D.C.: U.S. Patent and Trademark Office.
8. Pals, R. (1979). US Patent No. 4,134,963. Washington, D.C.: U.S. Patent and Trademark Office.
9. Zorska, E., Cholewa, J., Gadomski, Z. & Olech, M. (2007). Polish Patent No. 196166B1. Polish Patent Office, (in Polish).
10. Banach, M., Kowalski, Z., Wzorek, Z. & Gorazda, K. (2009). A chemical method of the production of "heavy" sodium tripolyphosphate with the high content of Form I or Form II. *Pol. J. Chem. Tech.* 11(2), 13/20. DOI: 10.2478/v10026-009-0018-x.
11. Banach, M., Wzorek, Z. & Gorazda, K. (2009). Production of medium bulk density sodium tripolyphosphate by chemical method. *Przem. Chem.* 88(4), 370–374, (in Polish).
12. Banach, M., Kowalski, Z., Wzorek, Z. & Gorazda, K. (2009). High bulk density sodium tripolyphosphate produced by chemical method. *Przem. Chem.* 88(11), 1236–1239, (in Polish).
13. Polish Committee of Standardization. (1993). Polish Standard: Methods of phosphoric salt examination: Determination of water content, gravimetric method. PN-93/C-84300/22, (in Polish).
14. Polish Committee of Standardization. (1993). Polish Standard: Methods of phosphoric salt examination: Size analysis with the use of mechanical method. PN-93/C-84300/27, (in Polish).
15. Polish Committee of Standardization. (1980). Polish Standard: Bulk density determination. PN-80/C-04532, (in Polish).
16. Procter & Gamble. Manufacturing Standards-European Operations (1998). Raw material specification. Granular sodium Tripoliphosphate, high bulk density. 10072234.