



ARCHIVES
of
FOUNDRY ENGINEERING

ISSN (2299-2944)
Volume 18
Issue 1/2018

9 – 14

DOI: 10.24425/118803

2/1



Published quarterly as the organ of the Foundry Commission of the Polish Academy of Sciences

Determination of the Technological Parameters Process for Continuously Cast Brass Ingot

A.W. Bydalek ^{a, *}, P. Kwaśniewski ^b, P. Schlafka ^a, W. Wolczyński ^c, K. Najman ^d

^a University of Zielona Góra, Faculty of Mechanical Engineering, Podgórna 50, Zielona Góra, Poland

^b AGH University of Science and Technology, Al. Mickiewicza 30, Kraków, Poland

^c Institute of Metallurgy and Materials PAN, Reymonta 25, Kraków, Poland

^d BOLMET S.A., Wiechlice, Poland

* Corresponding author. E-mail address: adam_bk@poczta.onet.pl

Received 31.08.2017; accepted in revised form 02.02.2018

Abstract

This article discusses issues related to continuous casting of brass. The tested material was CuZn39Pb2 brass with the use of continuous casting and different parameters of the process. The position consists of a melting furnace with a graphite refining pot of about 4000 cm³ chuting capacity, a graphite crystallizer of 9,5 mm nominal diameter, a primary and secondary cooling system and an extracting system as well. The analysis was carried out in terms of technological parameters of the process and type of charge. Highlighted: feedrate ingot, number of stops, and technological temperatures. The surface quality of the obtained ingots and the structure were analyzed. The most favorable conditions were indicated and technological recommendations indicated. They have been distinguished for ingots for plasticity and other technologies. Favorable casting conditions are low feed and low temperature. Due to the presence of impurities coming from the charge it is disadvantageous to have Ni greater than 0.053% by mass, and Fe more than 0.075% by mass. It is recommended to maintain a high zinc content in the melt which is associated with non-overheating of the metal during casting and earlier melting.

Keywords: Brass, Continuous casting, Recycling

1. Introduction

The continuous casting method is commonly used in the manufacture of brass [1-4]. Determination of process parameters refers to the formation of a liquid and solid phase separation layer [5 - 7]. The use of waste materials results in distortion of this layer and does not allow the use of known models [8-12] Especially when raw materials for its production materials are of quite different composition [13-15]. Therefore, it is necessary to

carry out research on the optimization of process parameters in relation to the recyclable materials used.

2. Own Research

The tested material was CuZn39Pb2 (according to European Standard CW612N) brass with the use of continuous casting and different parameters of the process. Whilst the research the influence of the amount of spent cooling liquid in primary

circulation, times of granulation stops and casting quality feed were tested. Chemical composition of CuZn39Pb2 brass is given in table 1.

Table 1.

Chemical composition of the test alloy, [% mass]

Cu	Pb	Al	Fe	Ni	Sn	other	Zn
59÷60	1.6÷2.5	≤0.05	≤0.3	≤0.3	≤0.3	≤0.2	rest

The feedstock for the casting process was scrap-metal. The feedstock underwent preliminary selection with the use of mobile spectrometers. The furnace feedstock is presented in fig. 1.

Size of the feedstock corresponded 8000g of complete CuZn39Pb2 alloy containing 2% zinc surplus above the demanded limit. In table 2 the proportions are given. The continuous casting process was held in laboratory conditions at an authorial research position destined to test processes of such kind. The position consists of a melting furnace with a graphite refining pot of about 4000 cm³ chuting capacity, a graphite crystallizer of 9,5 mm nominal diameter, a primary and secondary cooling system and an extracting system as well.

Table 2.

Proportions of used materials, [g]

Cu	Pb	Al	Fe	Ni	Sn	other	Zn
Species to obtain (CuZn39Pb2)							
4760	164	4	24	24	24	16	2984
Batch (CuZn40Pb2)							
457	24	0	2	2	2	2	298
Batch (CuZn39Pb2)							
4074	140	3	21	21	21	14	2554
Batch (other)							
229	-	-	-	-	-	-	192

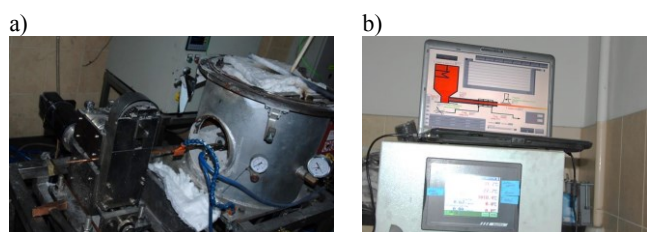


Fig. 2. Research workstation where: a) general view of continuous casting workstation, b) a set monitoring continuous casting process parameters

General view of the workstation and the monitoring and controlling system is presented in fig. 2. Continuous monitoring and controlling system (pict.2b) of specific work parameters allowed to set: material feed, the length of stop to crystallize, water spend in primary cooling.

Below in table 3 continuous casting parameters of CuZn39Pb2 alloy for cast no 1. Below in table 4 parameters of continuous casting for 2÷12 pressurized castings are juxtaposed.

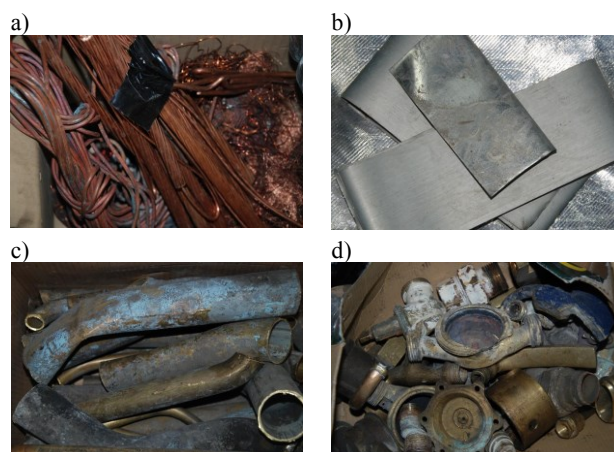


Fig. 1. Batch assortment, where: a) copper scrap, b) zinc scrap, c) CuZn40Pb2 scrap, d) CuZn39Pb2 scrap

Table 3.

Casting parameters – CuZn39Pb2 alloy - I

The feed rate	Stoppage	The amount of water	T metals	T water	T cast
[mm]	[s]	[l/min]		[°C]	
2	5	0.7	1045	21	85

Table 4.

Correlation of CuZn39Pb2 alloy continuous casting parameters

No	The feed rate	Stop-age	The amount of water	Temperature °C		
				Metals	Water	Cast
1	2	5	0.7	1045	21	85
2	5	5	0.7	1050	21	110
3	10	5	0.7	1050	21	150
4	10	3	0.7	1050	21	155
5	10	1	1.7	1055	21	230
6	5	1	3.3	1045	21	240
7	5	1	6.6	1085	21	260
8	10	3	1.7	1050	21	230
9	10	5	0.7	1050	21	240
10	8	2	0.7	1035	21	235
11	5	2	0.7	1035	21	230
12	7	3	0.7	1060	21	240

On the basis of consecutive research the assessment of obtained continuous castings was done:

- the visual assessment of all the obtained castings,
- the assessment of surface roughness,
- the analysis of chemical composition,
- the assessment of the castings structure quality.

Below in fig. 4 juxtaposition of all the obtained castings is presented. Below in table 5 the results of roughness measurements for particular castings are juxtaposed.

The research of chemical composition was held with OXFORD instruments spectrometer. Foundry-Master Xpert, which was equipped with copper and zinc alloys analysis patterns. Below in fig. 6 a spectrometer and samples subjected to chemical composition analysis are presented.



Fig. 4. CuZn39Pb2 alloy continuous castings where the order: bottom – casting no 1. top – casting no 12 is preserved

The surface roughness assessment of samples included the research held by the use of HommelWave roughness meter. The measurement was done by the use of a measuring head type T1E. The metrological range was 80µm, metrological length was 4.80mm, Lc 0.250mm. The exemplary results of roughness measurement is presented in fig. 5.

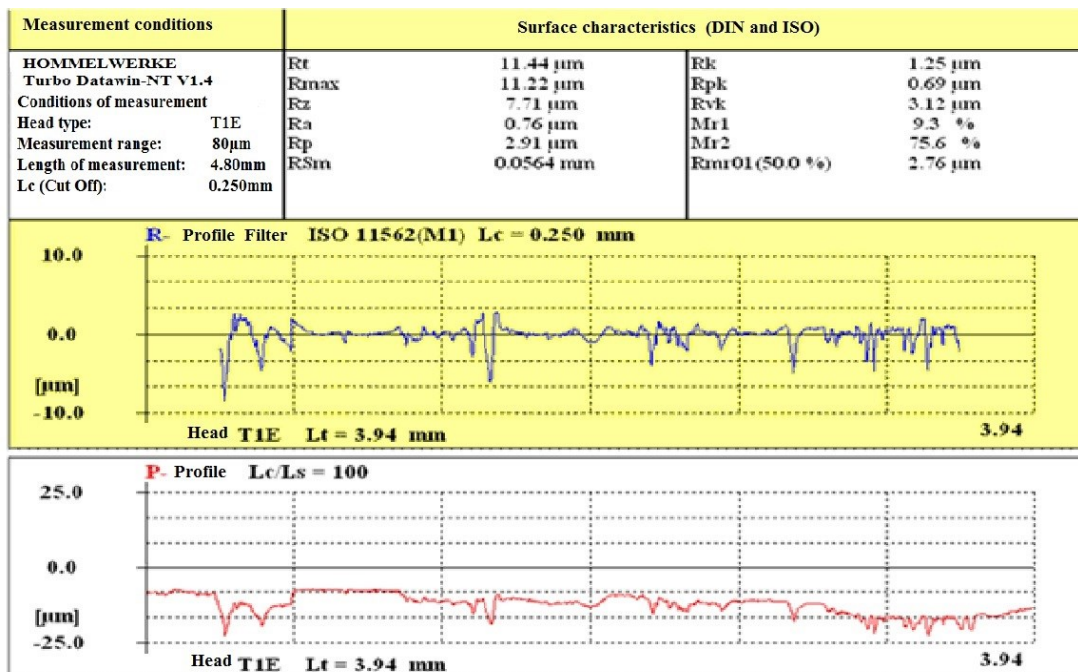


Fig. 5. The result of casting 1 from CuZn39Pb2 alloy surface roughness research

Table 5.

The results of roughness measurement for CuZn39Pb2 alloy

No	Rt	Rmax	Rz	Ra	Rp	RSm	Rk	Rpk	Rvk	Mr1	Mr2	Rmr01(50%)
	μm	μm	μm	μm	μm	mm	μm	μm	μm	%	%	μm
1	11.44	11.22	7.71	0.76	2.91	0.0564	1.25	0.69	3.12	9.3	75.6	2.76
2	15.82	15.82	7.75	0.70	4.72	0.0434	0.95	1.62	3.33	12.6	78.9	4.69
3	6.73	5.82	5.32	0.69	2.90	0.0456	1.65	0.66	1.97	8.1	78.0	2.75
4	16.64	15.88	12.23	1.76	7.74	0.0606	4.66	2.16	4.26	7.7	81.7	7.51
5	27.03	27.03	15.69	2.08	12.44	0.0901	4.55	4.66	6.08	11.7	78.5	12.47
6	20.63	20.63	11.16	1.47	11.13	0.0849	4.97	2.34	3.42	9.0	86.1	11.13
7	29.79	29.79	17.02	2.17	15.97	0.0718	4.62	4.24	7.87	11.9	80.3	15.84
8	14.35	14.35	7.94	1.00	6.76	0.0637	1.99	2.56	3.06	7.8	73.4	6.64
9	22.81	22.64	12.75	2.01	13.52	0.0681	5.38	4.99	5.24	8.9	81.8	13.60
10	14.27	13.24	10.10	1.54	6.67	0.0727	4.31	2.05	3.41	11.4	81.9	6.71
11	5.55	5.55	3.06	0.43	2.97	0.0544	0.93	0.71	1.62	14.7	77.9	2.93
12	16.20	16.20	8.28	1.26	6.87	0.0575	1.97	2.39	3.89	16.1	71.7	6.80

Table 6.

Analysis of the chemical composition of individual samples. (All less 0.0002% mass). [% mass]

No	Cu	Zn	Pb	Sn	Fe	Ni	other
1	61.7	36.0	1.7	0.18	0.17	0.05	0.04
2	61.5	36.2	1.7	0.18	0.17	0.05	0.05
3	61.8	36.0	1.6	0.17	0.17	0.05	0.05
4	60.8	37.0	1.6	0.17	0.17	0.05	0.05
5	62.4	35.4	1.6	0.16	0.17	0.05	0.04
6	62.5	35.3	1.6	0.17	0.17	0.05	0.04
7	62.6	35.2	1.6	0.17	0.18	0.05	0.04
8	62.5	35.3	1.6	0.17	0.18	0.05	0.05
9	63.2	34.6	1.6	0.17	0.18	0.05	0.05
10	62.2	35.6	1.6	0.17	0.17	0.05	0.05
11	63.100	34.730	1.691	0.182	0.181	0.054	0.062
12	63.290	34.590	1.641	0.182	0.182	0.054	0.060

The quality assessment of continuous castings produced from CuZn39Pb2 alloy was accomplished also on the basis of structure. Below in fig. 7 structure of continuous casting nr 1 is pictured. This sample is treated as a reference sample. Structure analysis was performed in cross section and longitudinal direction.

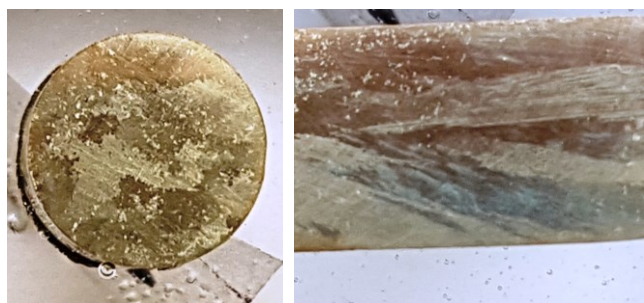


Fig. 7. Structure of cast No. 1 from CuZn39Pb2 alloy (x2.5)

The objective of these studies was to evaluate the effects of the influence of technological parameters on the formation of the structure of the ingot mainly for its later use in plastic forming processes.

Below in fig. 8 chosen pictures of castings no 6 and 7 produced at the constant feed 5 are presented. In fig. 9 photos of castings produced at feed rate 9 are shown. All the parameters of the continuous casting process are specified in table 4.

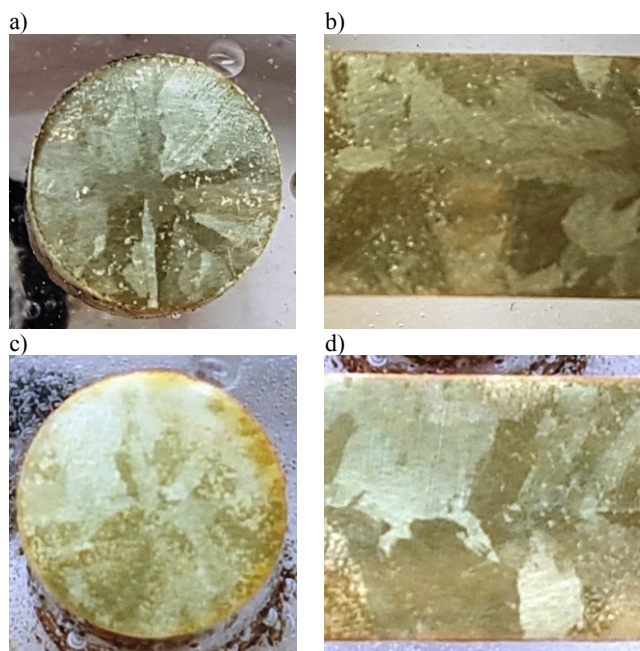


Fig. 8. Structure of CuZn39Pb2 castings where: a). b) cast 6. c). d) cast 7 (x 2.5)



Fig. 9. Structure of CuZn39Pb2 castings - cast 8 (x1.5)

3. Summary

It was observed that the obtained castings can be divided: (A) in terms of surface quality. B) in terms of grain size in the transverse structure. They differ also in orientation. The castings marked 1.2.3.6.7.8 and 11 had a smooth surface and were free from cracks. Castings 5.9.10 and 12 had visible surface defects. The grain size (0.5-2 mm) - casts 3.5.7 and 9; large grain (more than 2 mm) - castings 1.2.4.6.8 and 11. Orientations: axial. even surfaces - castings 1.2.3.4.5.6.8.11 and 12. not axial and uneven surface - casts 7. 9 and 10.

In conclusion, it was found that the most favorable casting conditions is low temperature at the inlet of the mold and low feed speed of the feeders to the crystallizer. The tests showed that samples designated as: 1.2.4 and 11 are suitable for further plastic processing. They were obtained mostly for the conditions of: low deputies of the casting and low water cooling rate. Interesting, however, were the trials 6 and 8 in which a uniform grain structure was obtained with different cooling conditions - higher feed rate and higher water expenditure in the crystallizer. In general, increasing the temperature of overheating liquid metal while increasing the feed rate and flow of water led to the formation of surface defects in the ingots.

It was considered that the conditions generated in trials 3 and 7 still allow the use of ingots for applications other than plastic working. The conditions planned in samples 5.9.10 and 12 were considered unfavorable for further processing and as final products.

Due to the presence of impurities in the bearing charge, the nickel content is greater than 0.053% by weight and iron over 0.075% by weight. The presence of increased amounts of lead and tin is preferred. The test results also indicate that it is advantageous to maintain a high content of zinc in the alloy - at the upper limit according to the standard.

Acknowledgements

This project was supported by the National Center for Research and Development under Grant No. PBS3/A5/52/2015 (PBS3/244 864/PP/MMB).

Reference

- [1] Kozana, J., Rządkosz, St. & Piękoś, M. (2010). Influence of the selected alloy additions on limiting the phase gamma formation in Cu-Zn alloys. *Archives of Foundry Engineering*. 10(1), 221-225. ISSN (1897-3310).
- [2] Anakhov, S.V. & Fominykh, S.I. (1997). Effect of the cooling rate after remelting on the structure of antifriction brass. *Metal Science and Heat Treatment*. 39(6), 240-243. ISSN (0026-0673).
- [3] Kondracki, M. & Szajnar, J. (2007). Possibilities for leaded brass replacement with multi-component brass. *Archives of Foundry Engineering*. 7(2), 57-64. ISSN (1897-3310).
- [4] Ziółkowski, E. (2006). Theoretical basis of the parameters balance algorithm of the charge combined the charge materials with imprecise chemical constitution (in Polish). *Archives of Foundry*. 19(6), 443-448. ISSN 1642-5308.
- [5] Hunt, J.D. (1984). SteadyState Columnar and Equiaxed Growth of Dendrites and Eutectics. *Materials Science and Engineering*. 65, 75-83. ISSN (2161-6213).
- [6] Weigand, B. & Lipnicki, Z. (2016). Development of the contact layer and its role in the phase change process. *International Journal of Heat and Mass Transfer*. 93, 1082-1088. ISSN (0017-9310).
- [7] Vusanović, I. & Voller, V.R. (2014). Understanding Channel Segregates in Numerical Models of Alloy Solidification: A Case of Converge First and Ask Questions Later. *Materials Science Forum*. 790/791, 73-78.
- [8] Szajnar, J. (2004). The Columnar Crystals Shape and Castings Structure Cast in Magnetic Field. *Journal of Materials Processing Technology*. 157/158, 761-764.
- [9] Gandin, Ch.A., Mosbah, S., Volkman, Th. & Herlach, D.M. (2008). Experimental and Numerical Modeling of Equiaxed Solidification in Metallic Alloys. *Acta Materialia*. 56, 3023-3035.
- [10] McFadden, S., Browne, D.J. & Gandin, Ch.A. (2009). A Comparison of CET Prediction Methods using Simulation of the Growing Columnar Front. *Metallurgical Transactions*. 40A, 662-672.
- [11] Konozy, L., Ishmurzin, A., Grasser, M., Wu, M.H., Ludwig, A., Tanzer, R. & Schutzenhofer, W. (2010). Columnar to Equiaxed Transition during Ingot Casting using Ternary Alloy Composition. *Materials Science Forum*. 649, 349-354.
- [12] Wołczyński, W. (2016). Large Steel Ingots: Microstructure Mathematical Modeling. Entry in: *The Encyclopedia of Iron, Steel, and Their Alloys*. Ed. CRC Press. Taylor & Francis Group. Boca Raton. London. New York. EdsRafaelColas. GeorgeE. Totten. v.III. Heat Treatment: Special - Molten. p. 1910-1924.
- [13] Bydałek, A.W. Biernat, S., Schlafka, P., Holtzer, M., Wołczyński, W. & Bydałek, F. (2016). The Influence of the

- Chemical Composition of Selected Waste Materials from the Production of Copper on the Final Environmental Assessment. *Archives of Metallurgy and Materials*. 61(4), 2135-2140. ISSN (1733-3490).
- [14] Schlafka, P., Bydałek, A.W., Holtzer, M., Wołczyński, W. (2016). The Influence of the Ionic reactions On The Refining Secondary Raw Materials. *Metalurgija*. 55(4), 609-612. ISSN (0543-5846).
- [15] Rzadkosz, S., Zych, J., Garbacz-Klempka, A., Kranc, M., Kozana, J., Piękoś, M., Kolczyk, J. & Jamrozowicz, Ł. (2015). Copper alloys in investment casting technology. *Metalurgija*. 54(1), 293-296. ISSN (0543-5846)