

Synthesis and characterization of the aluminium phosphates modified with ammonium, calcium and molybdenum by hydrothermal method

Kinga Łuczka^{1*}, Barbara Grzmil¹, Bogumił Kic¹, Krzysztof Kowalczyk²

¹West Pomeranian University of Technology, Szczecin, Institute of Chemical and Environment Engineering, ul. Pułaskiego 10, 70-322 Szczecin, Poland

²West Pomeranian University of Technology, Szczecin, Polymer Institute, ul. Pułaskiego 10, 70-322 Szczecin, Poland

*Corresponding author: e-mail: kluczka@zut.edu.pl

Synthesis and characterization of the aluminum phosphates modified with ammonium, calcium and molybdenum were conducted. The influence of process parameters (reactive pressure and molar ratios) in the reaction mixture were studied. The contents of the individual components in the products were in the range of: 10.97–17.31 wt% Al, 2.65–13.32 wt% Ca, 0.70–3.11 wt% Mo, 4.36–8.38 wt% NH₃, and 35.12–50.54 wt% P₂O₅. The materials obtained in the experiments were characterized by various physicochemical parameters. The absorption oil number was in the range from 67 to 89 of oil/100 g of product, the surface area was within the range of 4–76 m²/g, whereas the average particle size of products reached 282–370 nm. The Tafel tests revealed comparable anticorrosive properties of aluminum phosphates modified with ammonium, calcium, molybdenum in comparison with commercial phosphate.

Keywords: hydrothermal method, anticorrosive pigments, modified aluminum phosphates.

INTRODUCTION

The aim of pigment mixture development is to enhance the anticorrosion efficiency of non-toxic pigments and shift their efficiency closer to the old, toxic (but very efficient) chromate and lead pigments. Such development is necessary to meet tough environmental norms that are steadily becoming stricter^{1, 2, 3}. The latest EU legislation on organic coatings took effect in 2010 and was aimed at reducing volatile organic compounds in paint systems².

Literature reports seem to suggest that the anticorrosion properties of pigments are affected not only by their chemical composition, but also by other factors, including their particle size, oil number, specific surface area and water solubility^{4, 5, 6}. Changes in the structure and chemical composition of various materials can be obtained by using different process parameters in their preparation (e.g. substrate molar ratio, the pH of a reaction mixture, reaction time, pressure, temperature) or with microwave radiation^{7, 8, 9}. Microwave is an energy source which has found its applications in many scientific research areas. Microwave radiation has shown its capability for fast preparation of size controlled metallic nanostructures on different substrates^{10, 11}. Microwave technique attracts more interest because it can generate heat internally inside the sample so the heat can be transferred homogeneously and rapidly. The microwave technique requires far less energy than resistive heating and is less polluting than gas or oil fired heaters and is therefore more environmentally friendly¹². Moreover, rapid initial heating of the microwave can enhance the kinetics of the reaction due to the formation of high temperature throughout the sample¹³.

The aim of the presented work was to elaborate the preparation process of aluminum phosphates modified with ammonium, calcium and molybdenum by hydrothermal method. Their steel corrosion inhibition efficiency was investigated by means of the potentiodynamic polarization technique. The influence of preparation process parameters on several physicochemical properties of the products such as chemical composition, oil absorption and specific surface area was determined. Based on the


Tafel test results the corrosion potential, corrosion current density and corrosion rate for steel immersed in a phosphate extract in an aqueous NaCl solution were calculated and presented.

EXPERIMENTAL


Procedure

Studies on the synthesis of aluminum phosphates modified with ammonium, calcium and molybdenum were performed on the basis of the experimental planning and analysis according to a three-level 3^(k-p) fractional factorial designs with 9 experiments using the hydrothermal method. The process independent variables were: x₁ – the pressure (1.1 ± 1 MPa), x₂ – the molar ratio of Ca²⁺ to PO₄³⁻ in the substrates 0.2 ± 0.13 : 1 corresponding to the molar ratios of Al³⁺ to Ca²⁺ to Mo⁶⁺ to PO₄³⁻ in the reaction mixture (0.67 : 0.2 ± 0.13 : 0.2 ± 0.13 : 1).

The aim of the study was to obtain products with the molar ratio of (NH₄)₃Al₂(PO₄)₃ to CaMoO₄ varying in the range of 1 : (0.6 ± 0.4). Therefore, to obtain a product with the molar ratio of (NH₄)₃Al₂(PO₄)₃ to CaMoO₄ equalling 1 : 1, the reactor had to be feed with substrates in the molar ratios corresponding to those in the following reactions:



During the experiments, it turned out that a competitive reaction involving hydroxylapatite precipitation was also proceeding:



Multiple dependent variables defining the physicochemical properties of prepared products were as follows: the content of Al³⁺ (y₁), Ca²⁺ (y₂), Mo⁶⁺ (y₃), NH₃ (y₄), P₂O₅ (y₅), oil absorption number (y₆), specific surface area S_{BET} (y₇), and average particle size (y₈).

Table 1. Three-level $3^{(k-p)}$ fractional factorial design and physicochemical properties of aluminum phosphates modified with ammonium, calcium and molybdenum obtained hydrothermal conditions

Phosphate acronym	Independent variables		Dependent variables							
	x_1	x_2	y_1	y_2	y_3	y_4	y_5	y_6	y_7	y_8
	[MPa]		[wt%]					[g/100g]	[m ² /g]	[nm]
AACMPH1	0.1	0.07	17.31	3.50	1.07	6.41	43.5	73	76	346
AACMPH2	1.1	0.07	17.31	2.98	0.70	6.51	44.2	75	54	297
AACMPH3	2.1	0.07	15.25	2.65	0.79	8.38	50.54	67	34	343
AACMPH4	0.1	0.2	14.32	8.47	1.21	5.65	40.51	74	55	320
AACMPH5	1.1	0.2	13.49	9.45	1.58	5.78	40.68	75	57	311
AACMPH6	2.1	0.2	13.65	8.95	2.28	5.74	41.16	68	52	370
AACMPH7	0.1	0.33	10.97	13.32	3.11	4.36	35.12	81	51	282
AACMPH8	1.1	0.33	11.57	13.11	3.00	4.98	40.55	89	69	305
AACMPH9	2.1	0.33	11.08	13.09	2.55	5.71	42.44	74	41	310

The aim of the performed experiments according to the established plan was to determine the fractional design at 3 levels of the important factors affecting the investigated parameters and to find the right input values enabling to obtain a product with the expected properties¹⁴. A factorial plan and the results obtained from experiments are summarized in Table 1. Basing on the beginning studies it was taken that the constant conditions process were equal to: pH of the reaction was 6 and time reaction was allowed 20 minutes. The total salt concentration amounted to 40 wt%.

Sample preparation

Reagent grade substrates: $(\text{NH}_4)_2\text{HPO}_4$, CaCO_3 , $(\text{NH}_4)_6\text{Mo}_7\text{O}_{24} \cdot 4\text{H}_2\text{O}$, an aqueous ammonia (25 wt% of NH_3) and amorphous $\text{Al}(\text{OH})_3$ were used. Aluminum hydroxide was precipitated in the reaction of aluminum nitrate with potassium hydroxide at $\text{pH} = 7.5$ ¹⁵. The molar ratios of Al^{3+} : Ca^{2+} : Mo^{6+} : PO_4^{3-} in the reaction mixture amounted to 0.67 : (0.2 ± 0.13) : (0.2 ± 0.13) : 1. The constant process parameters were: pH of the reaction equal to 6 and the total salt concentration amounted to 40 wt%. A suspension of amorphous aluminum hydroxide and calcium carbonate was dosed into an ammonium molybdate and ammonium phosphates solution at a constant stirring velocity. The suspension of reactants with an appropriate pH was prepared in a glass reactor and the mixture was transferred into the microwave reactor and treated at a pressure of 1.1 ± 1 MPa (microwave reactor type ERTEC Magnum, output 750 W at a frequency of 2.45 GHz, Ertec Poland), for 20 min. The obtained precipitate was separated from the mother liquor using a vacuum filter, followed by triple washing with distilled water (the weight ratio of the liquid to the solid phase was 3 : 1). Finally, the obtained product was dried for 3 h at 70°C.

Anticorrosive properties of the modified aluminum phosphate for cold rolled steel were investigated by means of the potentiodynamic polarization technique. For comparison purposes, two commercial anticorrosive pigments, i.e. zinc phosphate and zinc aluminum phosphate (FC-M2, FAC) were tested.

Sample characterization

The content of aluminum, calcium and molybdenum in the products was determined by ICP-AES analysis (Optima 5300 DV, Perkin Elmer). The phosphates and ammonium contents were determined using a spectrophotometric method¹⁵ and ion selective electrode Orion

11–35 type, respectively¹⁶. The phase composition of the products was studied with X-ray diffraction analysis (CuK_α radiation, X'Pert PRO Philips diffractometer). The oil absorption (grams of oil required to form a homogeneous paste with 100 g of the tested dry pigment) was determined according to PN-EN ISO 787-5 standard¹⁷. The measurements of Brunauer-Emmett-Teller surface area (S_{BET}) of the materials were performed using Micrometrics Quadrasorb SI Quantachrome Instrument. N_2 adsorption/desorption measurements were carried out at liquid N_2 temperature. The average particle size of the materials was determined using a laser scanning microscope (VK-9700, Keyence, USA). The phosphate morphology was examined with a scanning electron microscope SU-70 (Hitachi, Japan). The chemical composition of the phosphates was determined using a scanning electron microscope with a cold field emission (HITACHI SU8020, resolving power 1.3 nm), coupled with the energy dispersive X-ray analyzer (EDX – Thermo Scientific).

Tafel experiments in the range from –250 to 500 mV in relation to OCP (scan rate 0.25 mV s⁻¹) for an uncoated steel substrate (SEA 1008/1010, Q-Panels, Q-Lab Europe, England) were performed using DC105 software and FAS2 femtostat (Gamry, USA). As a result, corrosion potential (E_{corr}), corrosion current density (i_{corr}) and corrosion rate (P) were determined using Echem Analyst software (Gamry). Steel polarization was carried out using electrolytes prepared by shaking a phosphate filler (2.5 g) with 100 g of 3.5 wt% NaCl aqueous solution for 2 h (i.e. twice for 1 h with a 22 h interval). Then, the suspension was centrifuged (4000 rpm, 10 min) and an aqueous extract was carefully decanted. The Tafel tests were made after 20 h of a glass cell filling with an electrolyte (aqueous NaCl solution or phosphate extract). The corrosion inhibition efficiency (η , %) of phosphate extracts was calculated according to the following equation:

$$\eta = \left[\frac{i_0 - i}{i_0} \right] \times 100 \quad (1)$$


where i_0 and i are corrosion current densities registered for steel substrate immersed in a 3.5 wt% NaCl aqueous solution and the aqueous extract of phosphate filler, respectively.

RESULTS AND DISCUSSION

Figure 1 and Table 2 shows the phase composition of the precipitated products, which was determined

Table 2. The phase composition and molar ratio of the components in obtained products

Phosphate acronym	Independent variables		Phase composition (peak intensity)			Molar ratio
	x_1 [MPa]	x_2	$(\text{NH}_4)_3\text{Al}_2(\text{PO}_4)_3$	$\text{Ca}_5(\text{PO}_4)_3(\text{OH})$	CaMoO_4	$\text{Al}^{3+}:\text{Ca}^{2+}:\text{Mo}^{6+}:\text{NH}_4^+:\text{PO}_4^{3-}$
AACMPH1	0.1	0.07	***	**	–	1.0 : 0.1 : 0.02 : 0.62 : 1
AACMPH2	1.1		***	**	–	1.0 : 0.1 : 0.01 : 0.62 : 1
AACMPH3	2.1		***	**	–	0.8 : 0.1 : 0.01 : 0.69 : 1
AACMPH4	0.1	0.2	**	**	**	0.9 : 0.4 : 0.02 : 0.58 : 1
AACMPH5	1.1		**	**	**	0.9 : 0.4 : 0.03 : 0.59 : 1
AACMPH6	2.1		**	**	**	0.9 : 0.4 : 0.04 : 0.58 : 1
AACMPH7	0.1	0.33	*	**	***	0.8 : 0.7 : 0.07 : 0.52 : 1
AACMPH8	1.1		*	**	***	0.8 : 0.6 : 0.05 : 0.51 : 1
AACMPH9	2.1		*	***	***	0.7 : 0.5 : 0.04 : 0.56 : 1

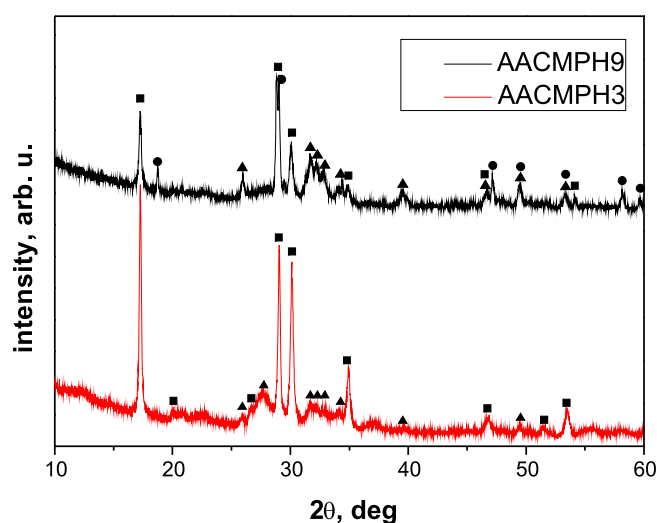**Figure 1.** X-ray diffraction patterns of products obtained (AACMPH3 and AACMPH9) [■] $(\text{NH}_4)_3\text{Al}_2(\text{PO}_4)_3$; [●] CaMoO_4 ; [▲] $\text{Ca}_5(\text{PO}_4)_3(\text{OH})$

using XRD analysis. $(\text{NH}_4)_3\text{Al}_2(\text{PO}_4)_3$, CaMoO_4 and $\text{Ca}_5(\text{PO}_4)_3(\text{OH})$, crystalline compounds, were identified. Their ratio varied depending on the composition of substrate mixture. For the lowest molar ratio of $\text{Al}^{3+}:\text{Ca}^{2+}$ in the initial mixture equalling 2 ($\text{Al}^{3+}:\text{Ca}^{2+}$ 0.67 : 0.33), the content of CaMoO_4 in the products was the highest. However, the higher was the molar ratio of reagents containing aluminum and calcium, the higher was the content of $(\text{NH}_4)_3\text{Al}_2(\text{PO}_4)_3$ in the precipitated solid phases.

The chemical composition of the obtained materials mainly depended on the substrate molar ration which determined the phase composition. Products with a higher molar ratio between $(\text{NH}_4)_3\text{Al}_2(\text{PO}_4)_3$ and CaMoO_4 contained more aluminum and ammonia and less calcium and molybdenum. Therefore, products in each group had similar chemical and phase compositions: I – AACMPH1-3, II – AACMPH4-6, III – AACMPH7-9. Similarly, products from different groups had different chemical and phase compositions (Tables 1 and 2). The precipitated products were in the range of: 10.97–17.31 wt% Al, 2.65–13.32 wt% Ca, 0.70–3.11 wt% Mo, 4.36–8.38 wt% NH_3 , and 35.12–50.54 wt% P_2O_5 (Table 1).

A statistical analysis, focused on determining process parameters that had a significant influence on the physicochemical properties of the obtained phosphates, was conducted to assess the effects of changes in input

values y_{1-8} for the extremum input values $x_{1,2}$. Pareto charts were drawn to illustrate the trends (Fig. 2). To confirm the assessment significance of obtained effects, Anova analysis was performed (Table 3).

The molar ratio of Ca^{2+} to PO_4^{3-} in substrates (x_2) was found to have a statistically significant effect on aluminum content (y_1) in the products. Bearing in mind that ($x_2(\text{L})$, effect–5.42) has a negative number (Table 3), it was fair to think that a lower values of x_2 would result in the increase of the dependent variable y_1 .

Therefore, aluminum phosphates modified with ammonium, calcium and molybdenum with a higher content of aluminum (the average content of 16.6 wt% Al) were to be precipitated from the reaction mixture with the $\text{Al}^{3+}:\text{Ca}^{2+}:\text{Mo}^{6+}:\text{PO}_4^{3-}$ molar ratio of 0.67 : 0.07 : 0.07 : 1.

The molar ratio of reagents (x_2) was found to have the highest statistic effect on calcium content (y_2) in the products. The positive effect ($x_2(\text{L})$, effect 10.13) of this influence seems to indicate the increase of y_2 values, starting from approximately 3 wt% Ca to about 13 wt% Ca along with the increase of x_2 from 0.07 : 1 to 0.33 : 1 (Table 3). The dependent variable y_3 , denoting molybdenum content in the obtained phosphates, also depended on the molar ratio of $\text{Ca}^{2+}:\text{PO}_4^{3-}$ in the reaction mixture. The statistical analysis demonstrated the positive sign of the effect ($x_2(\text{L})$, effect 2.03) which translated into the increase of molybdenum content in the products (from approximately 0.8 wt% to about 3 wt%) along with the increase of the independent variable (Table 3).

The content of ammonium groups (the dependent variable y_4) in the obtained products also depended on the $\text{Ca}^{2+}:\text{PO}_4^{3-}$ ratio in the reaction mixture ($x_2(\text{L})$, effect –2.08). It was found that the less calcium (and at the same time molybdenum) was introduced into the reaction mixture, the higher was the content of nitrogen in the products. It increased from approximately 5 wt% NH_3 to about 7 wt% NH_3 .

It was demonstrated that another dependent variable y_6 , i.e. the content of phosphates in the products was affected only by the molar ratio of the substrates. Following the analysis of effect assessment ($x_2(\text{L})$ –6.71), the highest content of phosphates in the obtained products was observed for the $\text{Ca}^{2+}:\text{PO}_4^{3-}$ molar ratio of 0.07 : 1 in the reaction mixture.

It was statistically demonstrated that the above discussed input variables correlated with the chemical composition of the products were not affected by the pressure of the process (0.1–2.1 MPa).

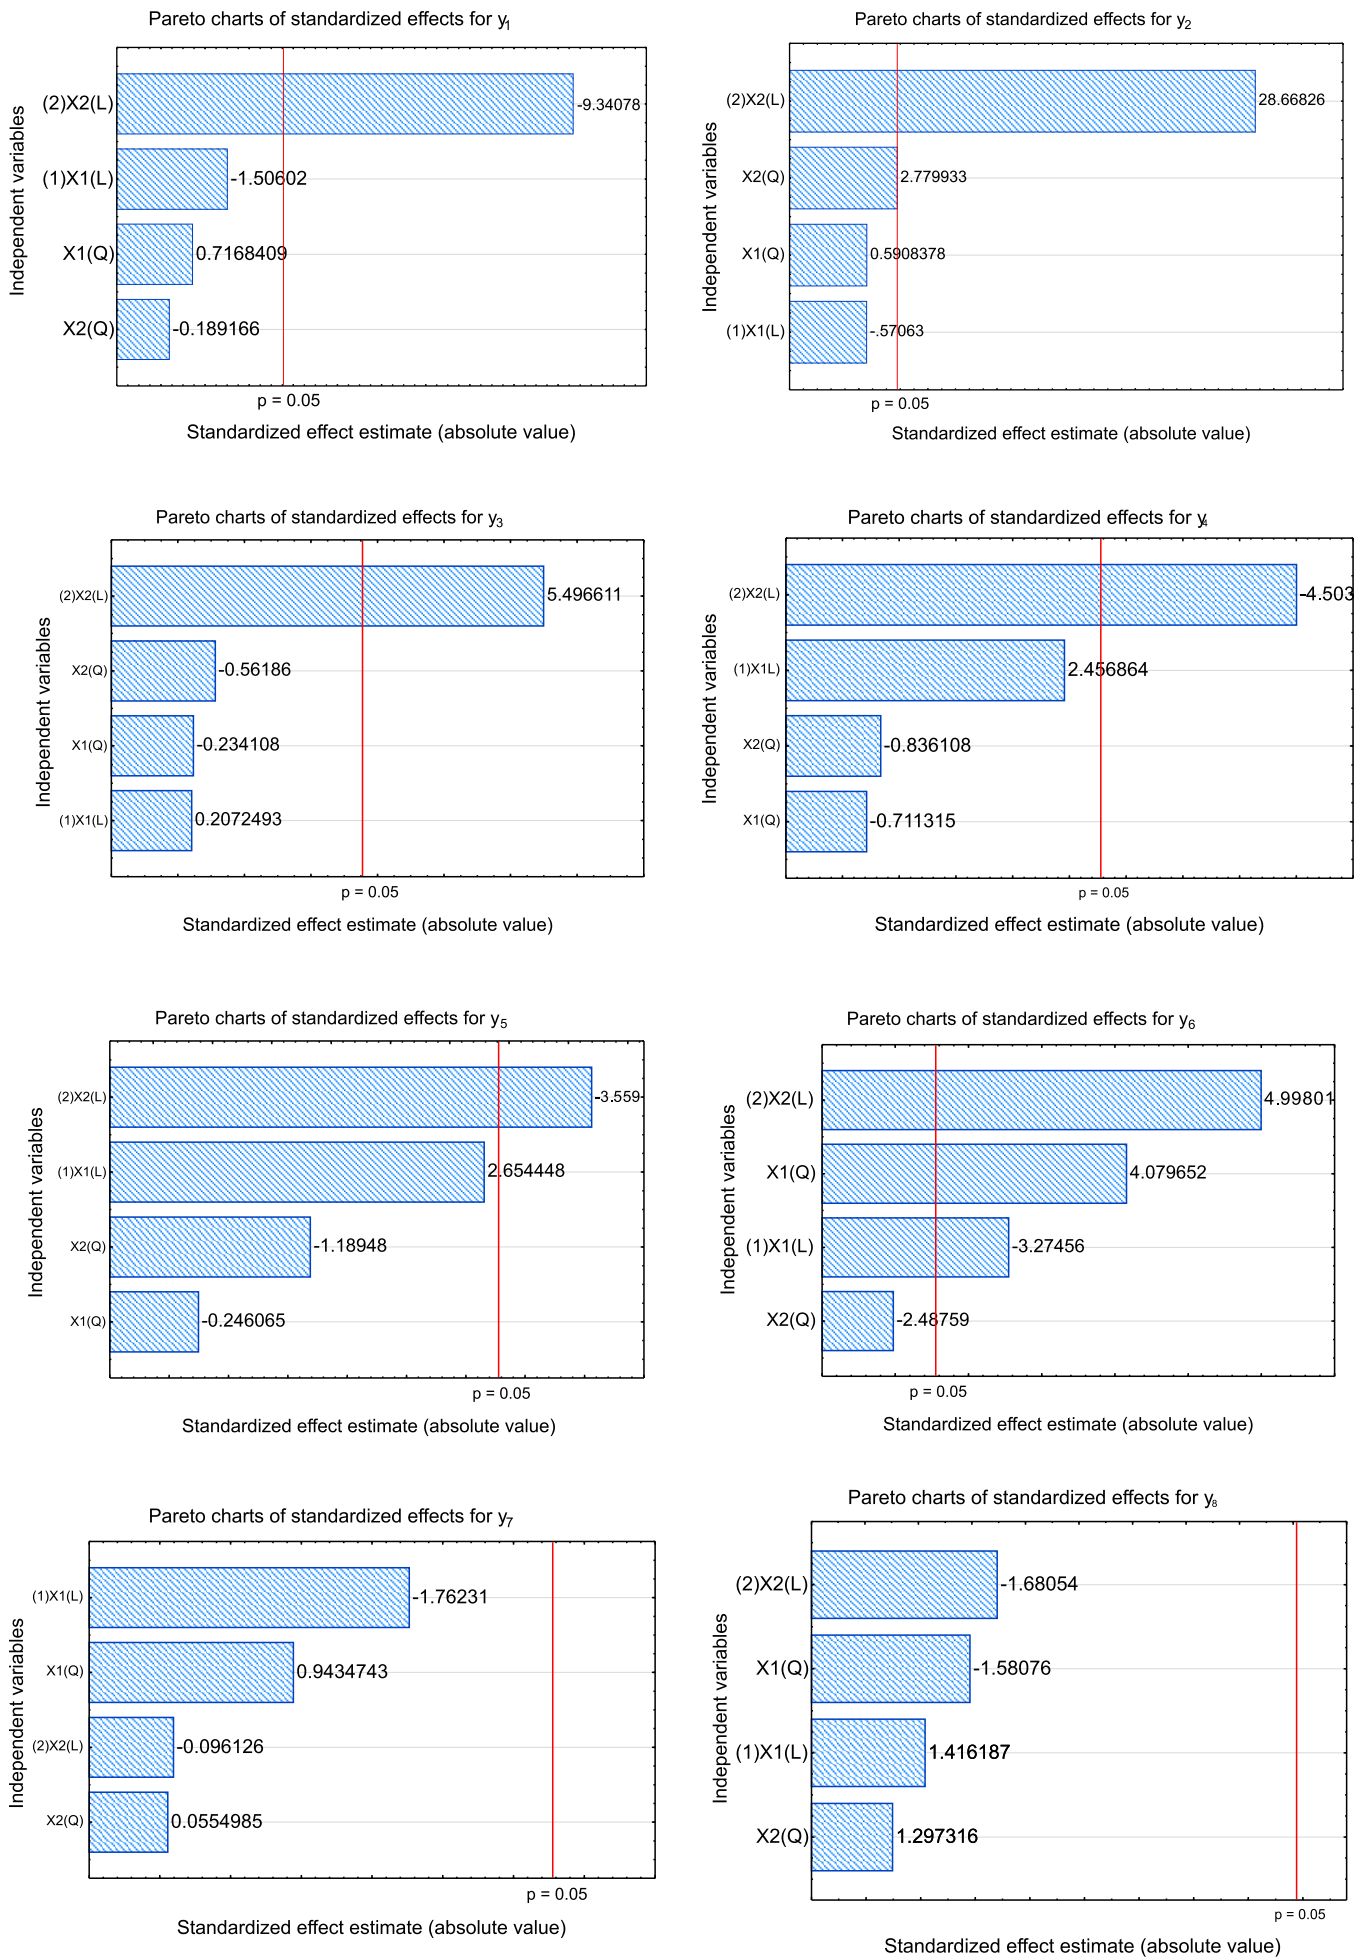


Figure 2. Pareto charts of standardized y_{1-8}

Table 3. ANOVA table analysis for dependent variables (y_1 – y_8)

Independent variables	Effect	Std. Error	t[4]	p	95% Confidence Interval for Difference	
					Lower Bound	Upper Bound
y_1						
Mean/constant	13.88333	0.236741	58.64356	0.000001	13.22603	14.54063
(1)X1(L)	-0.87333	0.579895	-1.50602	0.206526	-2.48338	0.73671
X1(Q)	0.36000	0.502203	0.71684	0.513101	-1.03434	1.75434
(2)X2(L)	-5.41667	0.579895	-9.34078	0.000731	-7.02671	-3.80662
X2(Q)	-0.09500	0.502203	-0.18917	0.859173	-1.48934	1.29934
y_2						
Mean/constant	8.39111	0.144279	58.15881	0.000001	7.99053	8.79169
(1)X1(L)	-0.20167	0.353411	-0.57063	0.598778	-1.18289	0.77956
X1(Q)	0.18083	0.306063	0.59084	0.586398	-0.66893	1.03060
(2)X2(L)	10.13167	0.353411	28.66826	0.000009	9.15044	11.11289
X2(Q)	0.85083	0.306063	2.77993	0.049822	0.00107	1.70060
y_3						
Mean/constant	1.810000	0.151021	11.98507	0.000278	1.39070	2.229302
(1)X1(L)	0.076667	0.369925	0.20725	0.845938	-0.95041	1.103743
X1(Q)	-0.075000	0.320364	-0.23411	0.826395	-0.96447	0.814474
(2)X2(L)	2.033333	0.369925	5.49661	0.005340	1.00626	3.060410
X2(Q)	-0.180000	0.320364	-0.56186	0.604202	-1.06947	0.709474
y_4						
Mean/constant	5.94667	0.188876	31.48453	0.000006	5.42226	6.471070
(1)X1(L)	1.13667	0.462649	2.45686	0.069927	-0.14785	2.421187
X1(Q)	-0.28500	0.400666	-0.71132	0.516171	-1.39743	0.827427
(2)X2(L)	-2.08333	0.462649	-4.50305	0.010797	-3.36785	-0.798813
X2(Q)	-0.33500	0.400666	-0.83611	0.450132	-1.44743	0.777427
y_5						
Mean/constant	42.07778	0.769502	54.68186	0.000001	39.9413	44.21426
(1)X1(L)	5.00333	1.884886	2.65445	0.056718	-0.2299	10.23662
X1(Q)	-0.40167	1.632359	-0.24607	0.817743	-4.9338	4.13049
(2)X2(L)	-6.71000	1.884886	-3.55990	0.023588	-11.9433	-1.47672
X2(Q)	-1.94167	1.632359	-1.18948	0.300029	-6.4738	2.59049
y_6						
Mean/constant	75.11111	0.789593	95.12639	0.000000	72.9189	77.30337
(1)X1(L)	-6.33333	1.934099	-3.27456	0.030657	-11.7033	-0.96341
X1(Q)	6.83333	1.674979	4.07965	0.015103	2.1828	11.48382
(2)X2(L)	9.66667	1.934099	4.99802	0.007501	4.2967	15.03659
X2(Q)	-4.16667	1.674979	-2.48759	0.067659	-8.8172	0.48382
y_7						
Mean/constant	54.3333	4.24700	12.79333	0.000215	42.5418	66.12490
(1)X1(L)	-18.3333	10.40299	-1.76231	0.152804	-47.2167	10.55000
X1(Q)	8.5000	9.00925	0.94347	0.398860	-16.5137	33.51370
(2)X2(L)	-1.0000	10.40299	-0.09613	0.928044	-29.8833	27.88333
X2(Q)	0.5000	9.00925	0.05550	0.958403	-24.5137	25.51370
y_8						
Mean/constant	320.4444	7.20682	44.46405	0.000002	300.4351	340.4538
(1)X1(L)	25.0000	17.65303	1.41619	0.229663	-24.0127	74.0127
X1(Q)	-24.1667	15.28798	-1.58076	0.189087	-66.6129	18.2796
(2)X2(L)	-29.6667	17.65303	-1.68054	0.168148	-78.6793	19.3460
X2(Q)	19.8333	15.28798	1.29732	0.264287	-22.6129	62.2796

The statistical analysis of the effect of independent variables (x_1 , x_2) on the dependent variables characterizing the morphology of materials demonstrated that the substrate molar ratio in the reaction mixture (x_2 (L) 9.67) and the pressure of the process (x_1 (L) -6.33) had a statistically significant influence on their oil number (y_6). The lower the pressure and the higher the Ca^{2+} :

PO_4^{3-} molar ratio, the higher oil number tended to be, characterizing the sorption properties of the products. Both of the input variables had no effect on the specific surface area and on the average particle size of the precipitated phosphates. Their specific surface area (y_7) and particle size (y_8) were in the range of 34–76 m^2/g and 280–370 nm, respectively.

The spatial graphs in Figure 2 show the effect of pressure and $\text{Ca}^{2+}:\text{PO}_4^{3-}$ ratio in the reaction mixture on the dependent variables y_{1-8} . The depicted areas can help to assess the influence of the above process parameters on the properties of precipitated phosphates. Based on that, a conclusion was drawn that only the substrate molar ratio affected the content of aluminum, calcium and molybdenum in the products, which is consistent with the results of the statistical analysis. The specific surface area was found to be slightly affected by the pressure

of the process, which in the statistical assessment of the effects was described to have a negligible effect.

The shape of the surface presented in Figure 3, depicting the effect of variables x_1 and x_2 on the oil number of the products, suggest the influence of both parameters with a maximum observed for the average pressure. The finding is consistent with the statistical analysis of ($x_2(\text{L})$ 9.67; $x_1(\text{L})$ -6.33; $x_1(\text{Q})$ 6.83) effects. However, the interpretation of the shape in terms of the effect of the independent variables on the content of nitrogen

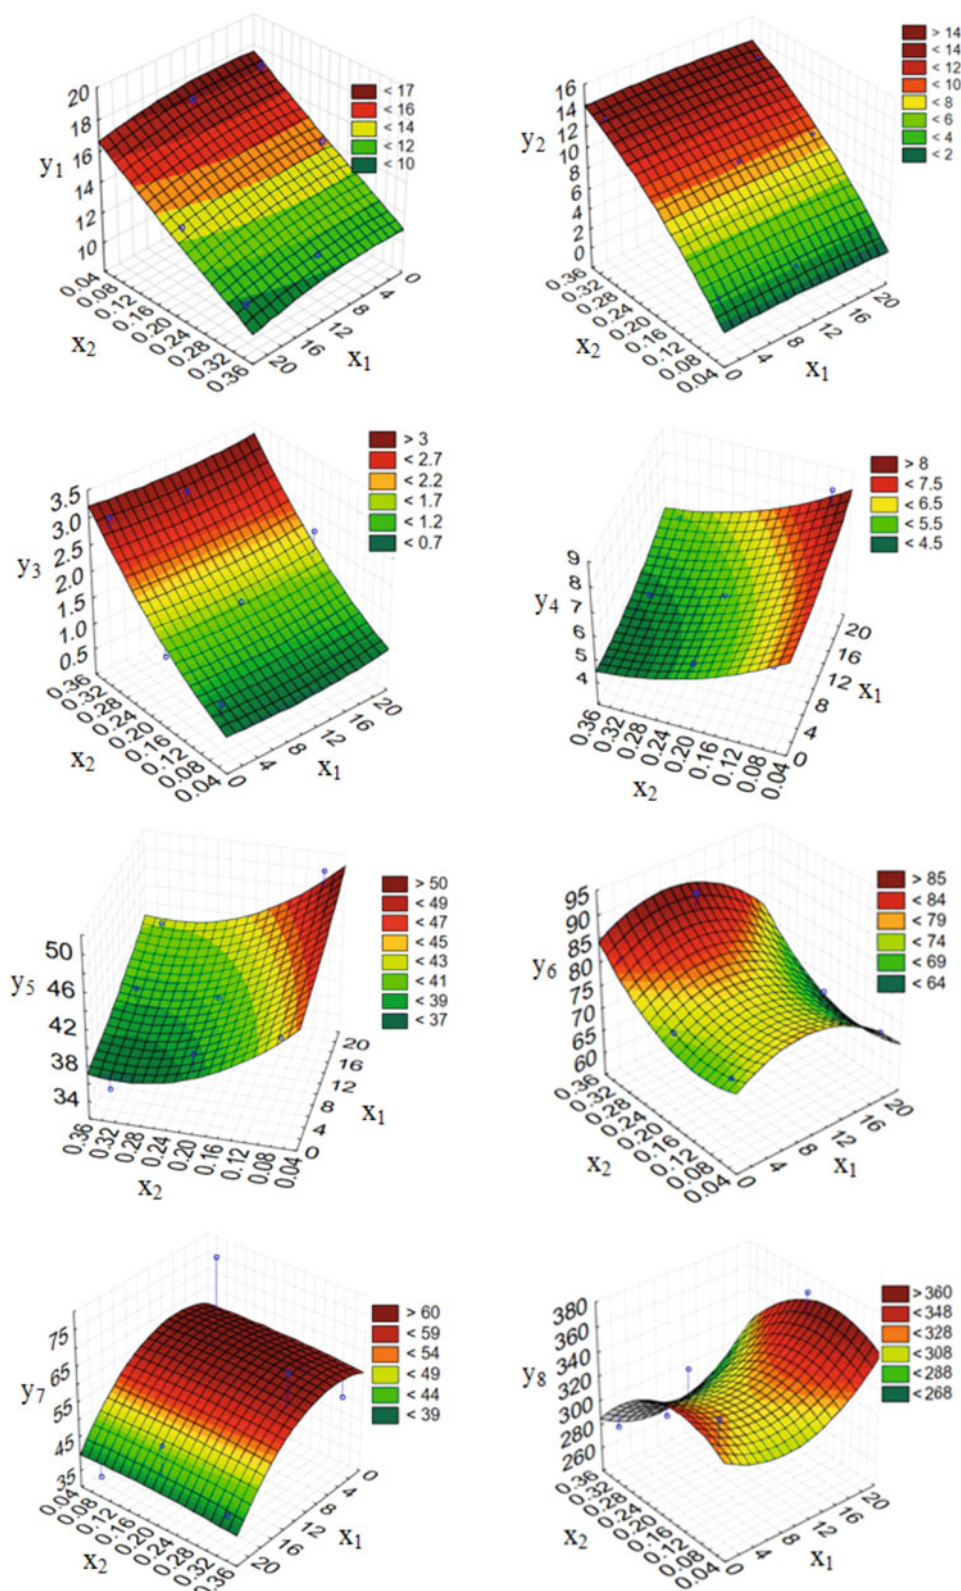


Figure 3. Response surface for dependent variables x_{1-2} to independent variables y_{1-8}

and phosphates and the particle size (y_4 , y_5 , and y_8) in the products, is anything but an easy task.

The molar ratio of the substrates had a significant effect on the first two input variables. However, the shape of the surface seems to suggest the effect of the pressure of the process. The effect of variables x_1 and x_2 on the particle size of the precipitated phosphates was thought to be statistically insignificant. The surface analysis suggests that products with the biggest particle size can be obtained at the $\text{Ca}^{2+} : \text{PO}_4^{3-}$ molar ratio of 0.2 : 1 and maximum pressure values.

Figure 4 presents a comparison of SEM images for the products precipitated in the reaction mixture with the $\text{Al}^{3+} : \text{Ca}^{2+} : \text{Mo}^{6+} : \text{PO}_4^{3-}$ molar ratios of (a) 0.67 : 0.33 : 0.33 : 1 (a); 0.67 : 0.2 : 0.2 : 1 (b), and 0.67 : 0.07 : 0.07 : 1 and (c) at the pressure of 2.1 MPa. The shape of particles was observed to be dependent on the molar ratio of the reagents. With the decreasing content

of Ca^{2+} and Mo^{6+} ions in the substrates, the product particle size was bigger. The observed associations correlated with the content of the $(\text{NH}_4)_3\text{Al}_2(\text{PO}_4)_3$ crystalline phase, whose share was bigger at the lower $\text{Al}^{3+} : \text{Ca}^{2+} : \text{Mo}^{6+} : \text{PO}_4^{3-}$ reagent molar ratio of 0.67 : 0.07 : 0.07 : 1. The particles of products with the highest content of the crystalline phase had the biggest size, although the statistical assessment did not show any effect of the reagent molar ratio on the property.

The relationship between the chemical composition of the prepared aluminum phosphates modified with ammonium, calcium and molybdenum and their corrosion inhibition efficiency was investigated using the presented Tafel test results.

Table 4 presents the results of corrosion inhibition efficiency tests for different extracts. The results were compared with those of FC-M2 zinc phosphate and FAC

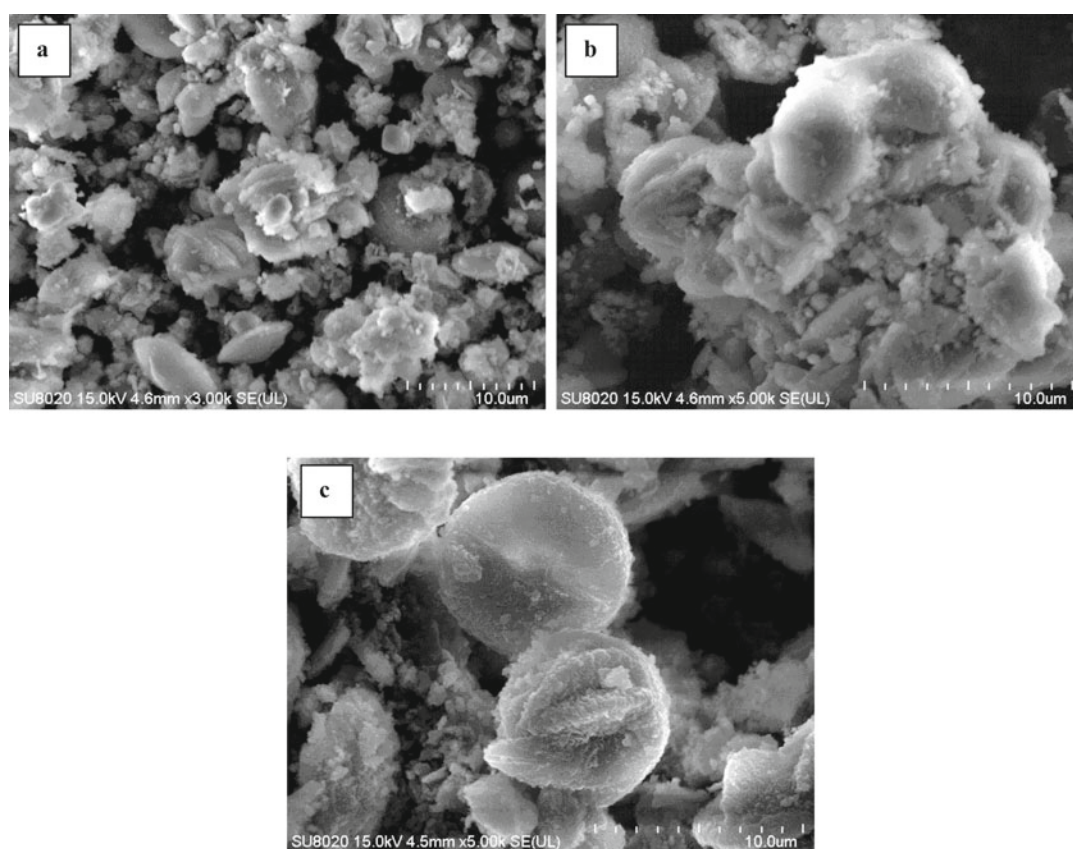


Figure 4. SEM images of the aluminum phosphates modified ammonium, calcium and molybdenum precipitated from reaction mixture with a molar ratio $\text{Al}^{3+} : \text{Ca}^{2+} : \text{Mo}^{6+} : \text{PO}_4^{3-}$ equal: (a) 0.67 : 0.33 : 0.33 : 1; (b) 0.67 : 0.2 : 0.2 : 1 (b) and (c) 0.67 : 0.07 : 0.07 : 1 at the pressure of 2.1 MPa

Table 4. Potentiodynamic polarization test result for steel immersed in extract of phosphate pigments in 3.5 wt% NaCl aqueous solution

Phosphate acronym	I_{corr} [$\mu\text{A}/\text{cm}^2$]	E_{corr} [mV vs. SCE]	P [mm/year]	η [%]
–	2.17	–799	0.025	–
FAC	1.1	–725	0.013	49
FC-M2	1.2	–796	0.014	45
AACMPH1	2.71	–775	0.0316	–25
AACMPH2	1.13	–779	0.0132	48
AACMPH3	1.44	–767	0.0168	34
AACMPH4	2.81	–767	0.0327	–29
AACMPH5	1.91	–771	0.0222	12
AACMPH6	2.26	–776	0.0263	–4
AACMPH7	2.16	–779	0.0251	0.5
AACMPH8	2.14	–772	0.0249	1.4
AACMPH9	1.99	–776	0.0232	8

aluminum-zinc phosphate (manufactured by Złoty Stok Antykorozja Sp. z o.o. in Złoty Stok, Poland).

Following the analysis of results, the corrosion of steel was concluded to proceed the slowest with AACMPH2 and 3 materials out of all the tested extracts of modified aluminum phosphates, precipitated in a microwave reactor. The rates of corrosion for AACMPH2 and 3 were 0.0132 mm/year and 0.0168 mm/year, respectively. While comparing the obtained results with those of steel investigated in a NaCl aqueous solution, the corrosion inhibition efficiency for phosphates obtained in the experiments was 48% and 34%, respectively. The effectiveness was close to that of commercial anti-corrosive pigments (FAC and FC-M2). The lowest corrosion inhibition efficiency was determined for phosphates used in the experiments involving AACMPH1 and 4, which amounted to -25% and -29%, respectively. Corrosion was observed to proceed with the slowest rate in the phosphate extracts with the lowest Ca to Mo molar ratio and with a higher total amount of aluminum and ammonium moles per one mole of phosphates.

Sediments precipitated in Tafel tests (Table 5) were examined using XRD and SEM-EDX analysis. Unfortunately, the identification of the crystalline phases in obtained powders was impossible due to their amorphous nature. The powders had different contents of aluminum, calcium, iron and phosphates. Molybdenum content was not determined. No correlation was found between the chemical properties of the extracted phosphates, the corrosion inhibition efficiency examined in potentiodynamic tests and the chemical composition of corrosion products.

Table 5. EDX analysis of sediments precipitated during the electrochemical studies

Phosphate acronym	Al	Ca	Mo	Fe	P	Molar ratio of Al : Ca : Mo : Fe : P
	Content [wt%]					
AACMPH1	2.49	0.44	0	15.41	3.18	0.90 : 0.11 : 0 : 2.69 : 1
AACMPH2	1.77	0.03	0	2.43	0.10	20.30 : 0.23 : 0 : 13.47 : 1
AACMPH3	0.58	0.29	0	22.98	5.39	0.12 : 0.04 : 0 : 2.36 : 1
AACMPH4	14.32	2.90	0	31.08	2.07	7.94 : 1.08 : 0 : 8.33 : 1
AACMPH5	1.99	0.34	0	4.89	1.55	1.47 : 0.17 : 0 : 1.75 : 1
AACMPH6	4.71	1.02	0	31.30	2.29	2.36 : 0.34 : 0 : 7.58 : 1
AACMPH7	11.29	1.67	0	53.27	0.97	13.35 : 1.33 : 0 : 30.45 : 1
AACMPH8	4.38	0.91	0	7.78	1.98	2.54 : 0.36 : 0 : 2.18 : 1
AACMPH9	2.36	0.63	0	14.46	2.53	1.07 : 0.19 : 0 : 3.17 : 1

CONCLUSIONS

Crystalline materials with varied content of nitrogen, aluminum, molybdenum, calcium, phosphorus and crystalline phases depending on process parameters were obtained using the hydrothermal method.

It was statistically demonstrated that the content of Al, Ca, Mo, N and P in the products was dependent on the variable x_2 , i.e. on the $Al^{3+} : Ca^{2+} : Mo^{6+} : PO_4^{3-}$ reagent molar ratio. The input variable x_1 (pressure) had no statistically significant effect on the dependent variables y_{1-5} . The input variables did not have any statistically significant effect on either S_{BET} specific surface area or the particle size of the obtained products. The pressure and the reagent molar ratio were shown to have a significant effect on oil number.

The highest corrosion inhibition efficiency for the phosphates discussed above was 48% and 34%, respectively. The efficiency was close to that of commercial

anti-corrosive pigments (FAC and FC-M2) which were used for comparison purposes.

The statistical assessment of planned examinations enables a selection of process parameters conducive to obtaining aluminum phosphates modified with ammonia, calcium and molybdenum with preset physicochemical properties.

ACKNOWLEDGEMENTS

This work was supported by the National Centre for Science in Poland under project for 2011–2014.

LITERATURE CITED

- Benda, P. & Kalendová, A. (2013). Anticorrosion Properties of Pigments based on Ferrite Coated Zinc Particles. *Phys. Procedia*. 44, 185–194. DOI: 10.1016/j.phpro.2013.04.023.
- Directive 2004/42/CE of the European Parliament and of the Council of 21 April 2004 on the limitation of emissions of volatile organic compounds due to the use of organic solvents in certain paints and varnishes and vehicle refinishing products and amending Directive 1999, 13/EC.
- United States Environmental Protection Agency. Retrieved December 1, 2014, from <http://www.epa.gov/iaq/voc.html>
- Mousavifard, S.M., MalekMohammadi Nouri, P., Attar, M.M. & Ramezanzadeh, B. (2013). The effects of zinc aluminum phosphate (ZPA) and zinc aluminum polyphosphate (ZAPP) mixtures on corrosion inhibition performance of epoxy/polyamide coating. *Ind. Eng. Chem. Res.* 19, 1031–1039. DOI: 10.1016/j.jiec.2012.11.027.
- Kołodziejski, R., Zieliński, J. & Grudzińska, E. (2009). Effect of microwaves on properties of desulfurized vacuum residue of crude oil. *Przem. Chem.* 88(11), 1188–1190.

6. Deyab, M.A. & Keera, S.T. (2014). Effect of nano-TiO₂ particles size on the corrosion resistance of alkyd coating. *Mater. Chem. Phys.* 146, 406–411. DOI: 10.1016/j.matchemphys.2014.03.045.
7. Grzmil, B., Kic, B. & Lubkowski, K. (2007). Studies on obtaining of zinc phosphate nanomaterials. *Rev. Adv. Mater. Sci.* 14, 46–48.
8. Łuczka, K., Grzmil, B., Srenscek-Nazzal, J. & Kowalczyk, K. (2013) Studies on obtaining of aluminium ammonium calcium phosphates. *J. Ind. Eng. Chem.* 19, 1000–1007. DOI: 10.1016/j.jiec.2012.11.023.
9. Łuczka, K., Sibera, D., Smorowska, A. & Grzmil, B. (2013) Preparation of aluminium ammonium calcium phosphates using microwave radiation. *Chem. Pap.* 67(9), 1210–1217. DOI: 10.2478/s11696-013-0326-8.
10. Varnaite – Žuravliova, S., Jankauskaite, V., Guobiene, A. & Prosycevas, I. (2014). Investigation of optical and morphological properties of metalized nanocomposites. *Appl. Surf. Sci.* 317, 639–647. DOI: 10.1016/j.apsusc.2014.08.149.
11. Huang, H., Zhang, S., Qi, L., Yu, X. & Chen, Y. (2006). Microwave-assisted deposition of uniform thin gold film on glass surface. *Surf. Coat. Technol.* 200, 4389–4396. DOI: 10.1016/j.surfcoat.2005.02.203.
12. Gaina, L., Torje, I., Gal, E., Lupan, A., Bischin, C., Silaghi-Dumitrescu, R., Damian, G., Lönnecke, P., Cristea, C. & Silaghi-Dumitrescu, L. (2014). Microwave assisted synthesis, photophysical and redox properties of (phenothiazinyl)vinylpyridinium dyes. *Dyes Pigm.* 102, 315–325. DOI: /10.1016/j.dyepig.2013.10.044.
13. Beall, G.W., Duraia, E.M., El-Tantawy, F., Al-Hazmi, F. & Al-Ghamdi, A.A. (2013). Rapid fabrication of nanostructured magnesium hydroxide and hydromagnesite via microwave-assisted technique. *Powder Technol.* 234, 26–31. DOI: 10.1016/j.powtec.2012.09.029.
14. Box, G.E.P., Hunter, J.S. & Hunter, W.G. (2005). *Statistics for Experimenters*. Hoboken, NJ: Wiley – Interscience.
15. Minczewski, J. & Marczenko, Z. (2005). *Chemia analityczna*. Warszawa, PWN.
16. Orion Ammonia Electrode. (2003). Instruction manual, Thermo Electron Corporation. Texas, USA.
17. Polish Committee for Standardization. (1999). General methods of test for pigments and extenders – Part 5: Determination of oil absorption value. PN EN ISO 787-5:1995, Warsaw.