

Functional groups grafted on poly(vinyl chloride) – evaluation of new modified polymers in metal ions adsorption

Faten Mbarki¹⁾, Fayçel Ammari^{1), *)}, Abir Bel Haj Amor¹⁾, Faouzi Meganem¹⁾

DOI: [dx.doi.org/10.14314/polimery.2017.109](https://doi.org/10.14314/polimery.2017.109)

Abstract: Poly(vinyl chloride) (PVC) has been subjected to numerous chemical modifications which were undertaken in order to improve its properties, the use of PVC in new applications and understanding of PVC-related phenomena. This work describes the chemical modification of PVC by amino groups (benzylamine and diethylenetriamine) through nucleophilic substitution reactions of its chlorine atoms to obtain P_1 polymer. The modified polymer was subsequently reticulated with dichlorodiethyl ether to obtain P_2 polymer. The obtained polymers were characterized using infrared spectroscopy (FT-IR), elemental analysis (CHN), differential scanning calorimetry (DSC), thermogravimetric analysis (TGA), differential thermal analysis (DTA), and X-ray diffraction (XRD). The modified polymers (P_1 and P_2) were tested for metal ion extraction (cadmium, cobalt, lead, or chromium) using the solid-phase extraction (SPE) method and the inductively coupled plasma atomic emission spectrometry (ICP-AES) technique. Quantitative adsorption measurements were performed using solutions containing $2 \cdot 10^{-4}$ M of heavy metal ions with pH = 3.5–4.5 at a flow rate of 0.6 dm³/min. The new extractants based on modified PVC (P_1 and P_2) were able to remove the negative effects of heavy metals contained in aqueous solutions. For Pb²⁺, the extraction percentage was 98 % using P_1 and 90.3 % using P_2 .

Keywords: poly(vinyl chloride), benzylamine, diethylenetriamine, dichlorodiethyl ether, substitution reaction, metal extraction.

Szczepienie funkcyjnych grup aminowych na poli(chloroku winylu) – ocena przydatności otrzymanych polimerów w adsorpcji jonów metali

Streszczenie: Przeprowadzono chemiczną modyfikację poli(chloroku winylu) (PVC) w reakcji nukleofilowego podstawienia atomów chloru grupami aminowymi (benzyloamina i dietylenotriamina). Otrzymany polimer P_1 szczepiono następnie eterem dichlorodietylowym – uzyskano polimer P_2 . Wytworzone polimery scharakteryzowano za pomocą spektroskopii w podczerwieni (FT-IR), analizy elementarnej (CHN), różnicowej kalorymetrii skaningowej (DSC), analizy termogravimetrycznej (TGA), różnicowej analizy termicznej (DTA) i dyfrakcji rentgenowskiej (XRD). Polimery P_1 i P_2 testowano w procesie ekstrakcji jonów metali (kadmu, kobaltu, ołowiu lub chromu), stosując ekstrakcję w fazie stałej (SPE) i metodę atomowej spektrometrii emisyjnej z plazmą wzbudzaną indukcyjnie (ICP-AES). Pomiary ilościowe adsorpcji prowadzono w roztworach wodnych zawierających $2 \cdot 10^{-4}$ M jonów metali ciężkich, o pH = 3,5–4,5 i przy szybkości przepływu 0,6 dm³/min. Nowe ekstrahenty na bazie zmodyfikowanego PVC (P_1 , P_2) adsorbowały metale ciężkie zawarte w roztworach wodnych – w wypadku jonów Pb²⁺ ekstrakcja za pomocą P_1 wyniosła 98 %, a za pomocą P_2 – 90,3 %.

Słowa kluczowe: poli(chlorek winylu), benzyloamina, dietylenotriamina, eter dichlorodietylowy, reakcja podstawienia, ekstrakcja jonów metali.

Poly(vinyl chloride) (PVC) is one of the most important polymers due to its versatility and excellent physicochemical properties. PVC is employed in a wide range of fields [1, 2]. PVC has been subjected to numerous reactions, mainly

dehydrochlorination [3] and nucleophilic substitutions [4, 5], degradation [6, 7], grafting and cross-linking [8–10]. The chemical modification of the PVC has been important in the development of macromolecular chemistry.

It is well known that PVC can be chemically modified in solution by the nucleophilic substitution of its chlorine atoms [11–13]. The modification of PVC through the formation of $C_{PVC}-X$ with X = N, O or S, is easier than that

¹⁾ University of Carthage, Faculty of Sciences of Bizerte, Laboratory of Organic Synthesis, 7021 Jarzouna, Bizerte, Tunisia.

*) Author for correspondence; e-mail: ammari1971@gmail.com

with $C_{\text{PVC}}-C$ [14]. The present work is aimed to perform a functionalization of PVC by nucleophilic substitution reactions with amine groups (benzylamine and diethylenetriamine) and by chemical grafting of dichlorodiethyl ether group. The new products based on modified PVC (P_1 and P_2) were able to remove toxic pollutants from wastewater. Several techniques are available for the study of the elimination of these toxic products from wastewater. Adsorption process is one of the most important methods for the removal of toxic organics, using several types of adsorbents, such as polymeric adsorbents [15].

This work has evaluated the efficiency of a modified polymer in the removal of toxic metals from the environment and especially from wastewater since water pollution is a major worldwide issue caused by contamination from several toxic pollutants [16, 17].

EXPERIMENTAL PART

Materials

Commercial PVC (P_0) ($M_r = 48\ 000$) and benzylamine were purchased from Fluka. *N,N*-Dimethylformamide (DMF), diethylenetriamine (99 %), dichlorodiethyl ether and $\text{Cr}(\text{NO}_3)_3 \cdot 9 \text{H}_2\text{O}$ (99 %) were produced by Sigma-Aldrich. $\text{CdCl}_2 \cdot \text{H}_2\text{O}$ (98 %), $\text{Pb}(\text{NO}_3)_2$ (98 %) and $\text{CoCl}_2 \cdot 6 \text{H}_2\text{O}$ (99 %) were provided by Fluka. Diethyl ether was bought from Panreac. Potassium iodide (KI) and sodium hydroxide (NaOH) were purchased from Prolabo.

Chemical functionalization of PVC

In order to make the polymer (PVC) more reactive, we performed the Conant-Finkelstein reaction with the aim to replace the chlorine atoms of the pure PVC with iodine ones through a nucleophilic substitution mechanism [18].

Preparation of amino-PVC

2 g of PVC polymer (32 mmol Cl/g) were dissolved in 30 cm³ of DMF and 2 cm³ of benzylamine (1.96 g, 18.3 mmol), 0.5 g of KI and 2 cm³ of diethylenetriamine (1.91 g, 18.5 mmol) were then added. The reaction mixture was stirred at 125 °C for 24 h and then cooled to the room temperature. The compound was collected by filtration, treated with a 0.1 M aqueous solution of NaOH, filtered and washed several times with distilled water. The modified polymer was dried for 24 h at the room temperature, crushed and washed with diethyl ether and distilled water. Finally, the obtained polymer (P_1) was dried in an oven for 12 h at 60 °C to evaporate water and the residual solvent was evaporated under vacuum at 70 °C for 48 h.

Grafting of dichlorodiethyl ether on amino-PVC

2 g of previously modified PVC (P_1) was dissolved in 30 cm³ of DMF and 6 cm³ of dichlorodiethyl ether were

added to the solution. The reaction mixture was stirred and heated at 125 °C for 24 h. The resulting product was filtered and washed with water. Then, the modified polymer was dried for 24 h at the room temperature and washed with diethyl ether and distilled water. The obtained polymer (P_2) was dried in an oven for 12 h at 60 °C and finally dried under vacuum at 70 °C for 48 h.

Extraction of some metal ions

The work consisted in using the polymers modified by amino and dichlorodiethyl ether groups for the removal of metal ions (Cr^{3+} , Cd^{2+} , Pb^{2+} , or Co^{2+}) using solid phase extraction method (SPE).

Metal ion extraction method

Aqueous metal salt solutions of $\text{Cr}(\text{NO}_3)_3 \cdot 9 \text{H}_2\text{O}$, $\text{CdCl}_2 \cdot \text{H}_2\text{O}$, $\text{Pb}(\text{NO}_3)_2$, and $\text{CoCl}_2 \cdot 6 \text{H}_2\text{O}$ were prepared at a known concentration of $2 \cdot 10^{-4}$ mol/dm³ with the pH of each aqueous solution varying between 3.5 and 4.5. Then 0.1 g of the modified polymer (powder was crushed in a mortar and was sieved through $a \leq 100$ μm sieve) was washed several times with distilled water to remove any possible salts present. The washed polymer was directly added to a flask ($V = 30$ cm³) containing 20 cm³ of the metal ion solution at the room temperature and subjected to stirring in order to determine the optimal extraction time according to the change in conductivity (σ) of the aqueous solution with time. Finally, the suspension was filtrated and the metal content in the filtrate evaluated by the inductively coupled plasma atomic emission spectrometry (ICP-AES) analysis.

Methods of testing

The infrared analysis using the (ATR FT-IR) technique was carried out on a Thermo Scientific Nicolet FTIR 200 spectrophotometer with a scanning range between 4000 and 400 cm⁻¹.

Differential scanning calorimetry (DSC) was performed on a SETARAM DSC 131. Differential thermal analysis (DTA) and thermogravimetric analysis (TGA) were performed on a SETARAM TGA 92 device.

The X-ray diffraction analysis (XRD) was done on a Bruker D8 Advance apparatus.

The pH was measured with a pH and conductivity meter, VWR / CO 3000L.

An elemental analysis of N was performed using a Perkin-Elmer Analyzer CHN Series II 2400.

The extraction percentage of each metal ion by synthesized polymers was obtained with inductively coupled plasma atomic emission spectrometry (ICP-AES) which was done on a Horiba Jobin Yvon spectrometer (Activa model). The wavelengths of the metal ions (Cr, Cd, Pb, or Co) were recorded in the following order: 267.719, 226.502, 220.353, and 238.892 nm.

The results of the metal ion extraction for each synthesized polymer were expressed as percentages, of their initial concentration. The percentage was calculated using the following expression: $E = [(C_i - C_f) / C_i] \cdot 100 \%$

where: C_i – the initial concentration of the metal in aqueous solution, C_f – the concentration of the remaining quantity of the metal ion in aqueous solution after 24 hours.

RESULTS AND DISCUSSION

Analysis of the modified polymers

IR spectroscopy

The IR spectroscopy analysis of the modified polymer (P_1) clearly shows that a substitution reaction takes place, as indicated by the appearance of characteristic bands of the amino groups at 3434 and 3310 cm^{-1} corresponding to NH_2 and NH , respectively, and also an absorption at 1665 cm^{-1} corresponding to N-H bending in plane. An absorption at 1467 cm^{-1} corresponding to aromatic C=C is also observed, confirming the presence of the benzene ring in polymeric chains of PVC. However, the spectrum also shows the presence of the chlorine stretching vibration bands ($\nu_{\text{C-Cl}}$) with low intensity at 701 cm^{-1} . This indicates that some chlorine atoms have not entirely disappeared. All the characteristic bands observed for P_1 were also seen in the FT-IR spectrum of P_2 (Fig. 1), with an increase in the intensity of the valence band corresponding to C–O–C which appears at around 1050–1170 cm^{-1} . This finding confirmed the grafting of ether group (dichlorodiethyl ether) on the amino-PVC.

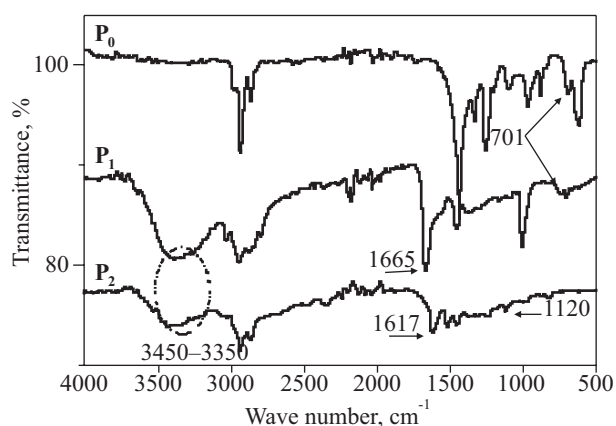


Fig. 1. FT-IR spectra of: P_0 , P_1 , and P_2

Comparison of the FT-IR spectra for P_1 and P_2 with that of P_0 clearly shows the modification of P_0 given that the P_0 spectrum has absorption bands at 701 cm^{-1} , corresponding to the C-Cl band, and two absorption bands at 2860 cm^{-1} and at 2930 cm^{-1} for symmetric and asymmetric CH_2 , respectively, which are only present in P_0 (Table 1). Finally, the absence of the chlorine stretching vibration

band ($\nu_{\text{C-Cl}}$) between 600 and 800 cm^{-1} in the P_2 spectra confirms that chlorine atoms have been substituted by benzylamine and diethylenetriamine.

Table 1. FT-IR spectroscopic data for P_0 and modified polymers P_1 and P_2

Characteristic vibration	Wave number, cm^{-1}		
	P_0	P_1	P_2
- CH_2 asymmetric and symmetric vibrations	2930–2860	2930–2860	2930–2860
-C-Cl vibration	701	701	–
- NH_2 asymmetric and symmetric vibrations	–	3434–3310	3437–3310
N-H bending	–	1665	1617
C=C aromatic	–	1467	1465
C-O-C ether	–	–	1170–1050

Elemental analysis

Comparing the element percentages (% C, % H, and % N) for P_1 and P_2 with those of P_0 clearly proves that a chemical change has happened. This is especially clear from the nitrogen percentage which increased from 0 % (P_0) to 6.31 % and 5.08 % for P_1 and P_2 , respectively. The percentage of other elements (C and H) also increased (Table 2).

Table 2. Elemental analysis for P_0 and modified polymers P_1 and P_2

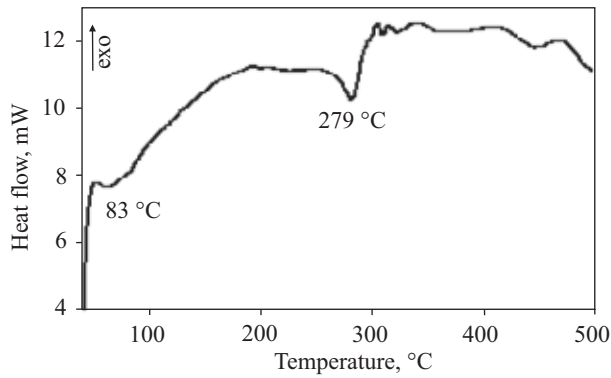
Sample name	% C	% H	% N	% $\Sigma_{\text{C,H,N}}$
P_0	38.85	4.73	0.00	43.58
P_1	65.25	8.29	6.31	79.85
P_2	69.08	5.43	5.08	79.59

DSC and DTA-TGA characterization of P_0 , P_1 and P_2

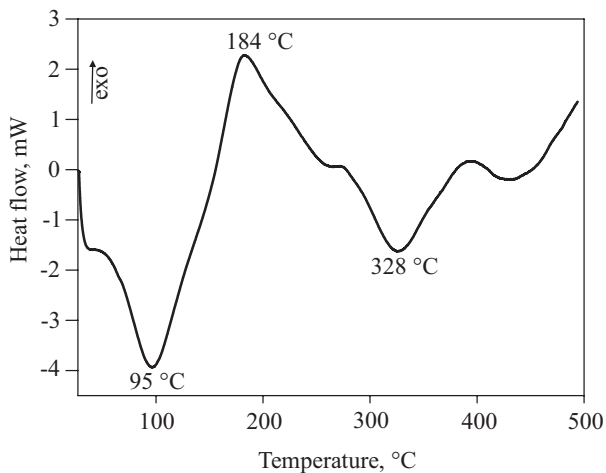
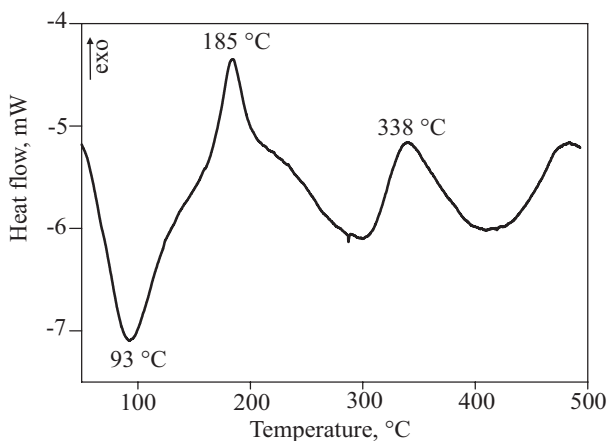
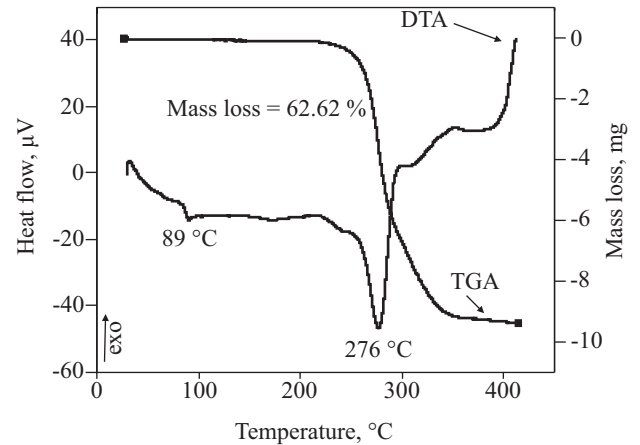
The DSC curve of the commercial PVC (P_0) recorded from a sample of mass $m = 7.6$ mg with a heating rate of 20 $^\circ\text{C}/\text{min}$ in the temperature range from 25 to 500 $^\circ\text{C}$ showed that the T_g is 83 $^\circ\text{C}$ (Fig. 2) and the melting point is 279 $^\circ\text{C}$.

On the other hand, the DTA-TGA curves of P_0 ($m = 14.5$ mg) also showed the presence of endothermic peak (melting point) around 276 $^\circ\text{C}$ which was accompanied by a significant weight loss of 62.62 % (Fig. 3).

The DSC curve of P_1 recorded from a sample of mass $m = 8.68$ mg with the heating rate of 20 $^\circ\text{C}/\text{min}$ in the temperature range from 25 to 500 $^\circ\text{C}$, showed three peaks: two endothermic and one exothermic. The first endothermic peak was observed at 95 $^\circ\text{C}$ and probably corresponds to the evaporation of residual water; the exothermic peak was observed at 184 $^\circ\text{C}$ showing the reorganization of

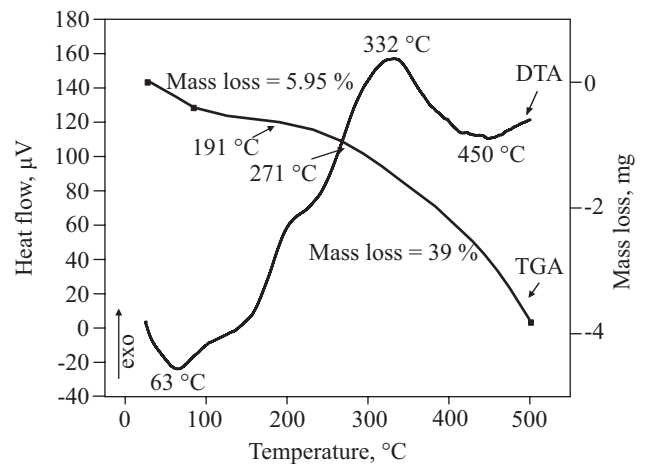
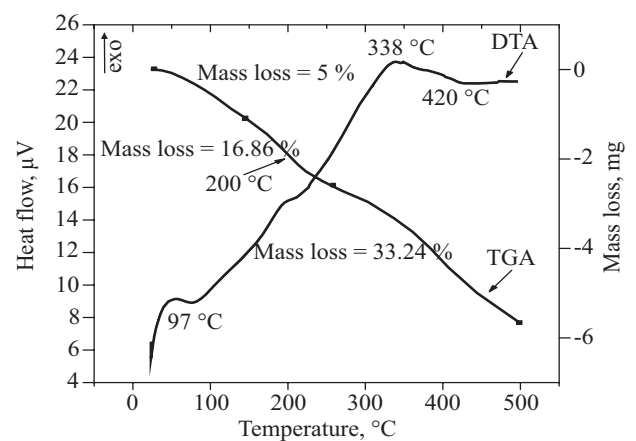
Fig. 2. DSC thermogram of P_0

polymeric chains without weight loss. The other endothermic peak at 328 °C shows the decomposition of the polymer (Fig. 4). On the other hand, the DTA-TGA curves of P_1 recorded from a sample of $m = 8.4$ mg with the heating rate of 20 °C/min in the temperature range of 25 to 500 °C (Fig. 5) showed an endothermic peak at 63 °C corresponding to the weight loss of 5.95 % that can be explained with the departure of water molecules. The range between 271 °C and 450 °C corresponds to a significant weight loss of 39 %; this has been attributed to the start of the polymer decomposition. The decomposition contin-

Fig. 4. DSC thermogram of P_1 Fig. 6. DSC thermogram of P_2 Fig. 3. DTA-TGA curves of P_0

ues for temperatures above 450 °C until the total decomposition of the polymer chains.

The DSC curve of P_2 (Fig. 6) was obtained from a sample of $m = 5.53$ mg and showed three peaks: one endothermic and two exothermic observed at 93 °C, 185 °C, and 338 °C, respectively. The first peak (93 °C) could be attributed to the evaporation of residual water. The exothermic peak in the temperature range between 150 °C and 250 °C marks the start of the polymer decomposition. The peak

Fig. 5. DTA-TGA curves of P_1 Fig. 7. DTA-TGA curves of P_2

at 338 °C has been attributed to the decomposition of the polymer. The DTA-TGA curves for P_2 were performed on 12.3 mg samples with the heating rate of 20 °C/min. The results were recorded between 50 and 450 °C (Fig. 7).

The analysis showed three peaks: one endothermic and two exothermic. The first peak at 97 °C was accompanied by the weight loss of 5 % corresponding to the departure of water molecules. The other peaks, observed at 200 and 338 °C, respectively, were accompanied by a significant weight loss of 33.24 % which may suggest that the polymer decomposition took place stepwise. In fact, the decomposition continues for temperatures above 400 °C until the total decomposition of the polymer chains (Table 3).

Table 3. DSC analysis of P_0 , P_1 and P_2 and their structures by XRD

Sample name	T_g °C	T_{endo} °C	T_{exo} °C	X-ray
P_0	83	279	–	Amorphous
P_1	–	95; 328	184	Amorphous
P_2	–	93	185; 338	Amorphous

T_g – glass transition temperature, it only appears in the case of P_0 (Fig. 2), T_{endo} – endothermic transformation, T_{exo} – exothermic transformation.

XRD characterization of the samples

The suspension of the final modified polymer with the metallic aqueous solution was filtered, and the com-

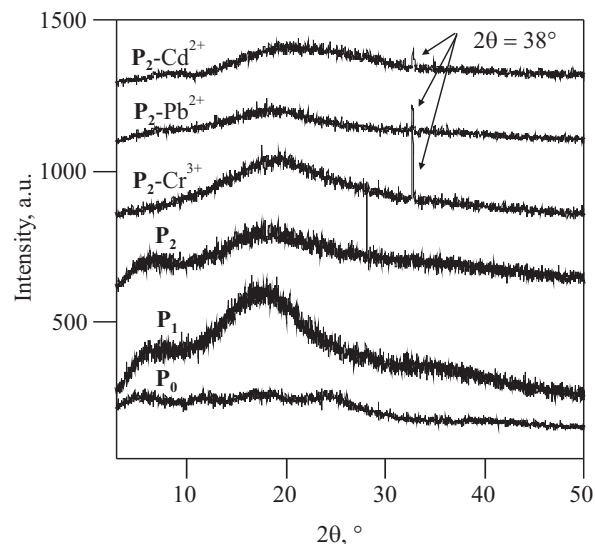
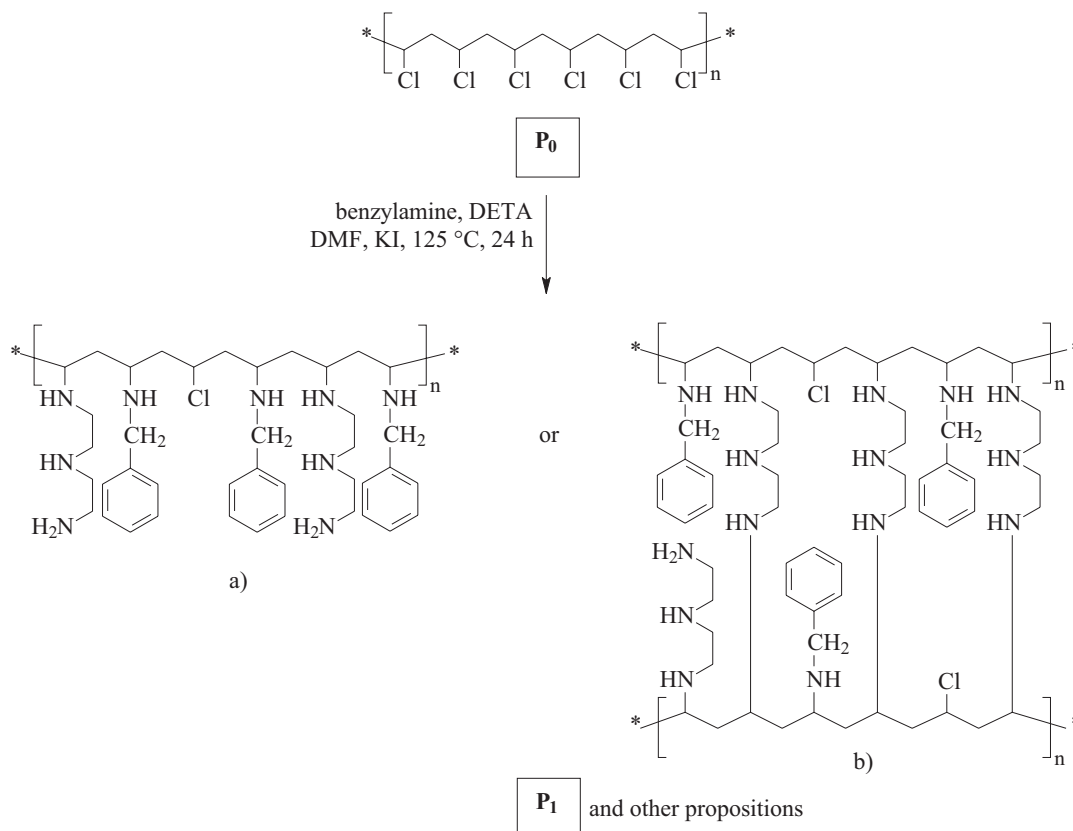


Fig. 8. X-ray diffractograms of: P_0 , P_1 , P_2 , P_2 - Cr^{3+} , P_2 - Pb^{2+} , and P_2 - Cd^{2+}

pound collected in the filter paper was dried at the room temperature and then analyzed with X-ray.

The X-ray diffractograms for P_0 , P_1 and P_2 in the $2\theta = 5$ – 60° range do not show any diffraction peaks. This result indicates that these polymers have an amorphous structure. Their XRD for P_2 - Cr^{3+} , P_2 - Pb^{2+} and P_2 - Cd^{2+} have a characteristic peak at $2\theta = 38^\circ$ which is absent for P_1 and P_2 in the $2\theta = 5$ – 60° range. The diffractograms also show the absence of a bump at $2\theta = 10^\circ$ for P_2 - Cr^{3+} , P_2 - Pb^{2+} and P_2 - Cd^{2+} complexes. The significance of this situation in-



Scheme A

indicates the insertion of the M^{n+} cation [Cr(III), Pb(II), or Cd(II)] in P_2 cavity (Fig. 8).

Proposed structures of P_1 and P_2

P_1 structure

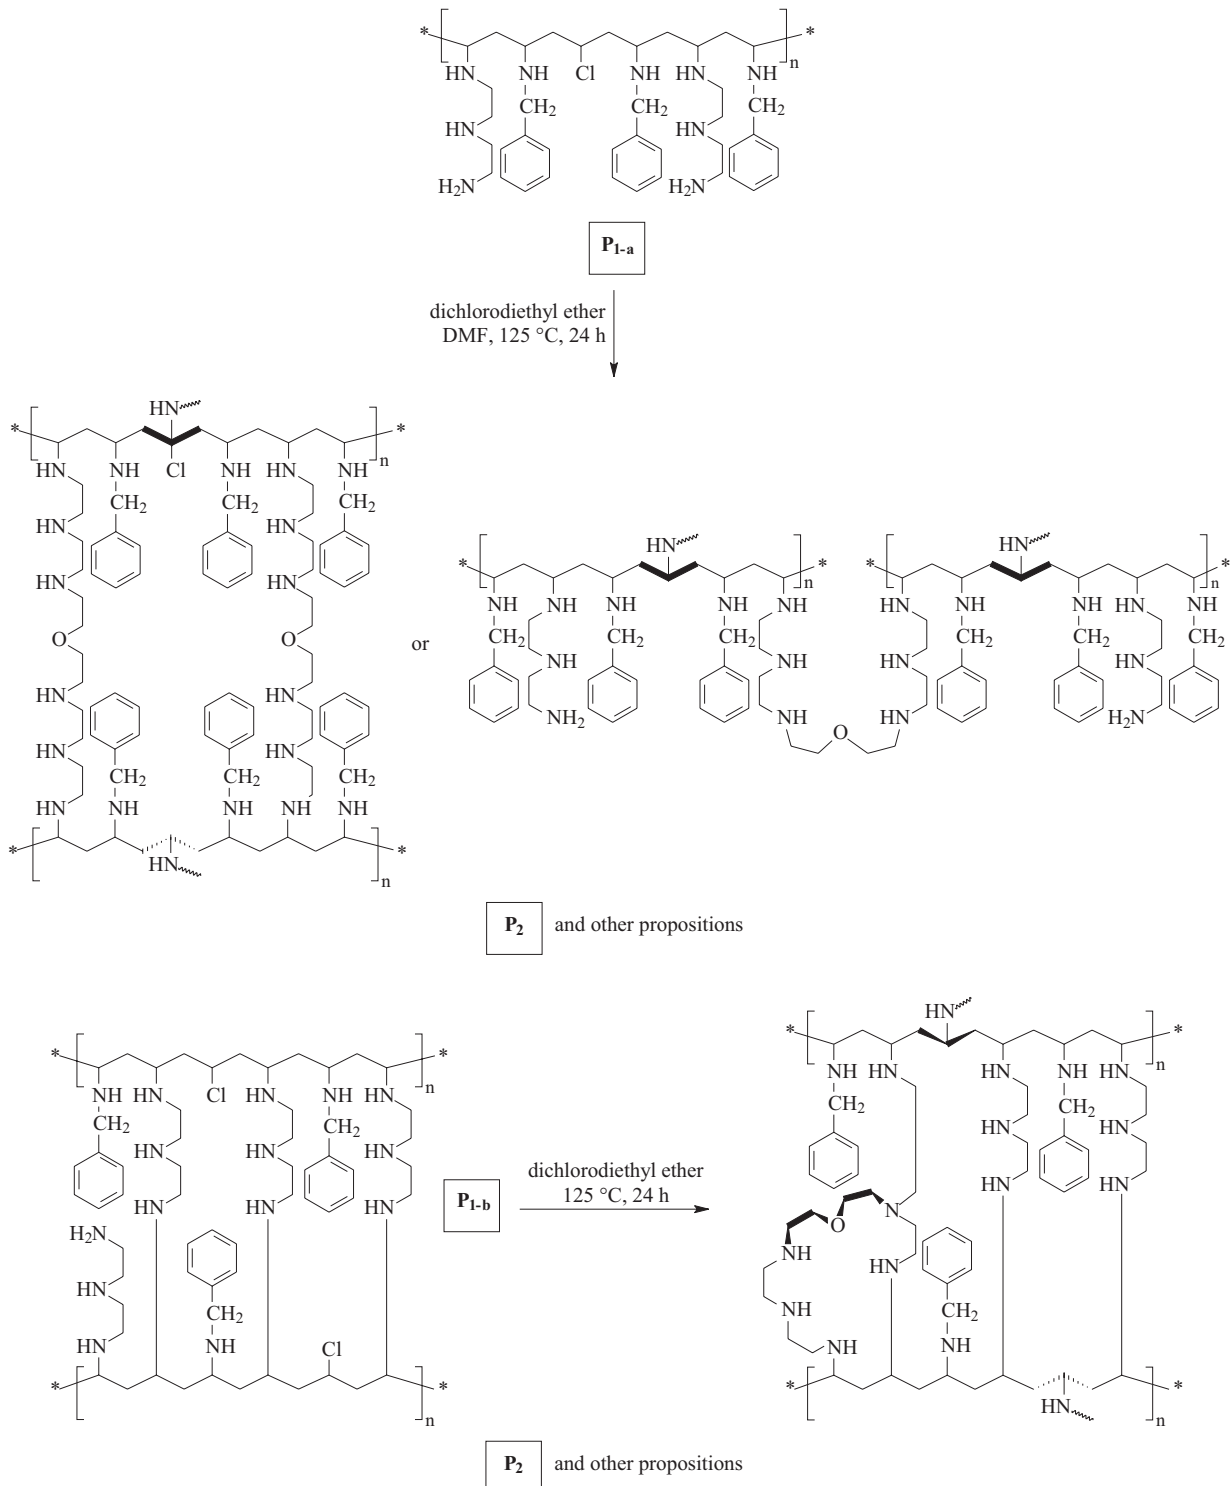
The different analyses of the modified polymer (P_1) prove the modification of commercial PVC (P_0) during the substitution reactions by benzylamine and diethylenetriamine. A possible structure of P_1 is shown in

Scheme A. Some chlorine atoms are still present in the proposed structures.

The IR spectrum of P_1 shows that the chlorine stretching vibration bands (ν_{C-Cl}) have not entirely disappeared; this suggests the presence of some chlorine atoms in P_1 structures.

P_2 structure

P_1 has been grafted with dichlorodiethyl ether. A possible structure of P_2 is shown in Scheme B. The proposed



Scheme B

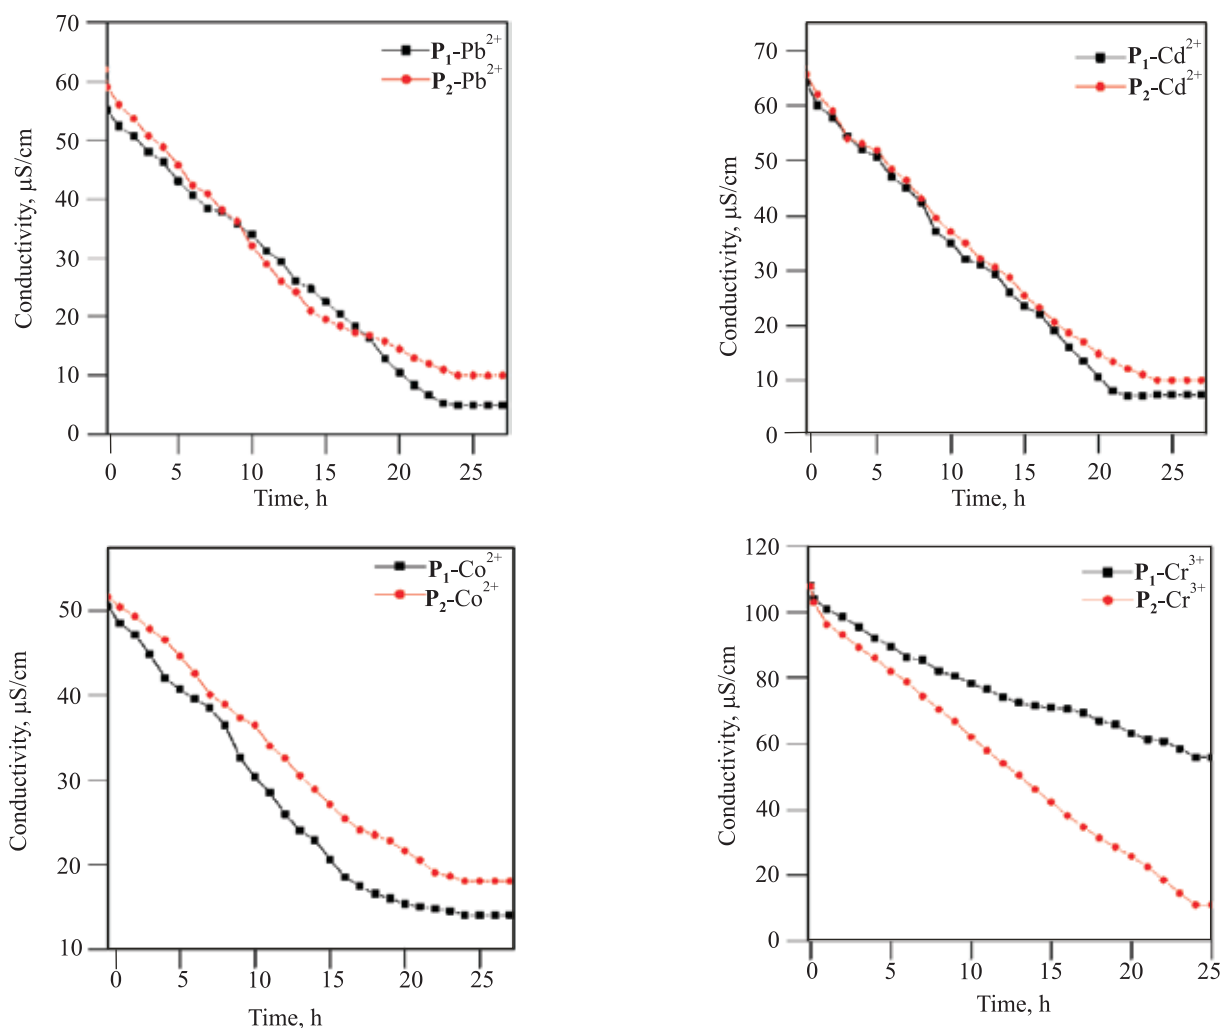


Fig. 9. Variation curves of electrical conductivity with time for aqueous solutions of metal cations (Pb^{2+} , Cd^{2+} , Co^{2+} , or Cr^{3+}) in contact with P_1 and P_2

structures are suggested by the complete disappearance of the $\nu_{\text{C-Cl}}$ band from the IR spectrum.

Metal cation extraction using modified polymers

Kinetic study

The kinetic study showed that the optimum extraction time obtained with polymers P_1 and P_2 is of approximately 24 h. The extraction results are the average of three experiments.

Figure 9 shows variation curves of average electrical conductivity with time for metal cations (Pb^{2+} , Cd^{2+} , Co^{2+} , or Cr^{3+}) in contact with the modified polymers (P_1 and P_2).

Percentages of metal cations extraction

The extraction percentages of metal ions (Cr^{3+} , Co^{2+} , Cd^{2+} , or Pb^{2+}) with the synthesized polymer (P_1) varied between 45 and 98 % and between 65.1 and 96.65 % for the other polymer (P_2) (Table 4, Fig. 10).

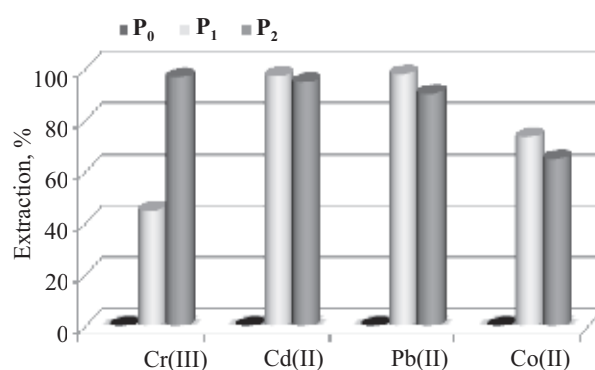


Fig. 10. Percentages of metal cations extraction with the polymers P_0 , P_1 and P_2

The extraction power of P_1 in the cases of the studied metals followed the following increasing selectivity order: $\text{Cr}^{3+} \ll \text{Co}^{2+} < \text{Cd}^{2+} < \text{Pb}^{2+}$, while the second polymer followed another order: $\text{Co}^{2+} \ll \text{Pb}^{2+} < \text{Cd}^{2+} < \text{Cr}^{3+}$. The extraction percentages using P_1 indicated more selectivity for $\text{Pb}(\text{II})$ with the percentage of 98 %, while P_2 showed more selectivity for $\text{Cr}(\text{III})$ with the percentage of 96.65 %.

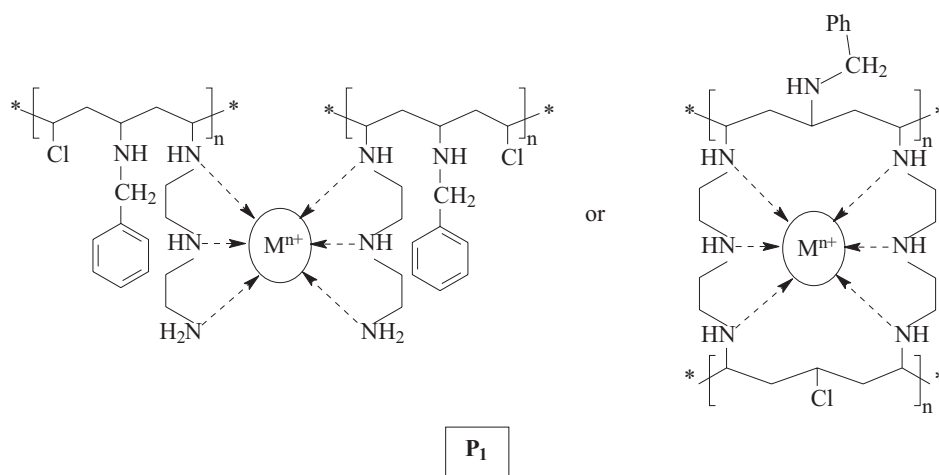
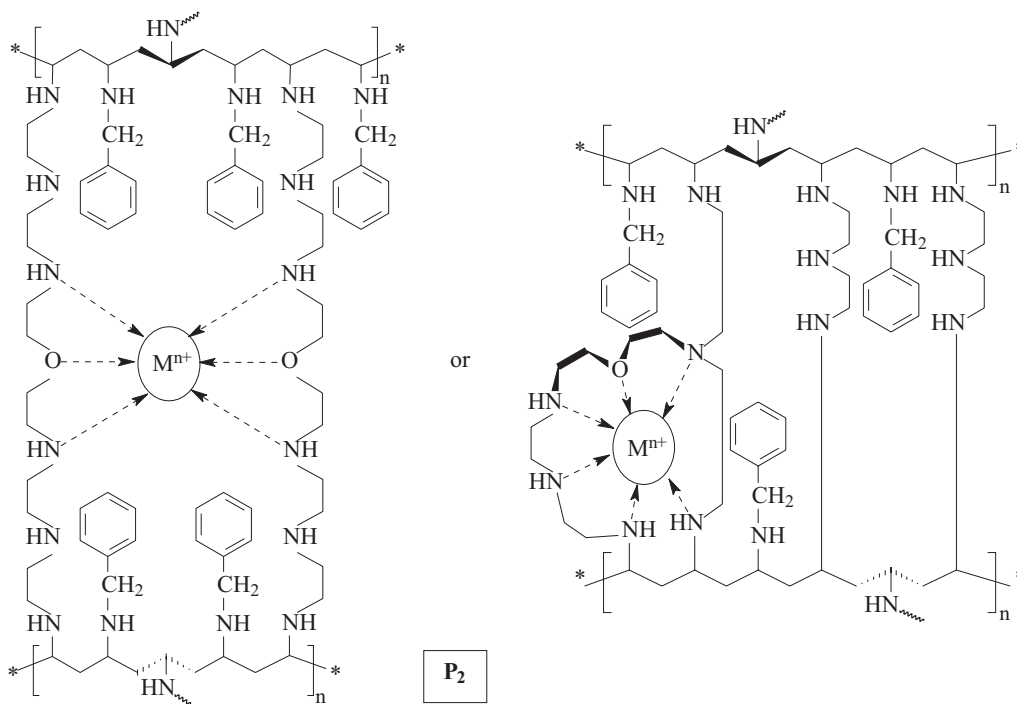
Table 4. Extraction percentages of metal cations (Cr^{3+} , Pb^{2+} , Cd^{2+} , or Co^{2+}) with modified polymers

Metal ions	Utilized salts	pH ($C = 2 \cdot 10^{-4} \text{ M}$)	E with P_0 %	E with P_1 %	E with P_2 %
Cr^{3+}	$\text{Cr}(\text{NO}_3)_3 \cdot 9 \text{ H}_2\text{O}$	3.5	0	45.00 ± 0.23	96.65 ± 0.79
Cd^{2+}	$\text{CdCl}_2 \cdot \text{H}_2\text{O}$	4.0	0	97.20 ± 0.41	94.85 ± 0.67
Pb^{2+}	$\text{Pb}(\text{NO}_3)_2$	3.7	0	98.00 ± 0.62	90.30 ± 0.80
Co^{2+}	$\text{CoCl}_2 \cdot 6 \text{ H}_2\text{O}$	4.5	0	73.50 ± 1.13	65.10 ± 1.23

Complexation with M^{2+} (Pb^{2+} , Cd^{2+} , and Co^{2+}) proved to be the best for P_1 given that the extraction percentages were 98, 97.2 and 73.5 % respectively for Pb^{2+} , Cd^{2+} , and Co^{2+} . These results can be explained by the compatibility between the size of the metal ion and the size of the complexing cavity and the type of hetero-atom ligands (oxygen and nitrogen atoms). This type of atoms (N, O) is able to fix the metal through noncovalent bonds (van der Waals bonds). According to the P_1 and P_2 structures

(Schemes A and B), there are several types of macrocyclic complexing cavities (Schemes C and D).

The retention of metal cations can also be explained by the presence of an electron-rich π system (benzene ring), this type of interaction was explained by the noncovalent cation- π interactions theory [19]. In the case of $\text{Cr}(\text{III})$, the polymer P_2 (96.65 %) is a better extractant than P_1 (45 %); P_2 accepts Cr^{3+} better, which is the least voluminous ion of those studied. Based on the hard-soft acid-base the-

**Scheme C****Scheme D**

ory, Cr(III) was classified as a hard ion, and has affinities to hard ligands which contain oxygen atoms like in P_2 cavity (Scheme D), but Cd(II) was classified as a soft ion and Pb(II) and Co(II) were classified as intermediate ions. Therefore, the chemical modification of commercial PVC is important for the extraction of heavy metals, and the chemical grafting with a bifunctional group has an important effect on extraction. In our case it improved the extraction power of P_1 to the point that the percentage of the trivalent Cr ion increased from 45 to 96.65 %. Polymeric adsorbents based on modified PVC are able to remove metal ions with great efficiency. The obtained results with these modified polymers can be compared with some published in the literature, however the reactants used are not the same. For Cd^{2+} , the extraction percentage by the modified polymer (P_1) (substituted by an aliphatic and aromatic amine) is higher (97.2 %) than the extraction percentage obtained and published in another work (22.6 %) [20].

CONCLUSIONS

The substitution reactions of commercial PVC ($M_n = 48\ 000$) by amino groups and the grafting by ether groups on the amino-PVC show the importance of chemical modification for the synthesis of long polymer chain functionalized materials. In this work these new materials containing electron-donating atoms such as nitrogen and oxygen were used as chelating agents for heavy metal extraction. The simple preparation procedure of the reactions depends on the used solvent, the temperature, and the reaction time. The simple (SPE) technique based on polymeric adsorbents proved to be an effective method for the metal ion extraction from aqueous phases [Pb(II), Cd(II), Co(II), or Cr(III)]. The extraction power of P_1 for the studied metals followed this increasing selectivity order: $Cr^{3+} \ll Co^{2+} < Cd^{2+} < Pb^{2+}$, while the modified polymer P_2 followed a different order: $Co^{2+} \ll Pb^{2+} < Cd^{2+} < Cr^{3+}$. P_1 was selective for Pb(II) and Cd(II) and the final polymer P_2 was selective for Cr(III). This work has enabled us to evaluate the extraction of heavy metals by new adsorbents based on modified PVC polymers.

ACKNOWLEDGMENT

The authors thank the Tunisian M.E.S.R.S for its financial support.

REFERENCES

- [1] Hu J., Jia X., Li C. *et al.*: *Journal of Materials Science* **2014**, 49, 2943.
<http://dx.doi.org/10.1007/s10853-013-8006-1>
- [2] Lafarge J., Kébir N., Schapman D., Burel F.: *Reactive and Functional Polymer* **2013**, 73, 1464.
<http://dx.doi.org/10.1016/j.reactfunctpolym.2013.08.001>
- [3] Kakuta N., Shimizu A., Ohkita H., Mizushima T.: *Journal of Material Cycles and Waste Management* **2009**, 11, 23.
<http://dx.doi.org/10.1007/s10163-008-0214-4>
- [4] Kameda T., Ono M., Grause G. *et al.*: *Polymer Degradation and Stability* **2009**, 94, 107.
<http://dx.doi.org/10.1016/j.polymerdegradstab.2008.10.006>
- [5] Kameda T., Ono M., Grause G. *et al.*: *Journal of Polymer Research* **2011**, 18, 945.
<http://dx.doi.org/10.1007/s10965-010-9492-3>
- [6] Yousif E., Hasan A.: *Journal of Taibah University for Science* **2015**, 9, 421.
<http://dx.doi.org/10.1016/j.jtusci.2014.09.007>
- [7] Borowska A., Sterzyński T., Piszczek K.: *Polimery* **2010**, 55, 306.
- [8] Bigot S., Louarn G., Kébir N., Burel F.: *Applied Surface Science* **2013**, 283, 411.
<http://dx.doi.org/10.1016/j.apsusc.2013.06.123>
- [9] Tooma M.A., Najim T.S., Alsahy Q.F. *et al.*: *Desalination* **2015**, 373, 58.
<http://dx.doi.org/10.1016/j.desal.2015.07.008>
- [10] Castañeda-Facio A., Benavides R., Martínez-Pardo M.E.: *Radiation Physics and Chemistry* **2014**, 97, 75.
<http://dx.doi.org/10.1016/j.radphyschem.2013.11.004>
- [11] Kameda T., Ono M., Grause G., Mizoguchi T., Yoshioka T.: *Materials Chemistry and Physics* **2009**, 118, 362.
<http://dx.doi.org/10.1016/j.matchemphys.2009.07.066>
- [12] Kameda T., Fukuda Y., Grause G., Yoshioka T.: *Journal of Applied Polymer Science* **2010**, 116, 36.
<http://dx.doi.org/10.1002/app.31452>
- [13] Lăzăroaie C., Rusen E., Mărculescu B. *et al.*: *UPB Scientific Bulletin, Series B: Chemistry and Materials Science* **2010**, 72, 127.
- [14] Moulay S.: *Progress in Polymer Science* **2010**, 35, 303.
<http://dx.doi.org/10.1016/j.progpolymsci.2009.12.001>
- [15] Lin S., Juang R.: *Journal of Environmental Management* **2009**, 90, 1336.
<http://dx.doi.org/10.1016/j.jenvman.2008.09.003>
- [16] Bolong N., Ismail A.F., Salim M.R., Matsuura T.: *Desalination* **2009**, 239, 229.
<http://dx.doi.org/10.1016/j.desal.2008.03.020>
- [17] Bhatnagar A., Sillanpää M., Witek-Krowiak A.: *Chemical Engineering Journal* **2015**, 270, 244.
[http://dx.doi.org/10.1016/S1385-8947\(15\)00412-X](http://dx.doi.org/10.1016/S1385-8947(15)00412-X)
- [18] Moulay S., Zeffouni Z.: *Journal of Polymer Research* **2006**, 13, 267.
<http://dx.doi.org/10.1007/s10965-005-9034-6>
- [19] Salonen L.M., Ellermann M., Diederich F.: *International Edition* **2011**, 50, 4808.
<http://dx.doi.org/10.1002/anie.201007560>
- [20] Ammari F., Meganem F.: *Turkish Journal of Chemistry* **2014**, 38, 638.
<http://dx.doi.org/10.3906/kim-1306-24>

Received 7 III 2016.