

# INVESTIGATION OF SOLIDIFICATION PROCESS AND MICROSTRUCTURE EXAMINATION OF AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> ALUMINIUM ALLOY

Grażyna Mrówka-Nowotnik, Małgorzata Wierzińska,  
Jan Sieniawski, Andrzej Nowotnik

## Summary

The main objective of this work was to examine a solidification process of AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> alloy and analyze morphology and composition of the complex microstructure of intermetallic phases in as-cast condition. To study the solidification process differential scanning calorimetry (DSC) was used. To identify intermetallics in AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> alloy optical light microscopy (LM), X-ray diffraction (XRD), scanning (SEM) and transmission (TEM) electron microscope and were used. The results show that the as-cast microstructure of AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> alloy after slow solidification at a cooling rate 5°/min, consisted: dendrites of  $\alpha$ -Al and intermetallic phases Al<sub>7</sub>Cu<sub>4</sub>Ni, Al<sub>6</sub>Fe, S-Al<sub>2</sub>CuMg, and Al<sub>3</sub>(CuFeNi)<sub>2</sub> and Al<sub>2</sub>Cu.

**Keywords:** aluminium alloys, solidification, microstructure, intermetallic phases

## Analiza procesu krystalizacji i kształtowania mikrostruktury stopu aluminium AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub>

### Streszczenie

Prowadzono analizę procesu krystalizacji oraz składu chemicznego i morfologii składników fazowych mikrostruktury stopu AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> w stanie lanym. W analizie procesu krystalizacji stopu stosowano metodę różnicowej kalorymetrii skaningowej (DSC). Identyfikację składników fazowych mikrostruktury stopu AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> prowadzono metodami mikroskopii świetlnej (LM), elektronowej: skaningowej (SEM) i transmisyjnej (TEM) oraz dyfrakcji rentgenowskiej (XRD). Analiza uzyskanych wyników badań pozwoliła ustalić, że mikrostruktura stopu AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub>, kształtowana w procesie krystalizacji z małą prędkością chłodzenia 5°C/min, składa się z dendrytów roztworu stałego  $\alpha$ -Al oraz wydzieleni faz międzymetalicznych: Al<sub>7</sub>Cu<sub>4</sub>Ni, Al<sub>6</sub>Fe, S-Al<sub>2</sub>CuMg, Al<sub>3</sub>(CuFeNi)<sub>2</sub> i Al<sub>2</sub>Cu.

**Słowa kluczowe:** stopy aluminium, krystalizacja

## 1. Introduction

Al-Cu-Ni-Mg aluminium alloys due to their excellent properties have a widespread application, especially in the aircraft, marine structures and automotive industry [1-4]. The main alloyin elements – Cu, Ni and Mg, partly dissolve in the primary  $\alpha$ -Al matrix, and to some amount present in the form of intermetallic phases. A range of different intermetallic phases may form during

Address: Prof. Jan SIENIAWSKI, Grażyna MRÓWKA-NOWOTNIK, DSc Eng., Małgorzata WIERZBIŃSKA, PhD Eng., Andrzej NOWOTNIK, PhD Eng., Rzeszow University of Technology, Department of Materials Science, 2 W. Pola St., 35-959 Rzeszów, Phone (+48, 0-17) 865 36 46, Fax (+48, 0-17) 854 48 32, e-mail: mrowka@prz.edu.pl

solidification, depending upon the overall alloy composition and crystallization condition. Their relative volume fraction, chemical composition and morphology exert significant influence on a technological properties of the alloys [1, 5-10]. In the aluminium alloys besides the alloying elements, transition metals such as Fe, Mn and Cr are always present. Even small amount of these impurities causes the formation of a new phase component [1, 4-10]. These phases are the consequence of equilibrium and nonequilibrium reactions occurred during casting of aluminium alloy. It worth to mention that good interpretation of microstructure relies on heaving a complete history of the samples for analysis. Therefore, the particle characterization is essential not only for choosing the best processing routes, but also for designing the optimized alloy composition.

## 2. Experimental procedure

The investigation was carried out on the AlCu4Ni2Mg2 casting aluminium alloy (composition: 4.3% Cu, 2.1% Ni, 1.5% Mg, 0.3% Zn, 0.1% Fe, 0.1% Si, Al-ball). The microstructure of examined alloy was observed using an optical microscope - Nikon 300, scanning electron microscope (SEM) HITACHI S-3400, and the transmission electron microscopes (TEM) Tesla BS-540 and Jeol-2100. The intermetallic particles from investigated AlCu4Ni2Mg2 alloy were extracted chemically in phenol [11-12]. The extracted powder was analyzed by using X-ray to determine the exact phase composition of the alloy. The X-ray diffraction analysis of the powder was performed using ARL-XTR'a diffractometer – Cu K $\alpha$  radiation at 40kV. DSC measurements were performed using a SETARAM Setsys Evolution 1200 with a sample weight of approximately 80-90 mg. Temperature scans were made from room temperature ~25°C to 800°C at constants heating rates of 5°C/min in a dynamic argon atmosphere. The heat effects associated with the transformation (dissolution/precipitation) reactions were obtained by subtracting a super purity Al baseline run and recorded.

## 3. Results and discussion

DSC curves obtained by heating (Fig. 1a) and cooling (Fig. 1b) as-cast specimens of the examined AlCu4Ni2Mg2 alloy are shown in Fig. 1. DSC curves demonstrate precisely each reactions during heating and solidification process of as-cast AlCu4Ni2Mg2 alloy. One can see from the figures that during cooling the reactions occurred at lower temperatures (Fig. 1b) compared to the values recorded during heating of the same alloy (Fig. 1a). The solidification process of this alloy is quite complex (Fig. 1) and starts from formation of aluminum reach ( $\alpha$ -Al) dendrites and Al<sub>6</sub>Fe phase. Possible reactions (the exact value of temperature) which followed during solidification of AlCu4Ni2Mg2 alloy obtained during DSC investigation are presented in Tab. 1.

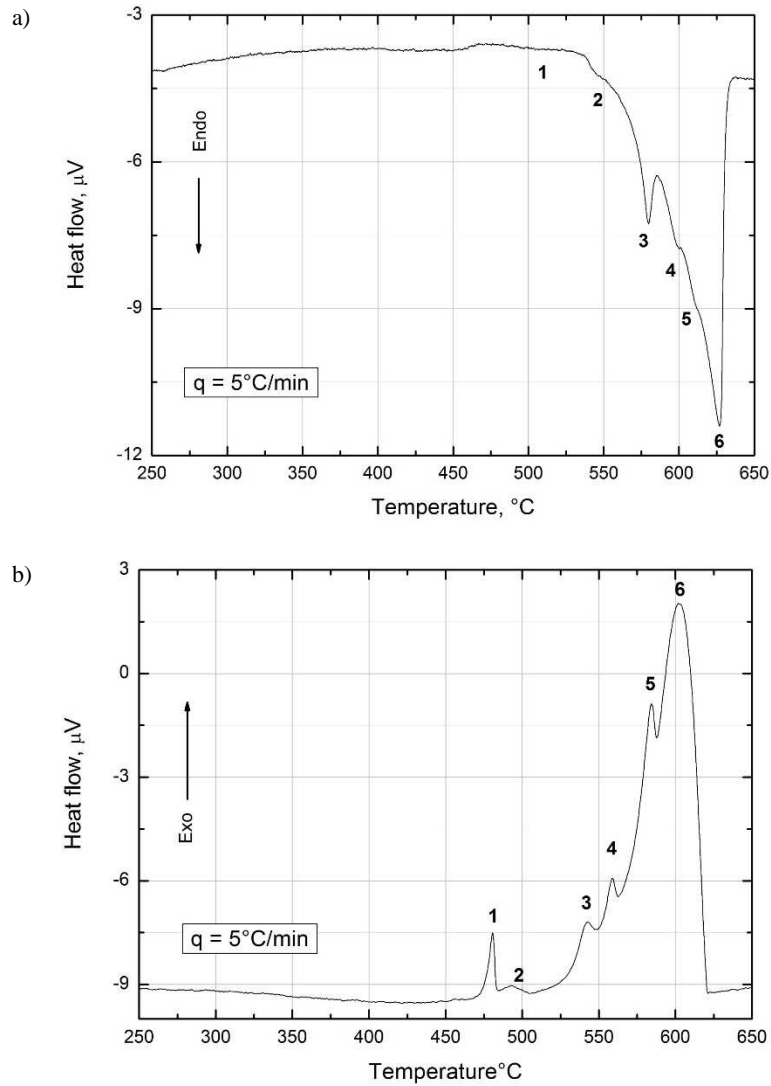


Fig. 1. DSC thermograms obtained during a) heating and b) cooling at a rate of  $5^{\circ}\text{C}/\text{min}$

Aluminum rich ( $\alpha\text{-Al}$ ) dendrites are formed at the beginning of solidification process. The addition of alloying elements to the alloys (Ni, Cu, Mg) as well as impurities (eg. Fe) changes the solidification path and reaction products. Therefore, as-cast microstructure of the tested alloy exhibits the appearance of mixture of intermetallic phases (Fig. 2a, b).

Table 1. Possible solidification reactions during nonequilibrium conditions in investigated AlCu4Ni2Mg2 alloy, at a heating rate 5°C/min

Possible reactions	Temperature, °C
$L \rightarrow (Al) + Al_6Fe$	612
$L \rightarrow (Al) + Al_4CuMg$	584
$L \rightarrow (Al) + Al_2Cu + Al_2CuMg$	558
$L \rightarrow (Al) + Al_2Cu + Al_7Cu_4Ni$	542
$L \rightarrow (Al) + Al_2Cu + Al_2CuMg + Al_3(CuFeNi)_2$	493
Solidus	480

The analyzed microstructure in as-cast state (Fig. 2) contains of primary aluminium dendrites and substantial amount of different intermetallic phases constituents varied in shape (i.e.: sphere-like, complex rod-like and ellipse-like), size and distribution. They are located at the grain boundaries of  $\alpha$ -Al and form dendrites network structure (Fig. 2). This alloy besides the eutectic phases and primary intermetallics contains a certain amount of the fine needle shaped particles of strengthening phases located in the boundary zone of the dendritic network structure (Fig. 2).

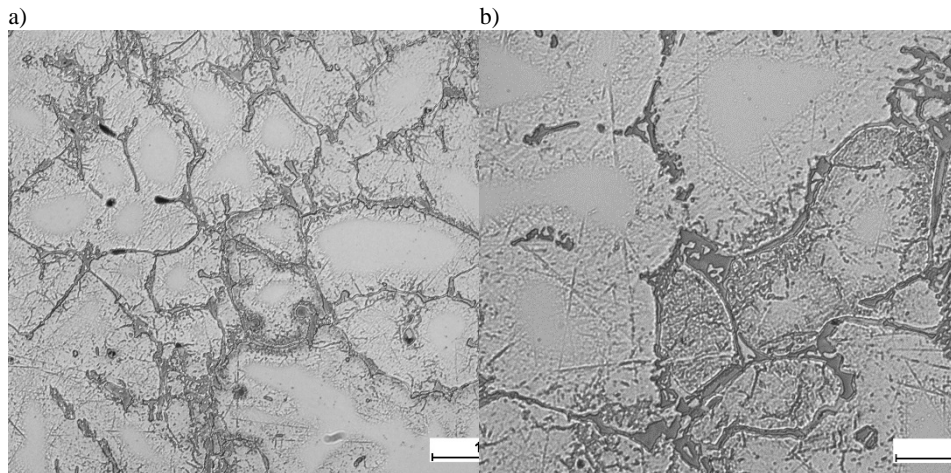


Fig. 2. The microstructure of AlCu4Ni2Mg2 alloy in as-cast state

In order to identify the intermetallic phases in the examined alloy, series of SEM observation and distribution maps were performed for the elements line Mg-K, Al-K, Fe-K, Ni-K, Cu-K (Fig. 3). The maximum pixel spectrum clearly shows the presence of Ni and Cu in the scanned microstructure. As seen in the elemental

maps in Fig. 3, the regions enriched in Ni and Cu correspond to the formation of large, irregular eutectic type precipitates phases observed in Fig. 2.

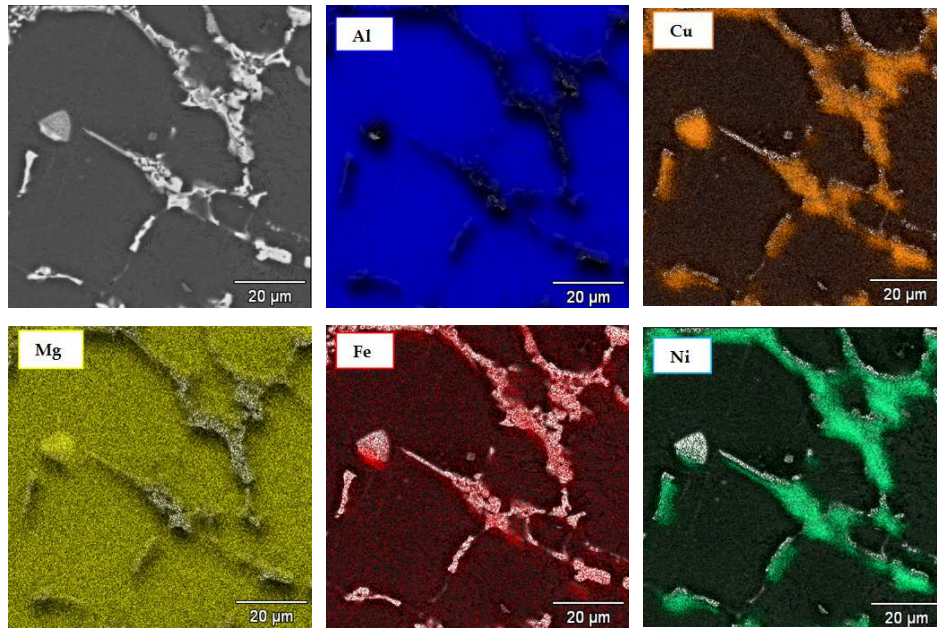


Fig. 3. SEM image of the AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> alloy and corresponding elemental maps of: Al, Mg, Fe, Ni and Cu

Figure 4 shows scanning electron micrographs of the particles extracted from the as-cast AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> alloy by using the phenolic dissolution technique. The EDS analysis (Tab. 2) performed on the extracted phases present in microstructure of the alloy revealed, that the phase with complex morphology is the Al<sub>7</sub>Cu<sub>4</sub>Ni one (Fig. 4a, c), whereas the plate-like is Al<sub>3</sub>(CuFeNi)<sub>2</sub> (Fig. 4b, d).

The phenol extraction method was successfully applied to the examined alloy in the as-cast condition. However, the problem we came across whilst extracting a very fine particles. The residue is separated by centrifuging and since some of the particles are very fine and available sieves are having too big outlet holes there is no chance prevents them from being flowing out from a solution. Therefore transmission electron microscopy technique TEM observation (Fig. 5) and X-ray diffraction analysis (Fig. 6) of samples of the examined AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> alloy were used in order to compare and confirm present results.

TEM micrographs and electron diffraction patterns analysis proved that the dispersed precipitates showed in Fig. 2 are the particles of intermetallic phases S-Al<sub>2</sub>CuMg (Fig. 5).

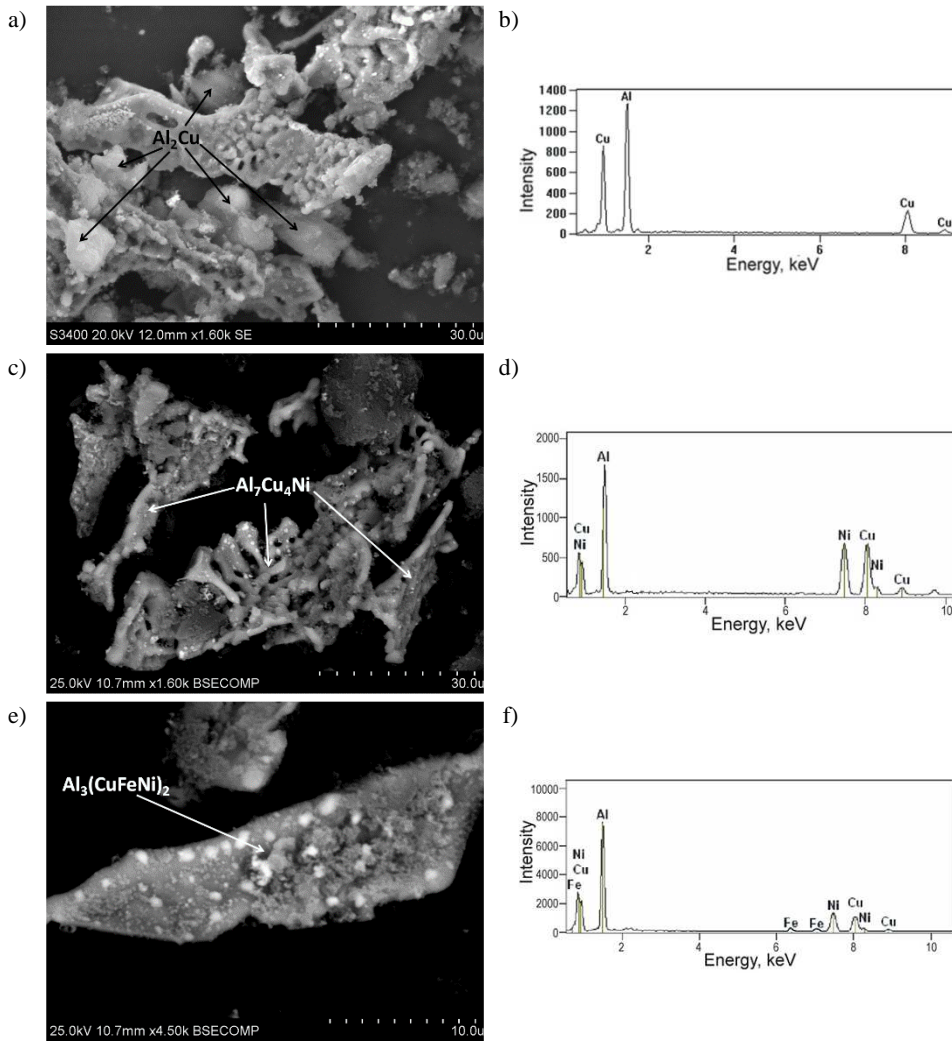


Fig. 4. SEM micrographs of the particles extracted from the AlCu4Ni2Mg2 alloy along with EDS spectra:  $\text{Al}_2\text{Cu}$  (a,b)  $\text{Al}_7\text{Cu}_4\text{Ni}$  (c,d) and  $\text{Al}_3(\text{CuFeNi})_2$  (e,f)

The results of the SEM/EDS analysis of the particles extracted with boiling phenol from AlCu4Ni2Mg2 alloy were compared with X-ray diffraction pattern (Fig. 6). The observed peaks confirmed SEM and TEM results. The majority of the peaks were from  $\text{Al}_7\text{Cu}_4\text{Ni}$ ,  $\text{Al}_6\text{Fe}$ , S- $\text{Al}_2\text{CuMg}$ , and  $\text{Al}_3(\text{CuFeNi})_2$ .

Table 2. The chemical composition of the intermetallic phases in the AlCu4Ni2Mg2 alloy

No. of analyzed particles	Suggested type of phases	Chemical composition of intermetallic phases, (%at)			References
		Cu	Ni	Fe	
14	Al <sub>2</sub> Cu	47.7÷51.9 52.5	-	-	This work [9]
25	Al <sub>7</sub> Cu <sub>4</sub> Ni	29.7÷45.2 38.7÷50.7 34.33	14.2÷22.6 11.8÷22.2 18.08	-	This work [10] [8]
30	Al <sub>3</sub> (CuFeNi) <sub>2</sub>	10.5÷19.3 9÷15	17.1÷20.5 18÷22	7.2÷9.5 8÷10	This work [9]


a)



b)



c)

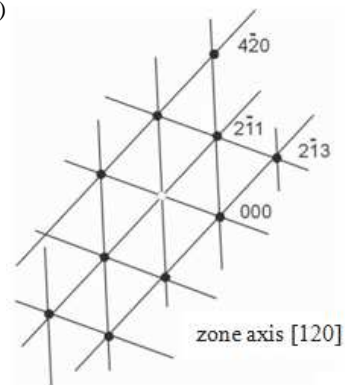Fig. 5. TEM micrograph of AlCu<sub>4</sub>Ni<sub>2</sub>Mg<sub>2</sub> alloy showing the precipitate of the S-Al<sub>2</sub>CuMg phase (a), and corresponding electron diffraction pattern (b, c)

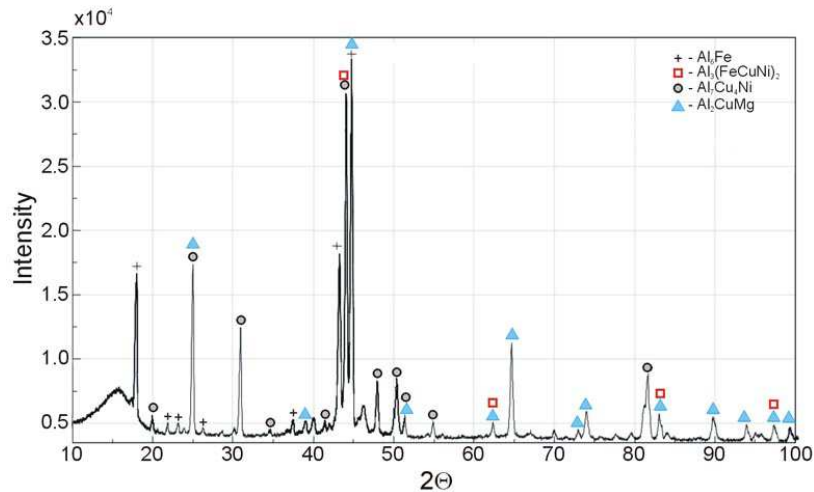


Fig. 6. The X-ray diffraction from the particles extracted from AlCu4Ni2Mg2 alloy

#### 4. Conclusions

The solidification process of investigated AlCu4Ni2Mg2 aluminium alloy is quite complex. DSC curves obtained by heating and cooling as-cast specimens of the examined alloy demonstrate precisely each reactions during heating and solidification process of as-cast AlCu4Ni2Mg2 alloy:

- $L \rightarrow (Al) + Al_6Fe - 612^\circ C$
- $L \rightarrow (Al) + Al_4CuMg - 584^\circ C$
- $L \rightarrow (Al) + Al_2Cu + Al_2CuMg - 558^\circ C$
- $L \rightarrow (Al) + Al_2Cu + Al_7Cu_4Ni - 542^\circ C$
- $L \rightarrow (Al) + Al_2Cu + Al_2CuMg + Al_3(CuFeNi)_2 - 493^\circ C$
- Solidus –  $480^\circ C$

Microstructure examination by different technique (LM, SEM/EDS, TEM, XRD) of as-cast alloy cooling with constants heating rates of  $5^\circ C$  during solidification confirmed DSC results. The analyzed microstructure in as-cast state contains of primary aluminium dendrites and substantial amount of different intermetallic phases constituents  $Al_7Cu_4Ni$ ,  $Al_6Fe$ ,  $S-Al_2CuMg$ , and  $Al_3(CuFeNi)_2$ . varied in shape (i.e.: sphere-like, complex rod-like and ellipse-like), size and distribution located at the grain boundaries of  $\alpha-Al$ . This alloy also contain some amount of the fine needle shaped particles of strengthening  $Al_2Cu$  and  $S-Al_2CuMg$  phases located in the boundary zone.



### References

- [1] S.D. MACKENZIE, G.E. TOTTEN: Analytical characterization of aluminium, steel, and superalloys. Taylor & Francis Group, Boca Raton 2006.
- [2] Aluminium Handbook. Vol.1 Fundamentals and materials. Aluminium-Verlag Marketing & Kommunikation GmbH, Düsseldorf 1999.
- [3] F. KING: Aluminium and its alloys. John Wiley & Sons, New York-Chichester-Brisbane-Toronto 1987.
- [4] L.F. MONDOLFO: Aluminium Alloys: Structure and Properties. Butterworths, London-Boston 1976.
- [5] G. GUSTAFSSON, T. THORVALDSSON, G.L. DUNLOP: The influence of Fe and Cr on the microstructure of cast Al-Mg-Si alloys. *Metallurgical and Materials Transactions*, **17A**(1986), 45-52.
- [6] G. MRÓWKA-NOWOTNIK, J. SIENIAWSKI: Intermetallic phase transformations during homogenisation of 6066 aluminium alloy. *Solid State Phenomena*, **186**(2012), 319-322.
- [7] G. MRÓWKA-NOWOTNIK, J. SIENIAWSKI: Analysis of intermetallic phases in 2024 aluminium alloy. *Solid State Phenomena*, **197**(2013), 238-243.
- [8] L. BÄCKERUD, G. CHAI: Solidification characteristics of aluminum alloys 3. American Foundry Society, Des Plaines, Illinois 1992.
- [9] N.A. BELOV, A.A. AKSENOV, D.G. ESKIN: Iron in aluminium alloys. Taylor & Francis Inc, New York 2002.
- [10] N.A. BELOV, D.G. ESKIN, N.N. AVXENTIEVA: Constituent phase diagrams of the Al-Cu-Fe-Mg-Ni-Si system and their application to the analysis of aluminium piston alloys. *Acta Mater.*, **53**(2005), 4709-4722.
- [11] K. SATO, I. IZUMI: Application of the technique for isolating and analysis intermetallic compounds to commercial aluminium alloys. *Journal of Japan Institute of Light Metals*, **35**(1985), 647-649.
- [12] A.K. GUPTA, P.H. MAROIS, D.J. LLOYD: Review of the techniques for the extraction of second-phase particles from aluminium alloys. *Materials Characterization*, **37**(1996), 66-80.

*Received in December 2015*